

*See also
Report #10020*

R 512

Technical Report

WINDOWS FOR EXTERNAL OR INTERNAL
HYDROSTATIC PRESSURE VESSELS

Part I — Conical Acrylic Windows Under
Short-Term Pressure Application

January 1967

NAVAL FACILITIES ENGINEERING COMMAND



U. S. NAVAL CIVIL ENGINEERING LABORATORY
Port Hueneme, California

Distribution of this document is unlimited.


19960410 063

DTIC QUALITY INSPECTED 1

DEPARTMENT OF DEFENSE
PLASTICS TECHNICAL EVALUATION CENTER
PICATINNY ARSENAL, DOVER, N. J.

g
PLASTICS
96/13

DISCLAIMER NOTICE

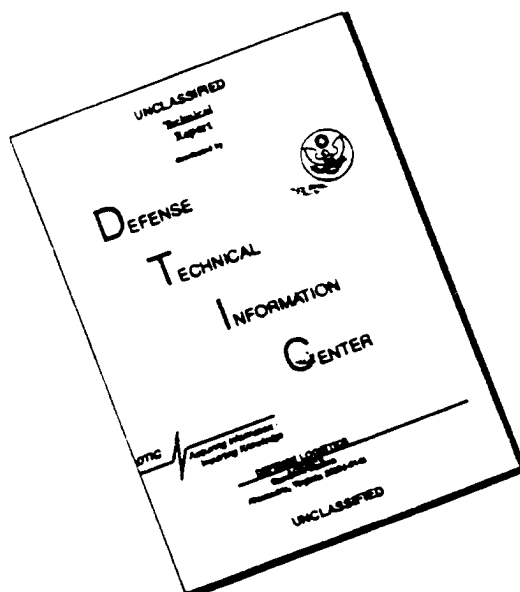

THIS DOCUMENT IS BEST
QUALITY AVAILABLE. THE COPY
FURNISHED TO DTIC CONTAINED
A SIGNIFICANT NUMBER OF
PAGES WHICH DO NOT
REPRODUCE LEGIBLY.

WINDOWS FOR EXTERNAL OR INTERNAL HYDROSTATIC PRESSURE VESSELS
PART I - CONICAL ACRYLIC WINDOWS UNDER SHORT-TERM PRESSURE APPLICATION

Technical Report R-512

Y-F015-01-07-001

by

J. D. Stachiw and K. O. Gray

ABSTRACT

Conical acrylic windows for fixed ocean-floor structures were placed under short-term loading (pressurization from zero to failure at a fixed rate). The windows, of different thicknesses and different included conical angles, were subjected to various applied pressures, and their subsequent behavior was studied.

Acrylic windows, in the form of truncated cones with included angles of 30°, 60°, 90°, 120°, and 150°, were tested to destruction at ambient room temperature by applying hydrostatic pressure to the base of the truncated cone at a continuous rate of 650 psi/min. The pressure at which the windows failed and the magnitude of displacement through the window mounting at different pressure levels were recorded. The ultimate strength of the conical windows (denoted by the critical pressure at which actual failure occurred) was found to be related both to thickness and included conical angle.

Graphs are presented defining the relationships of critical pressure versus thickness-to-diameter ratio, and pressure versus magnitude of displacement for the windows.

Nondimensional scaling factors for critical pressure and displacement applicable to large-diameter windows are discussed and presented in graphic form.

This initial study produced design criteria for conical acrylic windows for any ocean depth under conditions of short-term loading. These criteria may be applied to windows in either an internal pressure vessel used to contain high pressures, and thus simulate the ocean environment, or an external one used to resist high pressures, such as deep submergence structures in the ocean.

Distribution of this document is unlimited.

Copies available at the Clearinghouse (CFSTI) \$3.00

The Laboratory invites comment on this report, particularly on the results obtained by those who have applied the information

CONTENTS

| | Page |
|---|------|
| INTRODUCTION | 1 |
| BACKGROUND INFORMATION | 1 |
| DESIGN OF EXPERIMENT | 2 |
| Window Test Specimens | 3 |
| Window Specimen Holders | 3 |
| Instrumentation | 7 |
| TEST PROCEDURE | 7 |
| EXPERIMENTAL DATA | 12 |
| Scatter of Data | 12 |
| Size of Sample Group | 12 |
| Effects of Temperature | 12 |
| Subsidiary Experiments | 12 |
| Applicability of 1-Inch-Diameter Window Test Data to Windows of Larger Sizes | 12 |
| Evaluation of Other Window Mounting Flange Configurations | 12 |
| One-Inch-Diameter, 30° Conical Windows | 15 |
| One-Inch-Diameter, 60° Conical Windows | 15 |
| One-Inch-Diameter, 90° Conical Windows | 15 |
| One-Inch-Diameter, 120° Conical Windows | 15 |
| One-Inch-Diameter, 150° Conical Windows | 20 |
| Two-Inch-Diameter, 30° Conical Windows | 20 |
| Four-and-One-Half-Inch-Diameter, 60° Conical Windows | 20 |
| Eight-Inch-Diameter, 90° Conical Windows | 20 |
| FINDINGS | 26 |
| CONCLUSIONS | 29 |
| FUTURE STUDIES | 30 |
| APPENDIXES | |
| A - Physical Properties of Grade G Plexiglas | 31 |
| B - Modes of Failure of Conical Acrylic Windows | 32 |
| C - Statistical Evaluation of the Size of the Sample Groups | 60 |
| D - Temperature Influence Evaluation Tests | 61 |
| E - Applicability of 1-Inch-Diameter Window Test Data to Windows of Larger Sizes | 62 |

| | Page |
|---|------|
| F - Evaluation of Other Window Mounting Flange Configurations | 65 |
| G - Data From the Testing of Conical Acrylic Windows | 67 |
| REFERENCES | 100 |

INTRODUCTION

The Naval Facilities Engineering Command* is responsible for the construction and maintenance of underwater structures attached to the ocean floor. Such structures may include instrumented or manned underwater surveillance or observation posts that will rely, at least in part, on visual observation and the transmitting and receiving of electromagnetic radiation through "non-opaque" hull areas for the performance of their mission. Windows of certain types have been employed for these purposes on research submarines, and have been found to be of practical value especially for visual and sonic (sonar) observation in hydrospace. Similar windows will be utilized on permanent ocean floor installations. The published data on the strength of underwater optical-viewing windows used on submarines is very meager,^{1,2,3} and formulas for its calculation are lacking. Furthermore, the operational requirements of permanent underwater installations are sufficiently different from those of submarines to make most of the existing data inapplicable to the deep submergence structures. For these reasons, a study has been undertaken at the Deep Ocean Laboratory of the Naval Civil Engineering Laboratory (NCEL) to generate information for the design of feasible underwater windows. This information, besides satisfying the primary underwater window design requirements, will also prove valuable in the design and operation of windows in internal pressure vessels used for simulation of deep ocean environments.

The performance of underwater windows is influenced by such major factors as the duration of loading or application of pressure; temperature; the thickness, shape, and type of the window material; and the number of pressure cycles involved. Since all these variables must be considered in combination, the whole investigation must proceed in phases, with the factors evaluated in one combination at a time. The phase of study described in this report was planned to determine the relationship between the shape, thickness, and critical pressure of truncated-cone-shaped acrylic plastic windows under short-term loading at room temperature.

BACKGROUND INFORMATION

Windows for underwater applications where high pressures are encountered have been of conical shape since the beginning of deep submergence research. The first scientist to explore this field, Auguste Piccard,¹ not only introduced the conical window shape but also the use of acrylic plastic for windows in deep submergence structures. The conical shape was chosen because of its wide field of vision, as well as its wedging and self-sealing behavior under high pressure. Acrylic plastic, introduced for the underwater application by Professor Piccard in 1939, is still the primary material used for underwater high-pressure windows because of its low cost, wide availability, and excellent optical properties. It is readily bonded, permitting windows of any thickness to be built up by lamination of sheets, and is impact-resistant enough to render unnecessary additional protective covers except for windows employed on combat missions. The long, excellent performance record of acrylic plastic for underwater windows prompted the decision to investigate it first, ahead of other, recently developed optically transparent materials.

Acrylic plastic, like most plastics, deforms with time under sustained loading. For this reason, an acrylic window subjected to sustained pressure loading will ultimately fail at a much lower pressure than if it were pressurized rapidly till failure occurs. Thus, the pressure rating of a window is affected by the duration of load application. In addition, if the window is subjected to more than one pressure cycle of a given duration, its pressure rating will change accordingly. Therefore, to obtain complete design information for acrylic windows, it is necessary to subject them to different types of loadings. However, a standard must be established to which strengths can be compared. Since this has not been done in the course of underwater window investigation to date, a fundamental purpose of the initial phase

* Formerly Bureau of Yards and Docks.

of the present study was to set such a standard. The one selected around which to compile basic data was the failure of windows under short-term pressure application at an ambient temperature in the approximate range of 60° to 70°F. The short-term loading, which denotes not a specific time but pressurization from zero to failure (or critical pressure) at a fixed rate, here was to be applied at the rate of 650 psi/min.

Since the compressive and tensile strength of acrylic material decreases with an increase in temperature, it was considered wise to conduct experiments at prevailing room temperature of 60° to 70°F, for this would be a more severe test than if the pressurizing medium, water, were around 40°F, the temperature of most ocean depths. Also, this temperature range would facilitate the use of conical acrylic windows in internal pressure vessels, where the water employed is likely to be at room temperature.

DESIGN OF EXPERIMENT

The experimental study had two objectives: to determine the short-term pressure strength of a series of windows of different conical angles and thicknesses, and to provide experimental data for future analytical studies dealing with the strength of such windows. To implement the latter objective, the windows were designed not only with a 90° included conical angle, the one customarily used in all present underwater deep submergence windows, but also with 30°, 60°, 120° and 150° included angles. It was felt that by varying the angle from 30° to 150°, sufficient perturbation of the angle parameter was introduced into the experiment to permit the evaluation of its influence on window strength. The thickness-to-diameter (t/D) ratio was varied for the same reason. This ratio is a single, computationally useful nondimensional term combining the two other parameters besides cone angle which determine the critical pressure of conical windows: the thickness, t, of the truncated cone, and the minor diameter, D, of the cone. Sufficient perturbation was assured for the thickness-to-diameter ratio by varying it from 0.125 to 1.0. (Although the t/D ratios are herein expressed in decimal form, sometimes to three places, these values are actually the decimal equivalents of nominal fractional values.)

To obtain true experimental response from the windows whose t/D ratios and conical angles were varied, special effort was made to hold both the temperature and the rate of pressurization constant. Furthermore, the window material and metallic flanges for mounting test specimens were kept the same for each series of experiments, in order to prevent excessive variations in both window material strength and flange rigidity.

A summary of the experiment, reflecting the various categories of the complete test data found in Appendix G, is presented in Table 1.

Table 1. Summary of Experimental Work

| Window Diameter ^{1/} (in.) | Mounting Flange Type | Included Conical Angle (deg) | t/D Ratio (Nominal) | Remarks |
|--|----------------------|------------------------------|--|---|
| 1 | I | 30, 60, 90, 120, 150 | 0.125, 0.25, 0.375, 0.5, 0.625, 0.75, 0.875, 1.0 | Short-term critical pressure and displacement tests |
| 1 | I | 30 | 0.5 | Low-temperature-effect tests |
| 1 | II | 30 | 1.0 | Type II flange effect tests |
| 2 | I | 30 | 0.125, 0.25, 0.5 | Window t/D ratio scaling factor validation tests |
| 4-1/2 | I | 60 | 0.125, 0.25, 0.5 | Window t/D ratio scaling factor validation tests |
| 8 | I | 90 | 0.5 | Window t/D ratio scaling factor validation tests |

^{1/} Minor diameter of the truncated acrylic cone.

Window Test Specimens

The conical window test specimens (Figure 1) were machined from acrylic plates and sheets only. The material used was commercial quality Grade G Plexiglas, the physical properties of which are described in Appendix A. This off-the-shelf acrylic material was chosen with the designer in mind, permitting him to specify and easily procure fairly inexpensive stock for his own experimentation or use based on data presented herein.

Since the windows were machined from commercially available sheets and plates of acrylic material, small variations were anticipated in their mechanical properties. Preliminary experiments indicated this variation in strength, together with variations in conical angle and thickness resulting from the necessary machining tolerances, caused considerable scatter of experimental values. Although such a scatter increased the experimental task, certain advantages result for the potential designer. From the range of scatter of experimentally derived critical pressures, the designer can determine what deviations of window strength may be expected when ordinary machine shop tolerances are used on Grade G Plexiglas material received from various manufacturers. Knowing what deviations to expect from the average window strengths given in this report, he will then be able to introduce an appropriate factor of safety.

Since it may often be difficult or economically impractical to provide future submarines, permanent underwater installations, or pressure vessels requiring cone-shaped acrylic windows with custom-fitted, lapped-in-place originals or replacements, this study has relied exclusively on mass-produced, interchangeable specimens. None of the windows received any further shaping or lapping in place following fabrication in the NCEL machine shop. Spot checks of the as-machined windows indicated dimensions were less than ± 30 minutes off from specified nominal angle, and ± 0.020 inch from the specified nominal thickness. The sealing surfaces of the windows were machined to a 32 rms finish, while the parallel viewing surfaces were polished to an optical finish.


Window Specimen Holders

The test specimens were mounted in metallic flanges designed to fit into the end closure of the pressure vessel (Figure 2). The pressure vessel employed for this study was the Mk-I modification of 16-inch Naval gun shells,⁴ a convenient, medium-size vessel with a useful inside diameter of 9 inches. (This diameter determined the choice of the minor diameter of 1 inch for the basic series of window test specimens, since the major diameter of the acrylic window specimens tested could reach 6-1/4 inches, and in the case of validation tests with larger diameter windows, 8 inches.)

The mounting flanges, machined from mild steel, were of sufficient thickness to withstand all but minor deformation during application of hydrostatic pressure to the window specimens. In addition to the dimensional stability offered by the rigidity of the comparatively massive flange construction, the hydrostatic loading caused by surrounding fluid under pressure also acted on the flange to minimize its expansion from the wedging action of the conical window. It can, therefore, be postulated that for all practical purposes the window flanges were rigid, and only the acrylic windows were deformed during the tests.

Mounting flanges with conical cavities of different angle sizes were employed to accommodate the range of 30° to 150° included angles of the conical window specimens. A cylindrical cavity of varying length extended beyond the conical cavity of the mounting flange, to accommodate the displaced (extruded or deflected) portion of the window resulting from pressure action. (See Figure 3.) Flanges were of two types, DOL (Deep Ocean Laboratory) Type I and DOL Type II, with a difference in configuration related chiefly to the radial restraint provided by the cavity receiving the displaced portion of the window and explained in the paragraphs which follow. In this study, the DOL Type II configuration flange was used only in a small number of tests, for exploratory purposes.

To standardize the displacement aspect of testing, all windows were machined to position the low-pressure (minor-diameter) surface flush with the small end of the conical cavity in the mounting flange. Thus, as the thickness of the windows tested varied, the high-pressure face (the one exposed to the hydrostatic pressure) extended to different elevations in the flange conical cavity. As the window moved axially under hydrostatic pressure, portions of it would protrude into the adjoining cylindrical cavity, and would not be further subjected to wedging action by the flange.

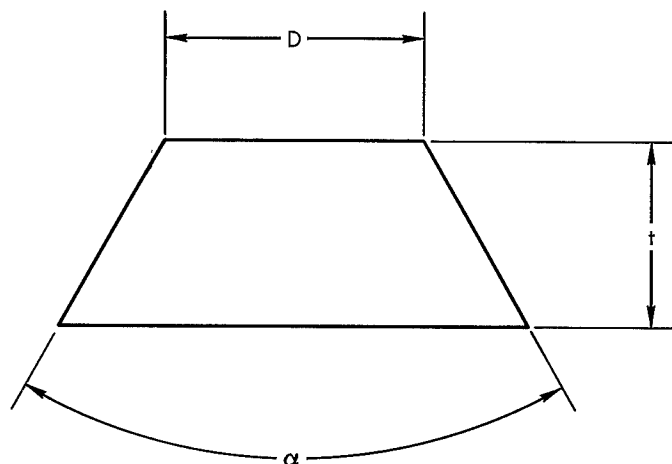

| Included Conical Angle, α ^{1/} (deg) | Window Diam, D ^{2/} (in.) | t/D Ratio (Nominal) | | | | | | | |
|---|--|--|-------|-------|-------|-------|------|-------|-----|
| | | 0.125 | 0.25 | 0.375 | 0.5 | 0.625 | 0.75 | 0.875 | 1.0 |
| | | Nominal Thickness, t (in.) ^{3/} | | | | | | | |
| 30 | 1 | 1/8 | 1/4 | 3/8 | 1/2 | 5/8 | 3/4 | 7/8 | 1.0 |
| 60 | 1 | 1/8 | 1/4 | 3/8 | 1/2 | 5/8 | - | - | - |
| 90 | 1 | 1/8 | 1/4 | 3/8 | 1/2 | 5/8 | - | - | - |
| 120 | 1 | 1/8 | 1/4 | 3/8 | 1/2 | 5/8 | - | - | - |
| 150 | 1 | 1/8 | 1/4 | 3/8 | 1/2 | 5/8 | - | - | - |
| 30 | 2 | 1/4 | 1/2 | - | 1 | - | - | - | - |
| 60 | 4-1/2 | 9/16 | 1-1/8 | - | 2-1/4 | - | - | - | - |
| 90 | 8 | - | - | - | 4 | - | - | - | - |

^{1/} Dimensional tolerance of ± 30 minutes.


^{2/} Diameter of low-pressure face (minor diameter), with tolerance of ± 0.005 inch.

^{3/} Commercial stock size, with tolerance of $\pm 10\%$.

Figure 1. Types of conical acrylic window test specimens.



Figure 2. Steel mounting flange for conical acrylic windows attached to end closure of Mk-I pressure vessel.

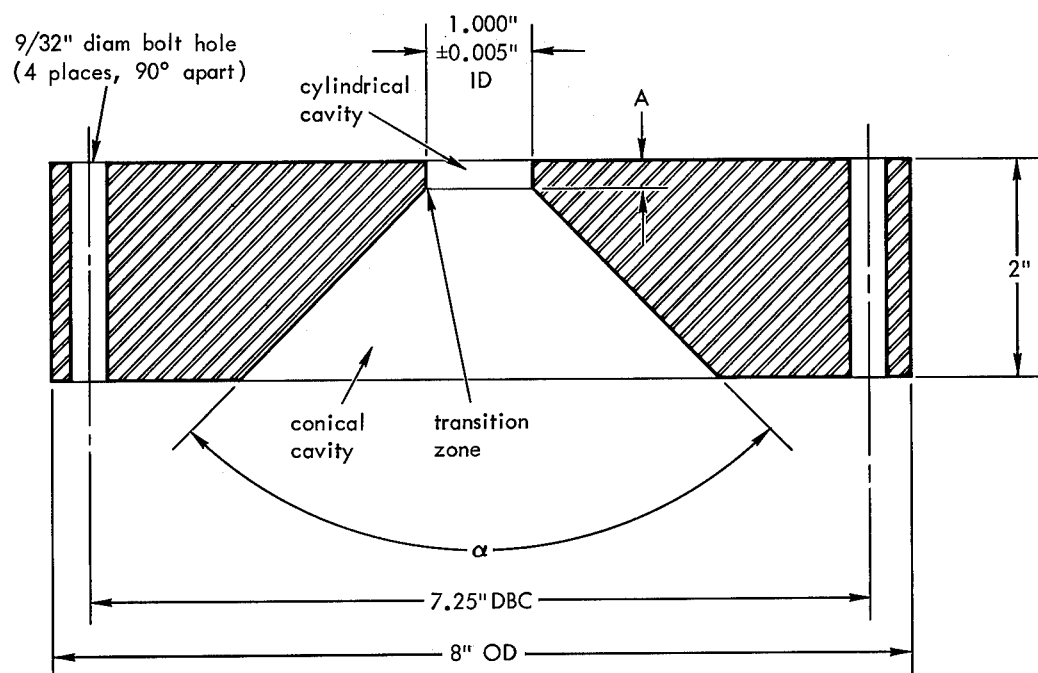

| Included Conical Angle, α ^{1/} (deg) | Cylindrical Cavity Length, A (in.) |
|---|---|
| 30 | 1/4 |
| 60 | 1/4 |
| 90 | 1/4 |
| 120 | 1/2 |
| 150 | 1-1/4 |

^{1/} Dimensional tolerance of ± 30 minutes.

Figure 3. Steel mounting flanges, DOL Type I configuration, for 1-inch-diameter conical acrylic window test specimens.

Exploratory work (Table G-11, Appendix G) indicated that continued radial support for the displaced portion of the window has a definite relationship to the window critical pressure. Therefore, each test mounting flange, though its cylindrical cavity in many cases had a length of only 0.25 inch, was backed by a flange adapter (Figure 4) with a cylindrical cavity always matching the minor diameter of the mounting flange cavity. In this way, regardless of how much a window extruded, its extruded portion was always radially restrained by a cylindrical wall, either of the flange or of the adapter. Such arrangement standardized the test conditions for window specimens whatever their thickness, conical angle, diameter, or amount of displacement under testing. The type of flange configuration assuring the displaced portion of support, whatever its length, was designated DOL Type I, and the one not providing such support, DOL Type II. (See Appendix F.) In the latter configuration, the cavity for receiving the displaced portion of the window was not cylindrical but flared sharply, and was not extended by use of a flange adapter.

Instrumentation

The instrumentation consisted of a thermometer, a pressure gage, and a displacement measuring device. The thermometer was used to measure the temperature of the water in contact with the window in the vessel; the pressure gage, the pressure of the water in the vessel; and the displacement measuring device, within 0.001 inch, the displacement of the center of the window low-pressure face as it extruded or deflected into the cylindrical cavity of the mounting. Since the displacement measuring device (Figures 5 and 6) was mechanical, no problems were encountered in zeroing or balancing it. Although more sophisticated instrumentation employing electric resistance strain gages² or photoelastic techniques³ could have been used, its potential contribution in the determination of ultimate short-term window strength was deemed insufficient to warrant consideration.

TEST PROCEDURE

The window mounting flange with the appropriate conical opening was placed on the flange adapter (Figure 4) and bolted in position. The window, to which the displacement indicator wire was already fastened by means of a small acrylic anchor piece cemented onto its low-pressure face, was liberally coated with silicone grease and inserted into the mounting flange. No retaining device was necessary, as the grease exerted enough adhesion to keep the window from falling out. Next, the mounting assembly was inserted into the end closure of the pressure vessel and locked in place. The 0.010-inch-thick steel wire connected to the window low-pressure face was then fastened to a 1-pound weight. With the wire positioned over pulleys that centered one wire end over the window and the other over a dial indicator, the weight was placed on the dial indicator rod, depressing it slightly (Figure 5). During the experiment, the weight was kept from shifting on the dial indicator rod by a plastic weight guide tube and a recess on the bottom of the weight into which the indicator rod fitted. The test setup with the displacement measuring device in position is shown in Figure 6.

To permit pressurization of the vessel, three entries were provided in the top of the vessel end closure. One was used to admit the pressurizing fluid to the vessel, one for sensing the pressure, and one to remove entrapped air and to relieve the pressure in the vessel on completion of the test. The pressure inside the vessel was monitored at all times with a 16-inch-diameter Bourdon tube-type pressure gage connected to a fitting in the end closure with 1/16-inch-outside-diameter tubing. The use of such small tubing was instrumental in reducing the severity of the hydraulic shock to the mechanism of the gage at the moment of window failure, when the pressure in the vessel was reduced from as high as 30,000 psi to 0 psi in less than 1 second. The pressurization of the vessel was accomplished by means of two air-driven pumps with a maximum pressurization capability of 30,000 psi (Figure 7).

Although different rates of pressurization were feasible, a pumping rate of 650 \pm 100 psi/min was selected as a standard. The temperature of the pressurizing medium (fresh water) and of the vessel was maintained in the general range of 60° to 70°F, although for some selected tests it was reduced to a range of 35° to 40°F. The temperature readings were recorded before and after window failure to obtain an average.

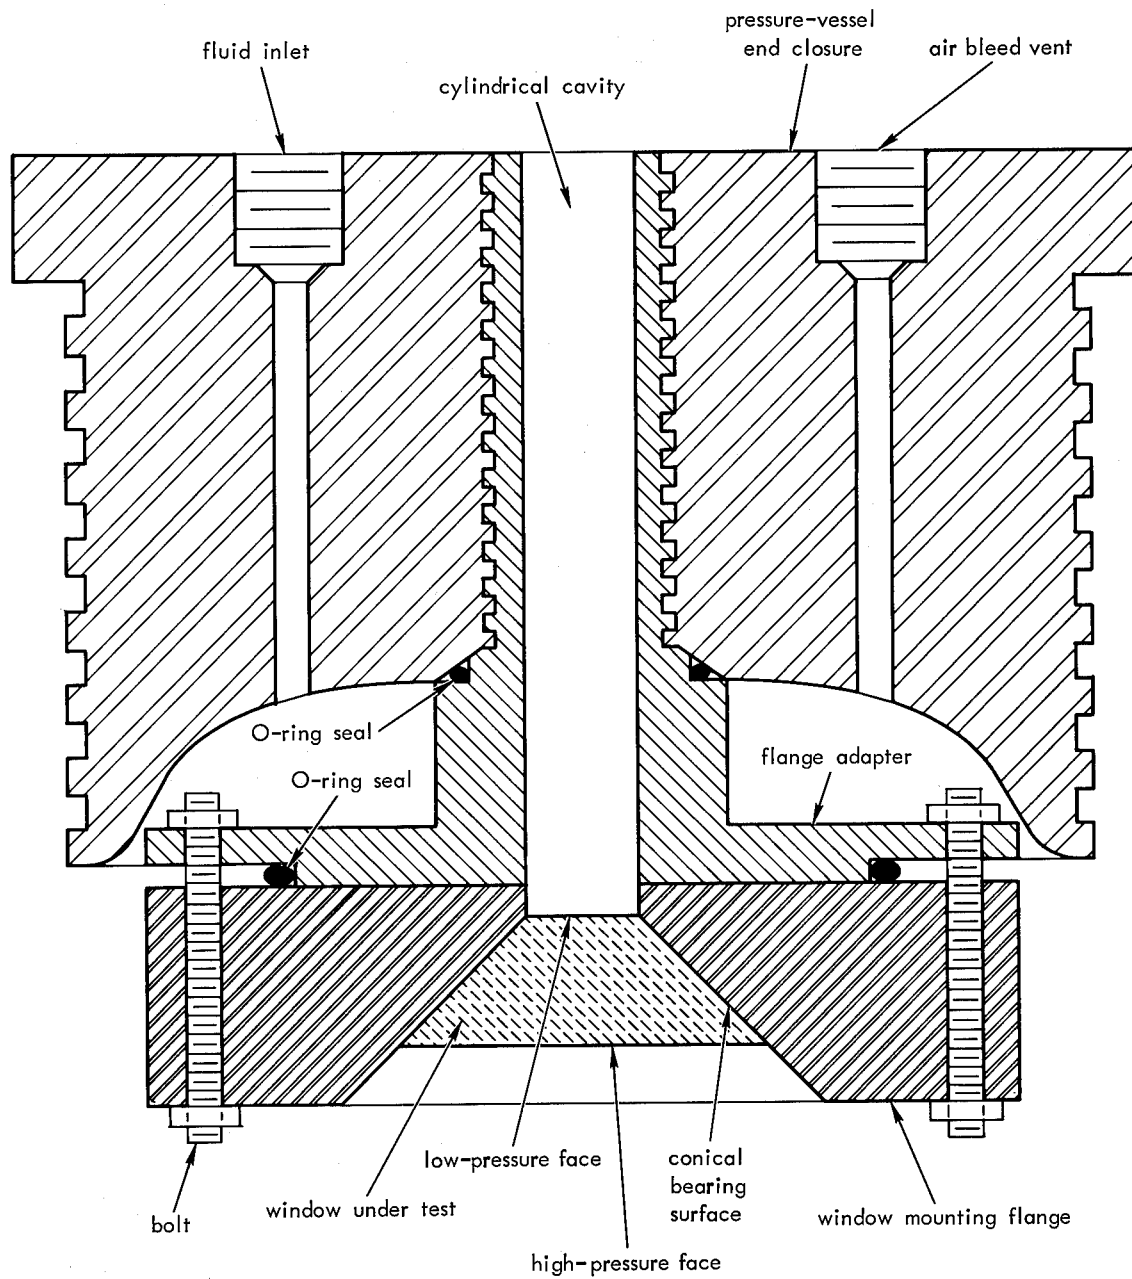


Figure 4. Flange adapter attached to DOL Type I mounting flange, with mounting assembly positioned in end closure of pressure vessel.

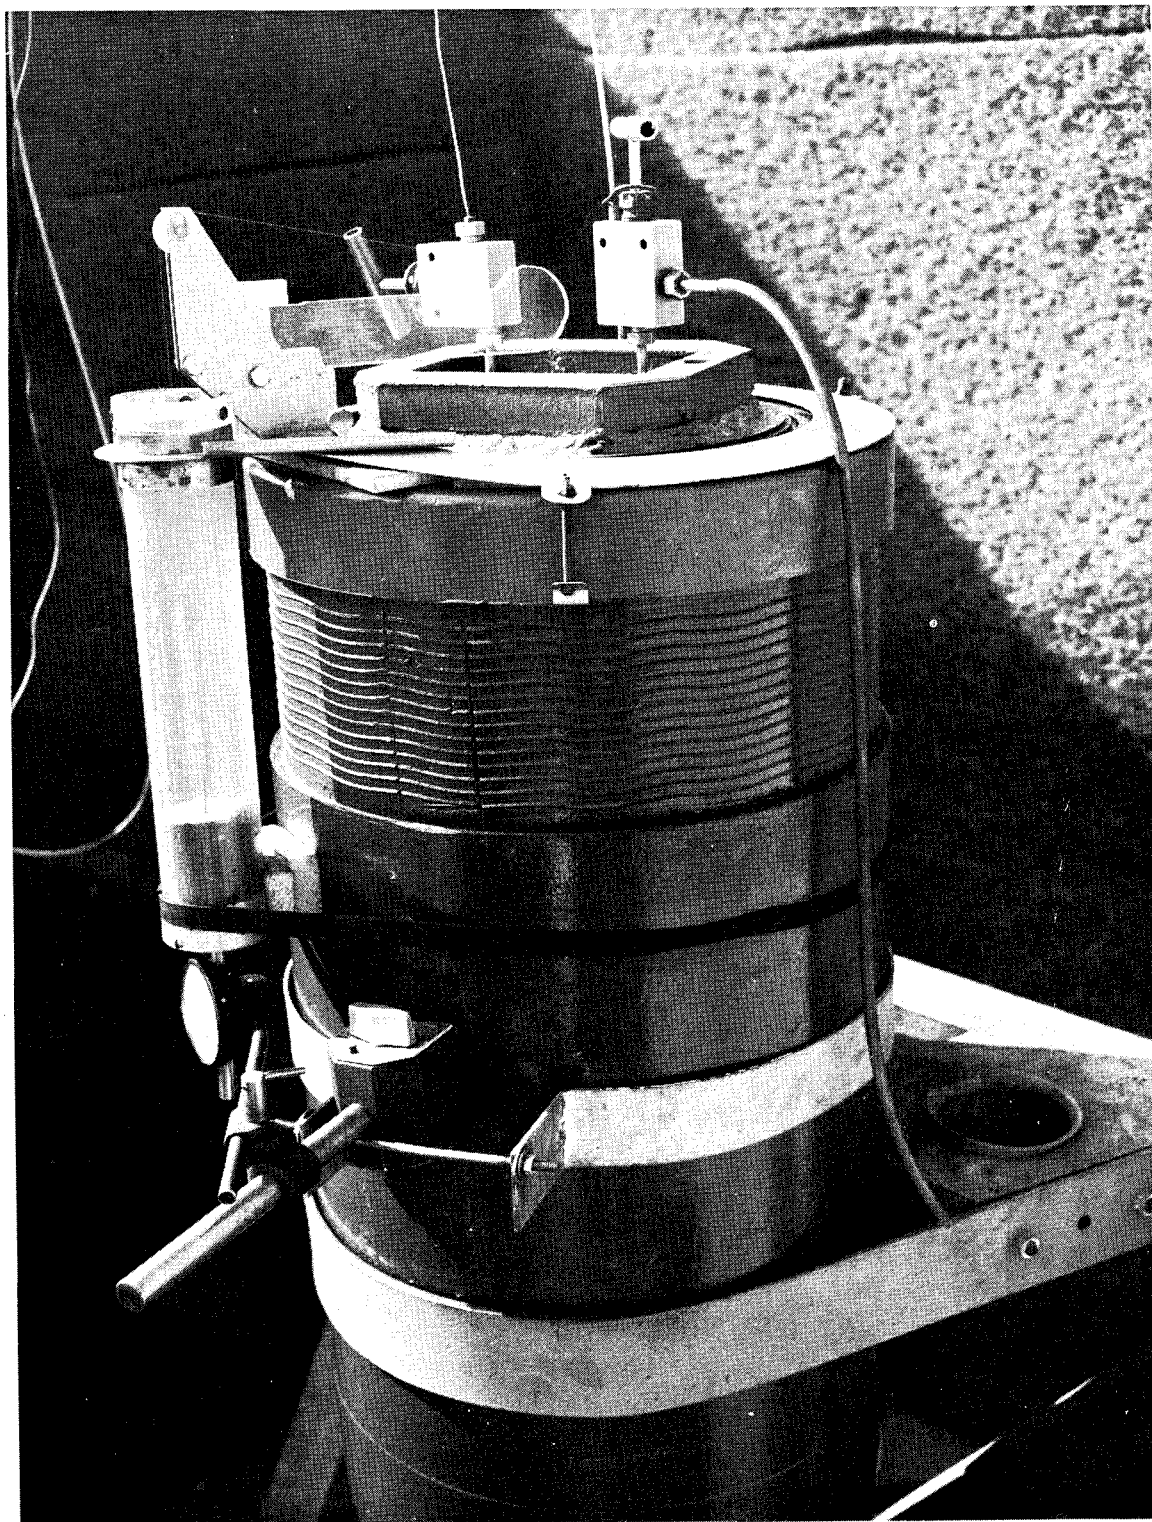


Figure 5. Window displacement measuring device.

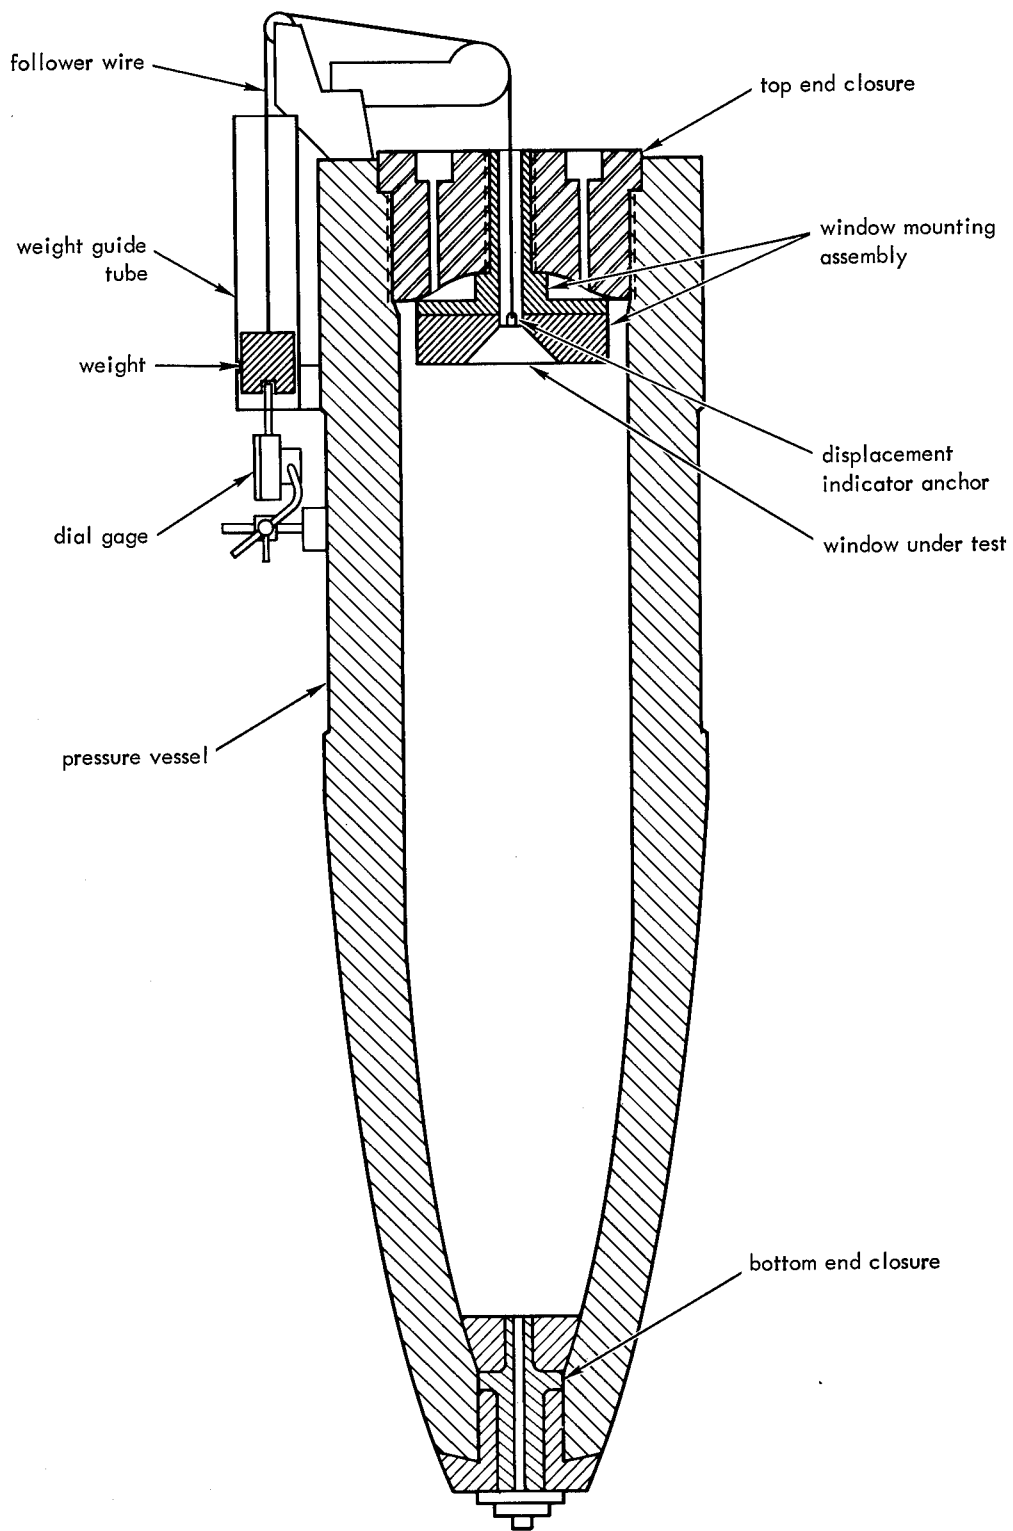


Figure 6. Schematic of window test assembly, with window displacement measuring device in position.

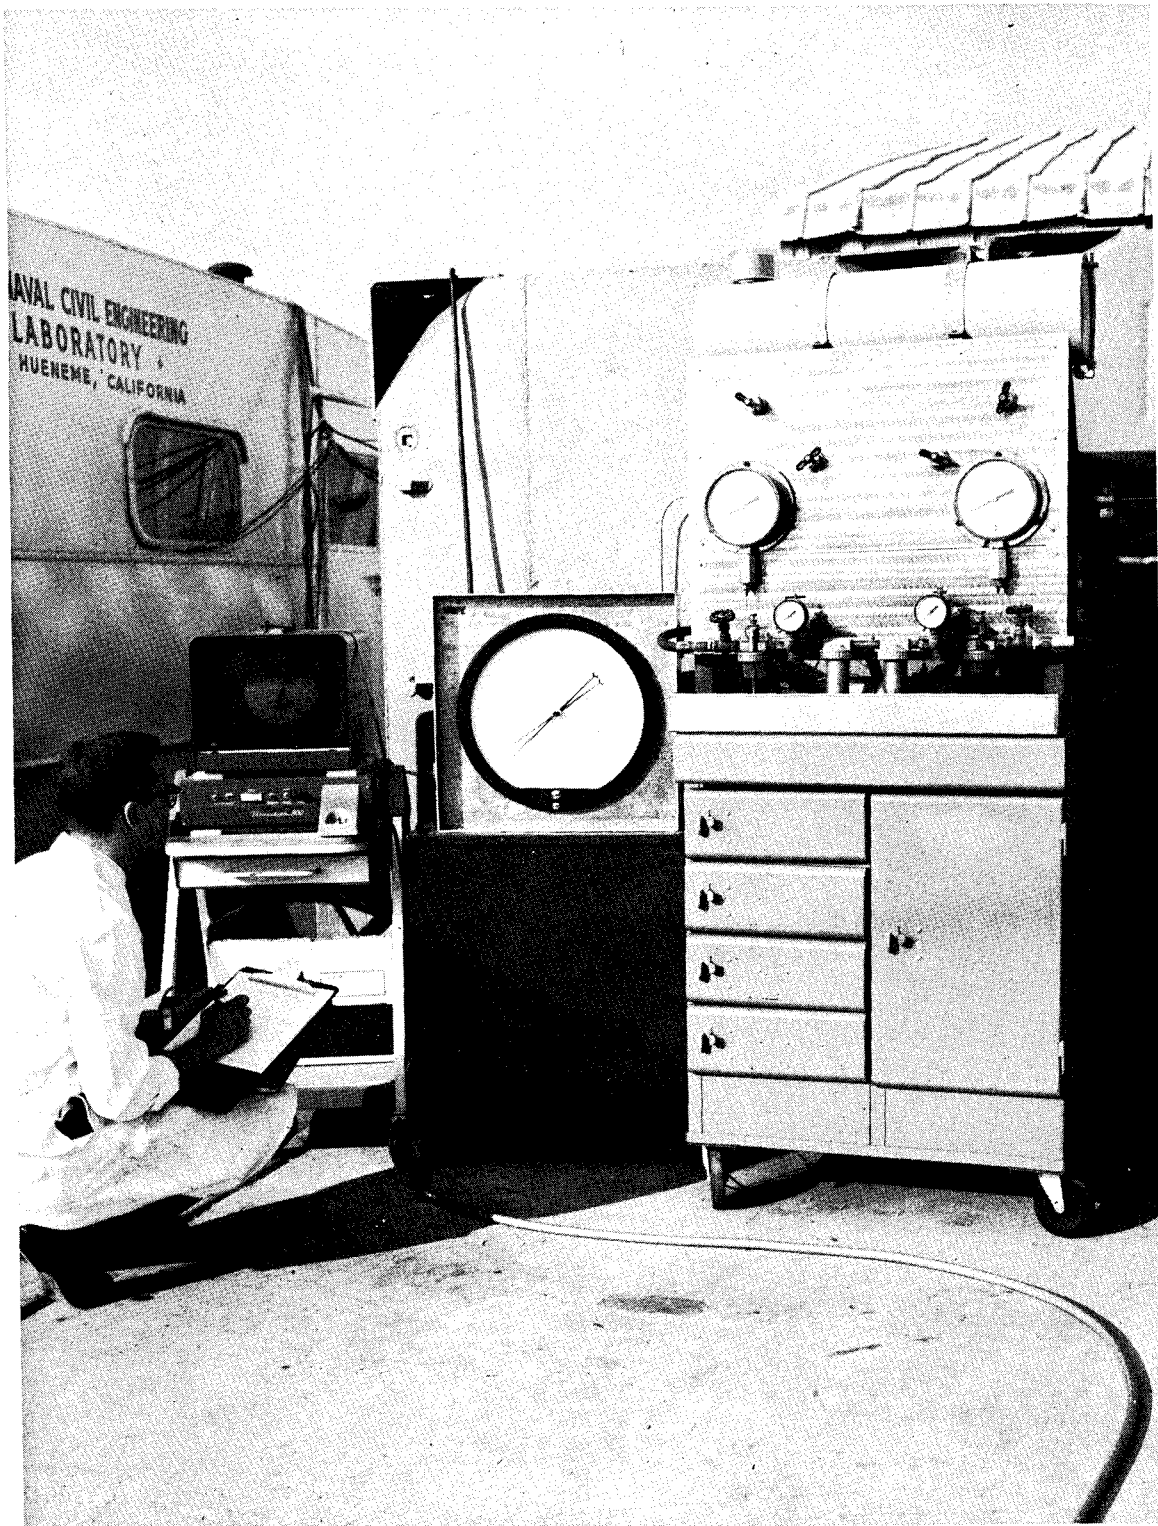


Figure 7. High-pressure pumping unit, precision pressure gage (center), and television monitor used in test procedure.

Once the pressurization process was begun, it was continued until the window failed. Displacement readings were recorded at 1,000-psi intervals without interruption of the pressurizing. Both the pressurization and the recording of displacement data were continuous until window failure occurred with an explosive release of compressed water and fragments of window. Water and fragments were ejected high into the air through the opening in the end closure. To protect the operator of the pressurizing system from possible failure of the vessel, he as well as the monitoring equipment were separated from the test area by a massive concrete block (Figure 8). The dial indicator readings were observed by means of a closed-circuit television system (Figure 9).

EXPERIMENTAL DATA

All the windows which were tested to destruction failed explosively. There was, however, a distinct difference in the mode of failure among the windows, depending on their t/D ratio and included angle. Discussion of the modes of failure is presented in Appendix B.

Scatter of Data

Experimental data consisting of critical pressures at which window failures occurred and magnitudes of displacement at different pressures varied from window to window, even though the windows were of the same nominal dimensions. To obtain a representative value of the experimental parameters, five or more windows of each nominal thickness used were tested for each t/D ratio, and their critical pressures and displacements averaged. This procedure was repeated for each conical angle considered. Since eight nominal t/D ratios and five conical angles were investigated, around 200 experiments were performed and the data from them recorded.

Because the average of any number of experimental readings at a given t/D ratio does not convey adequately the scatter of individual readings, both the minimum and the maximum of each experimental parameter range were also recorded for each t/D ratio. In general, it can be stated that the range of scatter of individual experimental points is less than plus-or-minus 10% of the average value computed for a given t/D ratio and conical angle. Such a magnitude of scatter range is small when one considers that the variation in temperature was of the same magnitude, the thickness of the windows varied within plus-or-minus 0.020 inch of nominal thickness, and that the angular dimension varied within ± 30 minutes of the nominal value.

Size of Sample Group. The size of the sample group was varied and statistical methods were used to verify that five experimental values provided an adequate representation of the experimentally determined variables. The discussion of this study is presented in Appendix C.

Effects of Temperature. Groups of similar specimens were tested at both 35° to 40°F and 67° to 75°F; it was determined that the lower temperature produced a measurable increase in the critical pressure. The discussion of this study is presented in Appendix D.

Subsidiary Experiments

Applicability of 1-Inch-Diameter Window Test Data to Windows of Larger Sizes. Several experiments were conducted with larger windows to determine if the data obtained from tested 1-inch-diameter windows was applicable to larger sizes. It was determined that the t/D ratio (with certain limiting conditions) is a direct scaling factor for critical pressure and that displacement, while not directly scalable, can be estimated reasonably accurately with an appropriate scaling factor. The data and discussion are presented in Appendix E.

Evaluation of Other Window Mounting Flange Configurations. Exploratory experiments were conducted which demonstrated that the configuration of the transition zone between the adjoining cavities of the mounting flange, the conical cavity and the one for accommodating the acrylic displacement, has considerable influence on the short-term critical pressure of the window.

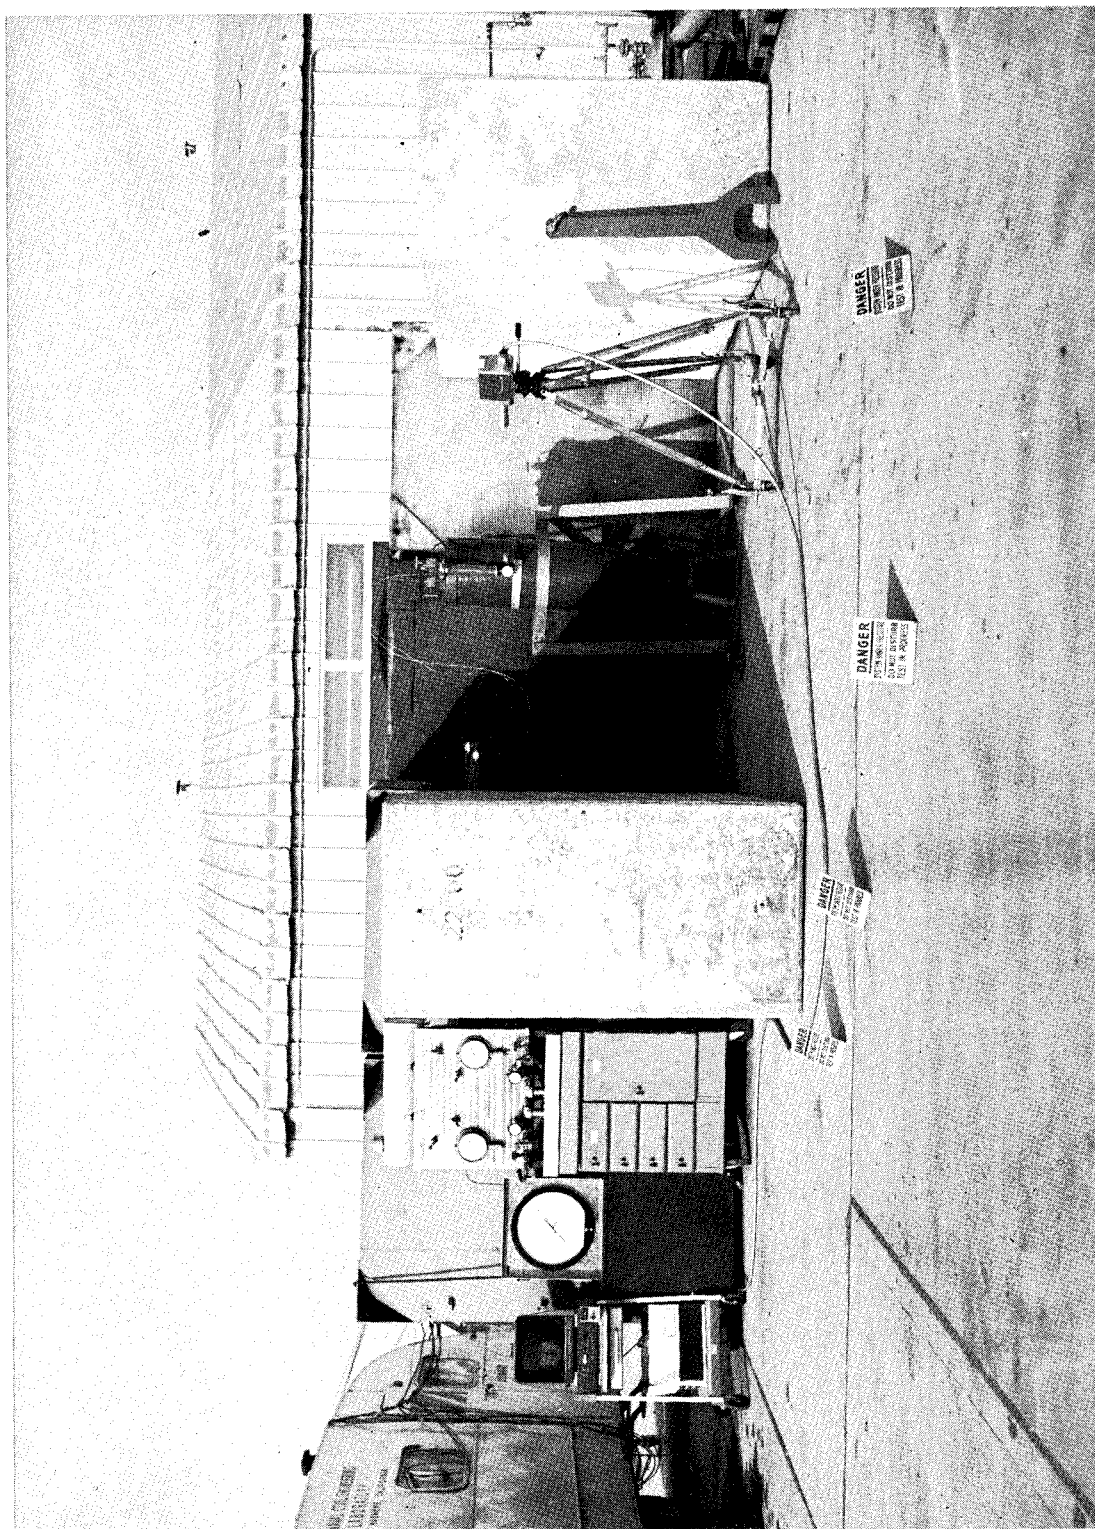


Figure 8. Complete setup for window test program.

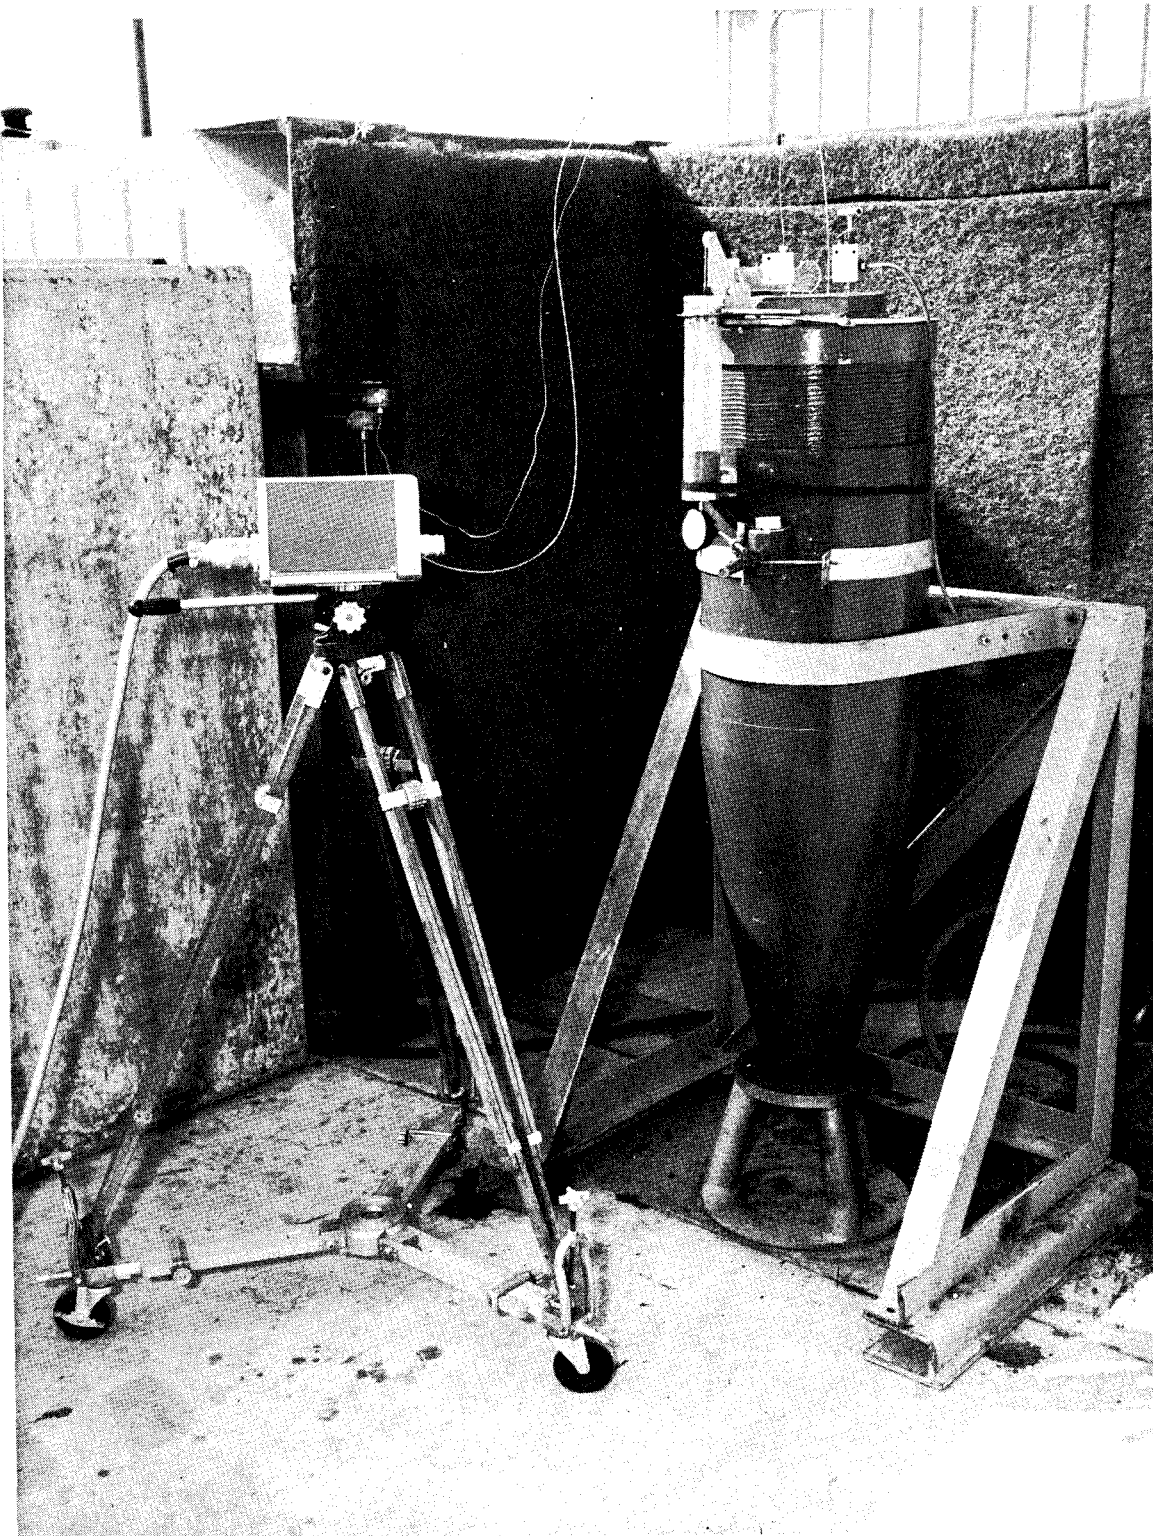


Figure 9. Window displacement measuring system with television camera used to monitor dial gage readings.

One-Inch-Diameter, 30° Conical Windows

Complete data from the testing of 1-inch-diameter, 30° conical windows are presented in Tables G-1 through G-11, Appendix G.

All these windows failed by being ejected from the vessel. In every case the whole window disintegrated into small particles that were carried outside the vessel by the high-velocity stream of water. Inspection of the mounting flange failed to show any pieces of the fractured window adhering to it.

The critical pressure recorded during the testing of the 30° window specimens (Figure 10), when plotted, appear to vary exponentially with t/D ratios, with small variations in the ratio producing large differences in pressure. The displacements of the windows (Figure 11) were large and decidedly nonlinear for all t/D ratios.

One-Inch-Diameter, 60° Conical Windows

Complete data from the testing of 1-inch-diameter, 60° conical windows are presented in Tables G-12 through G-16, Appendix G.

In comparing the critical pressures of the 60° windows (Figure 12) with those of the 30° windows, it became apparent that the 60° type of window was the more pressure-resistant. The differences in critical pressure between windows of the same t/D ratio but different included angle varied with the t/D ratio. The difference was quite small at low t/D ratios, but extremely large at intermediate and high t/D ratios. The high critical pressures of 60° windows were accompanied by smaller displacements (Figure 13) when comparison was made at the same pressure to 30° windows of the same t/D ratio.

One-Inch-Diameter, 90° Conical Windows

Complete data from the testing of 1-inch-diameter, 90° conical windows are presented in Tables G-17 through G-22, Appendix G.

The critical pressures of the 90° windows (Figure 14) were not markedly higher than those of the 60° windows with the same t/D ratio. This showed that the increase in short-term pressure resistance of conical windows, with increase of included angle, was reaching a plateau with the 90° windows, and probably no further gain in pressure resistance was to be achieved by enlarging the included conical angle to 120° or 150°. The displacements of the 90° windows (Figure 15) were observed to be significantly less than those of the 60° windows.

One-Inch-Diameter, 120° Conical Windows

Complete data from the testing of 1-inch-diameter, 120° conical windows are presented in Tables G-23 through G-27, Appendix G.

The critical pressures of these windows (Figure 16) were found to be essentially the same as those of the 90° windows. This seemed to indicate that no further advantage was to be gained in terms of pressure capability by increasing the angle of the windows past 90°.

The displacements of the 120° windows (Figure 17) were observed to be approximately the same as those of 90° windows. Since the displacements were generally smaller than those for the 90° windows, and since the cold-flow cratering (pressure-induced plastic deformation, here a depression, occurring at room temperature) on the high-pressure face of the 120° windows appeared to be less pronounced at the same pressure than for 90° windows, the 120° windows would probably perform better optically at higher pressures than the 90° windows.

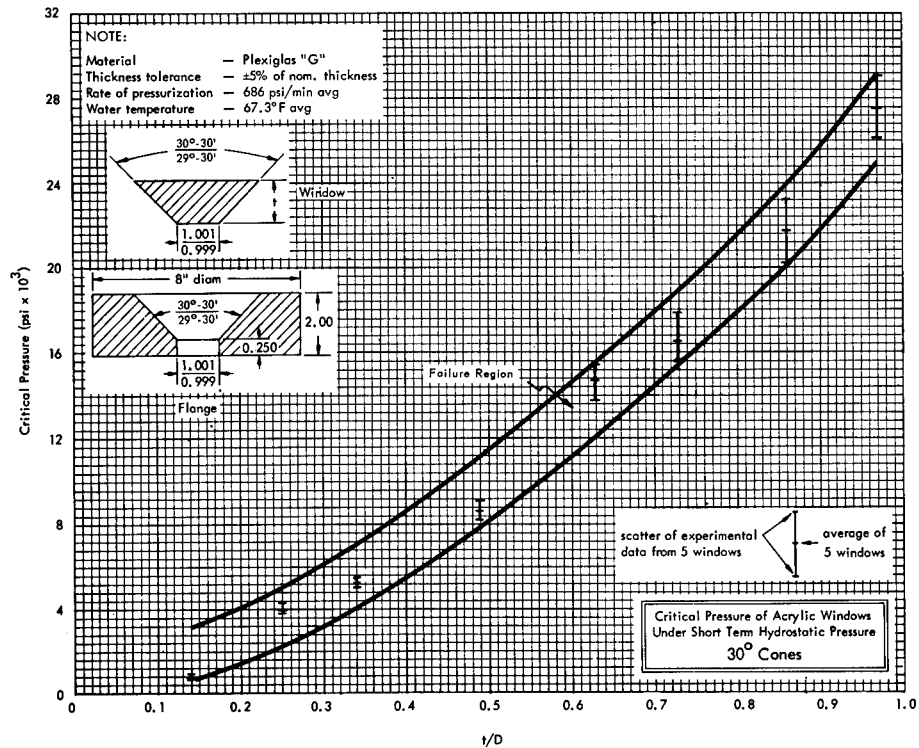


Figure 10. Critical pressures of 1-inch-diameter, 30° conical acrylic windows under short-term hydrostatic pressure.

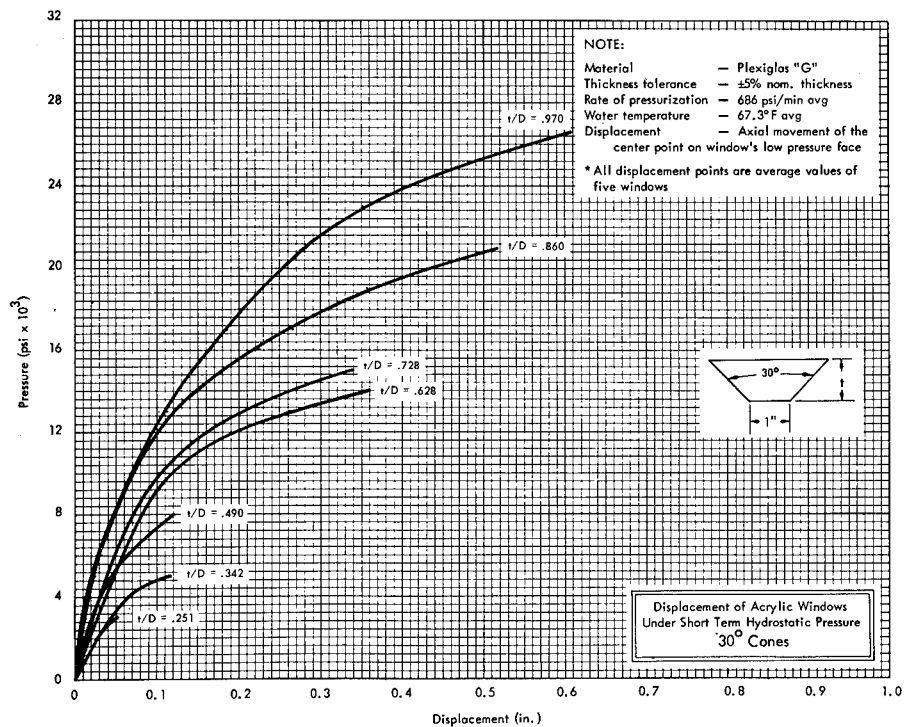


Figure 11. Displacements of 1-inch-diameter, 30° conical acrylic windows under short-term hydrostatic pressure.

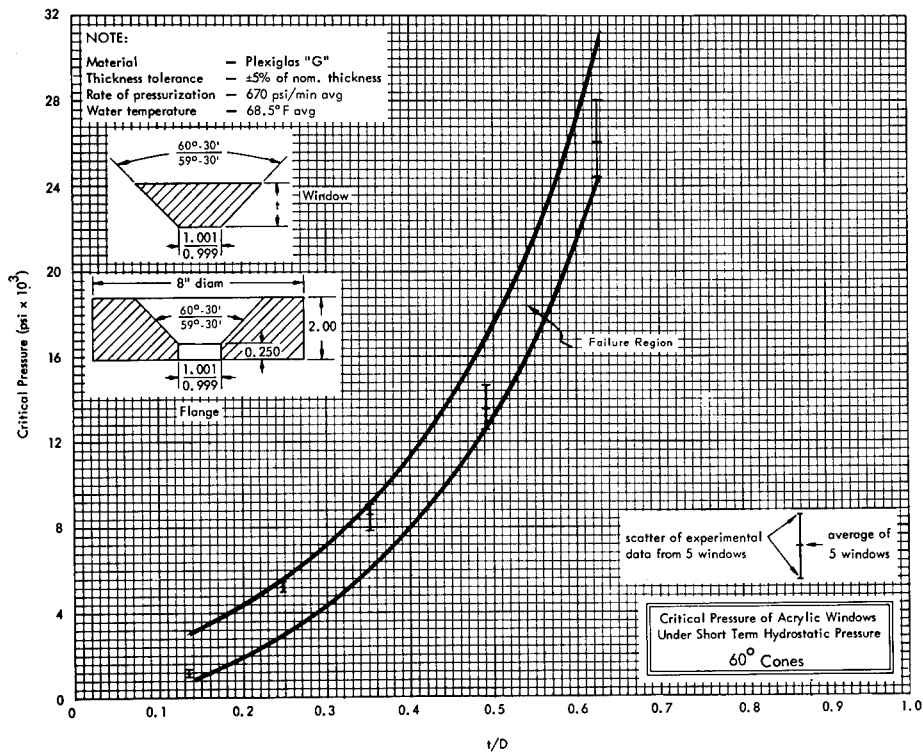


Figure 12. Critical pressures of 1-inch-diameter, 60° conical acrylic windows under short-term hydrostatic pressure.

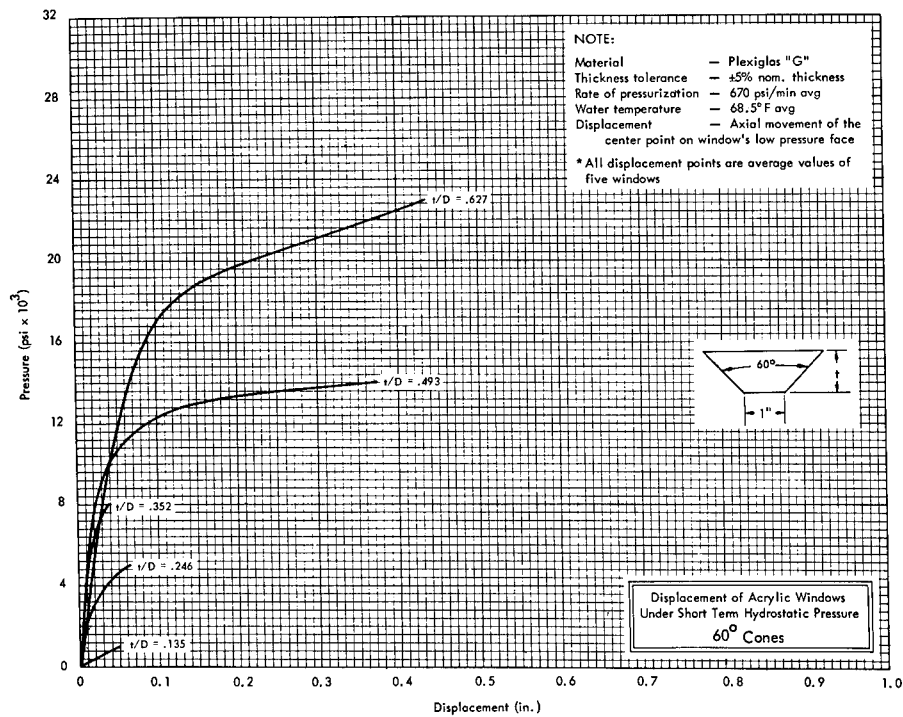


Figure 13. Displacements of 1-inch-diameter, 60° conical acrylic windows under short-term hydrostatic pressure.

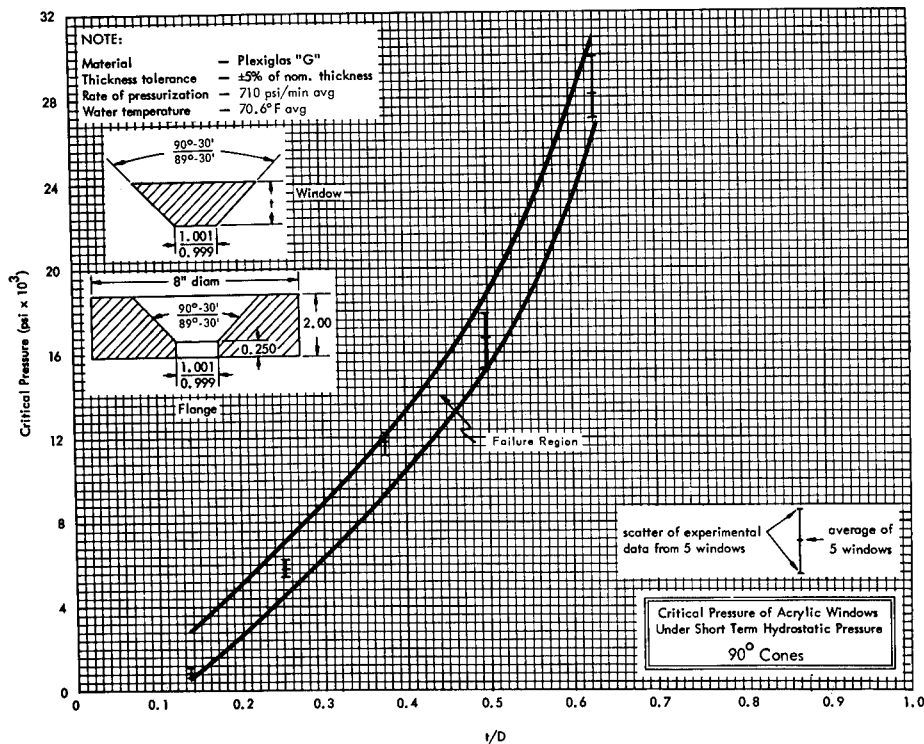


Figure 14. Critical pressures of 1-inch-diameter, 90° conical acrylic windows under short-term hydrostatic pressure.

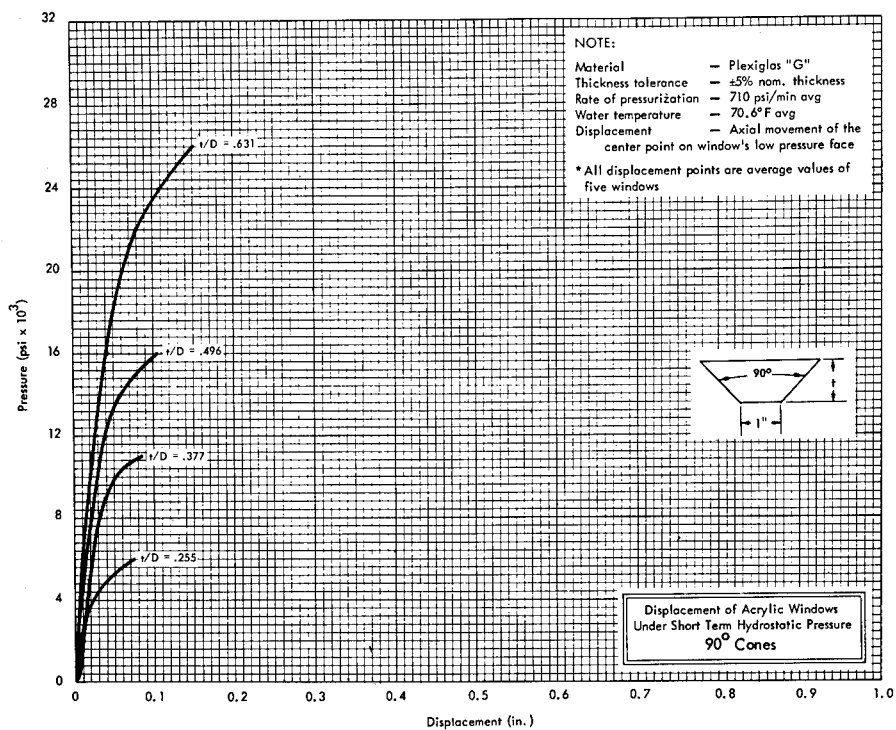


Figure 15. Displacements of 1-inch-diameter, 90° conical acrylic windows under short-term hydrostatic pressure.

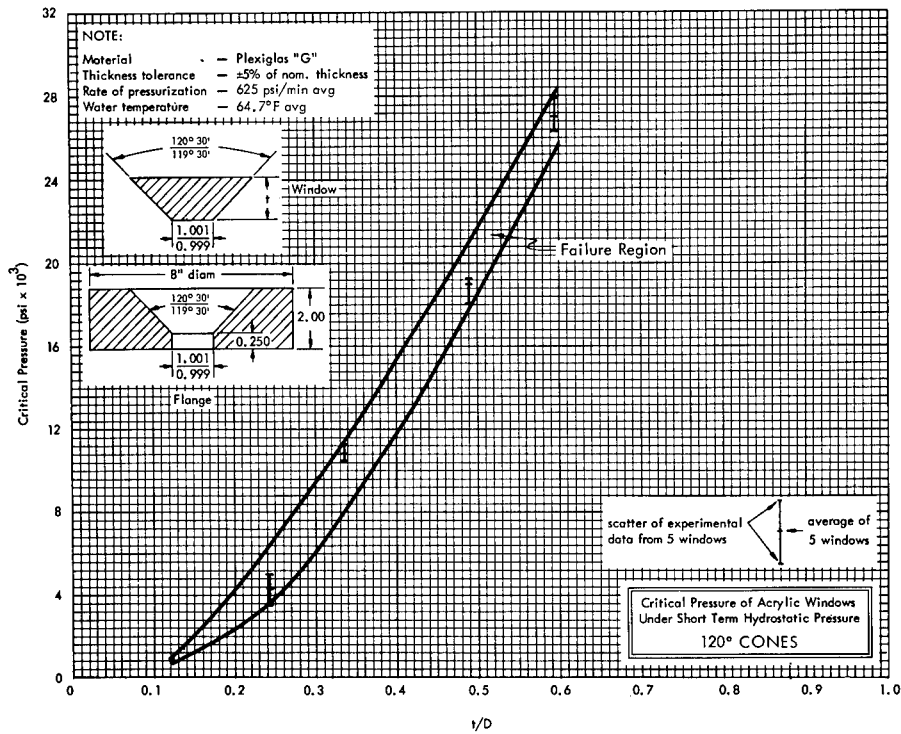


Figure 16. Critical pressures of 1-inch-diameter, 120° conical acrylic windows under short-term hydrostatic pressure.

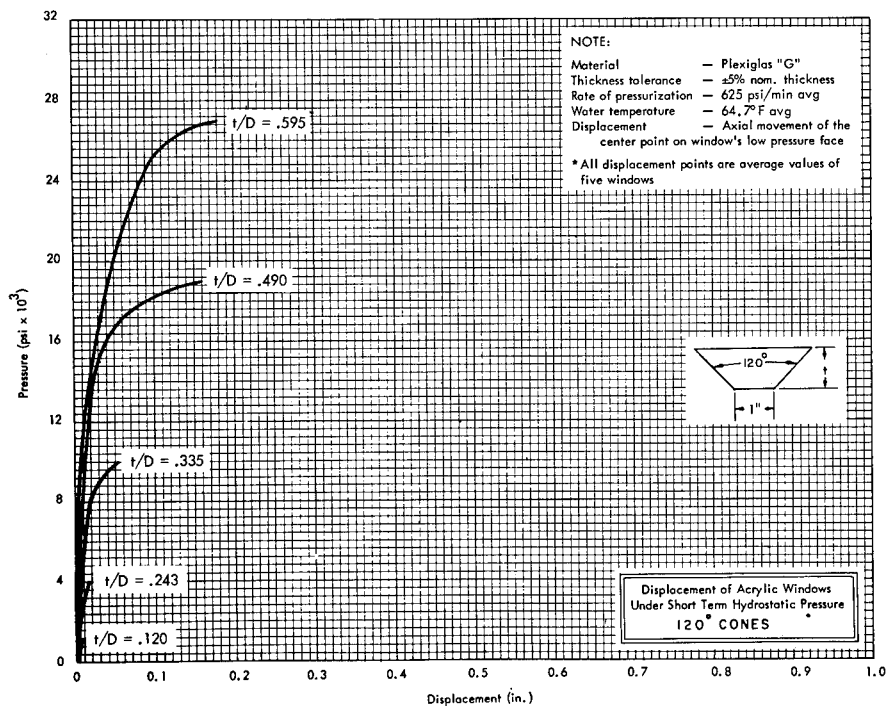


Figure 17. Displacements of 1-inch-diameter, 120° conical acrylic windows under short-term hydrostatic pressure.

One-Inch-Diameter, 150° Conical Windows

Complete data from the testing of 1-inch-diameter, 150° conical windows are presented in Tables G-28 through G-33, Appendix G.

The critical pressures of the 150° conical windows (Figure 18) were in general the same as those of 120° windows, except for 0.375 t/D ratio windows, whose critical pressures were slightly higher. This indicated that, for the most part, no benefit in critical pressure was to be derived by increasing the included angle of the windows above 90° or 120°.

The displacements of the 150° conical windows (Figure 19) were, in general, the same as those of the 120° windows, but noticeably smaller than those of the 90° windows. The shape of the displacement curves shows that very little plastic flow took place in the 150° conical windows prior to their failure at critical pressure, much the same as in the case of the 120° windows.

Two-Inch-Diameter, 30° Conical Windows

Complete data from the testing of 2-inch-diameter, 30° conical windows are presented in Tables G-34 through G-37, Appendix G.

These windows failed at pressures (Figure 20) approximately the same as those of 1-inch-diameter, 30° windows with the same t/D ratio.

The displacements of the 2-inch-diameter windows (Figure 21) were found to be considerably larger than those of the 1-inch-diameter windows with the same t/D ratios. A definite ratio between the magnitudes of displacement for windows of these two diameters could not be derived which would be accurate regardless of t/D ratio. Nevertheless, a 1:2 ratio, representing the ratio between the 1-inch- and 2-inch-diameter windows, can prove useful in estimating the displacement of 2-inch-diameter windows of various t/D ratios from known displacements of 1-inch-diameter windows.

Four-and-One-Half-Inch-Diameter, 60° Conical Windows

Complete data from the testing of 4.5-inch-diameter, 60° conical windows are presented in Tables G-38 through G-40, Appendix G.

The window specimens tested of this type, with t/D ratios of 0.125, 0.25, and 0.5, failed at essentially the same pressures (Figure 22) as the 1-inch-diameter windows with the same t/D ratios. The displacements of the 4.5-inch-diameter windows, however, differed considerably from those of the 1-inch-diameter, 60° windows. When the magnitude of displacement of the 4.5-inch-diameter windows (Figure 23) was compared to that of the 1-inch-diameter windows, it was found to be considerably higher. Although a definite ratio between the magnitudes of displacement for windows with these two diameters could not be derived which would be accurate regardless of the t/D ratio, it appears that a t/D ratio of 1:4.5 is a good approximation. This figure would indicate that the ratio of displacement magnitude for 1-inch- and 4.5-inch-diameter windows is probably the same as that of the two window diameters.

Eight-Inch-Diameter, 90° Conical Windows

The short-term hydrostatic testing with an 8-inch-diameter, 90° conical window (Figures 24 and 25) was conducted under the same experimental conditions as those for 1-inch-diameter, 90° windows, except that an 18-inch-inside-diameter pressure vessel (Figure 25) was used for pressurization. Only the 0.5 t/D ratio was investigated, and its critical pressure compared to that of the 1-inch-diameter conical windows with a 0.5 t/D ratio.

The critical pressure (Figure 26) of the 8-inch-diameter, 90° window was found to be essentially the same as the critical pressure of the 1-inch-diameter, 90° window with corresponding t/D ratio.

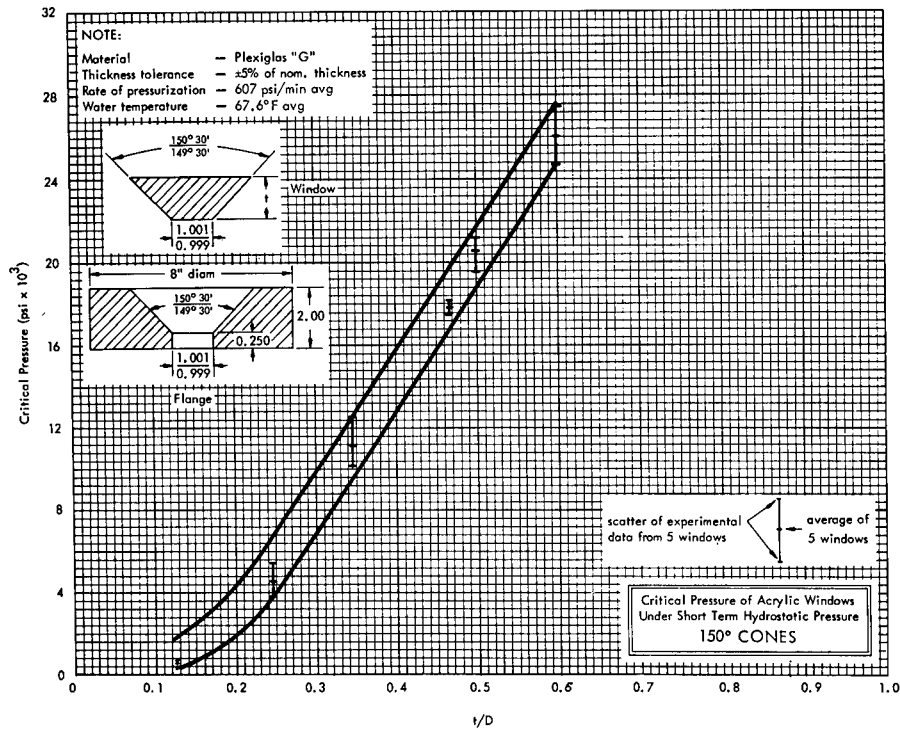


Figure 18. Critical pressures of 1-inch-diameter, 150° conical acrylic windows under short-term hydrostatic pressure.

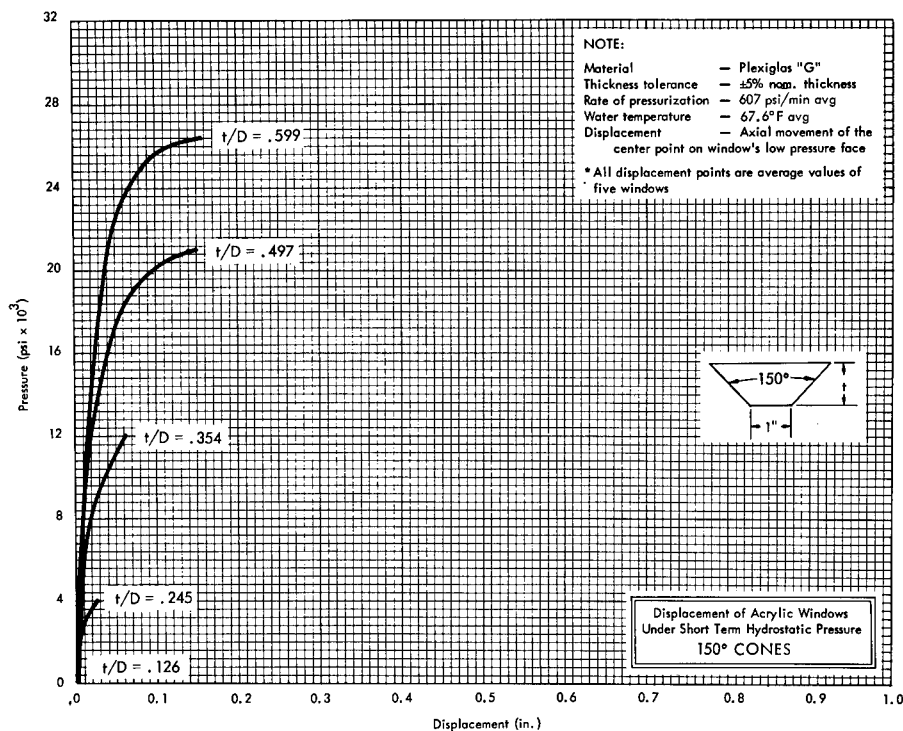


Figure 19. Displacements of 1-inch-diameter, 150° conical acrylic windows under short-term hydrostatic pressure.

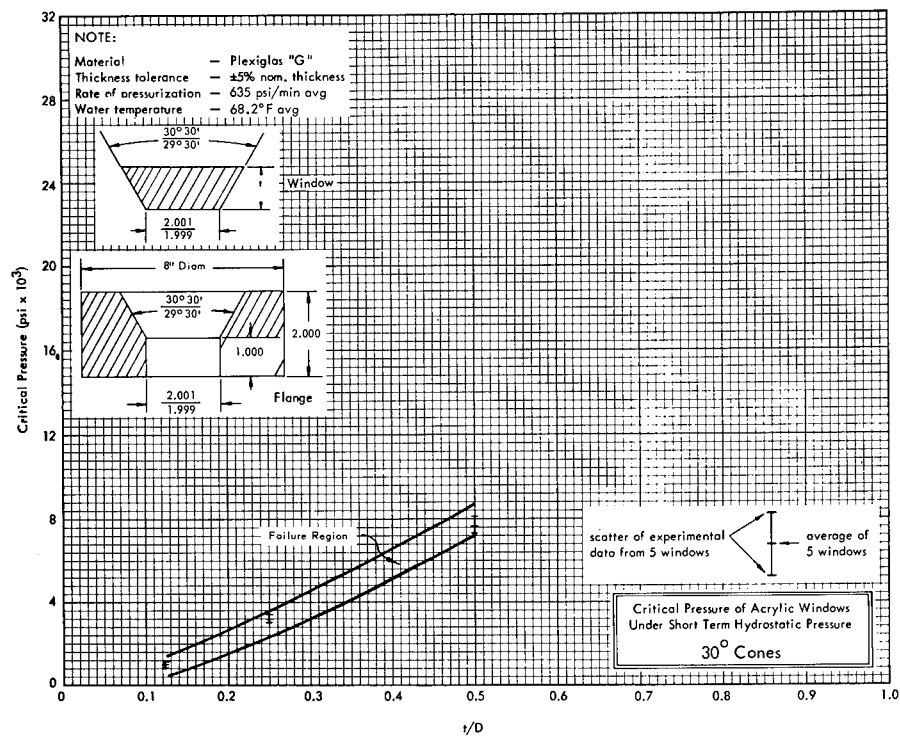


Figure 20. Critical pressures of 2-inch-diameter, 30° conical acrylic windows under short-term hydrostatic pressure.

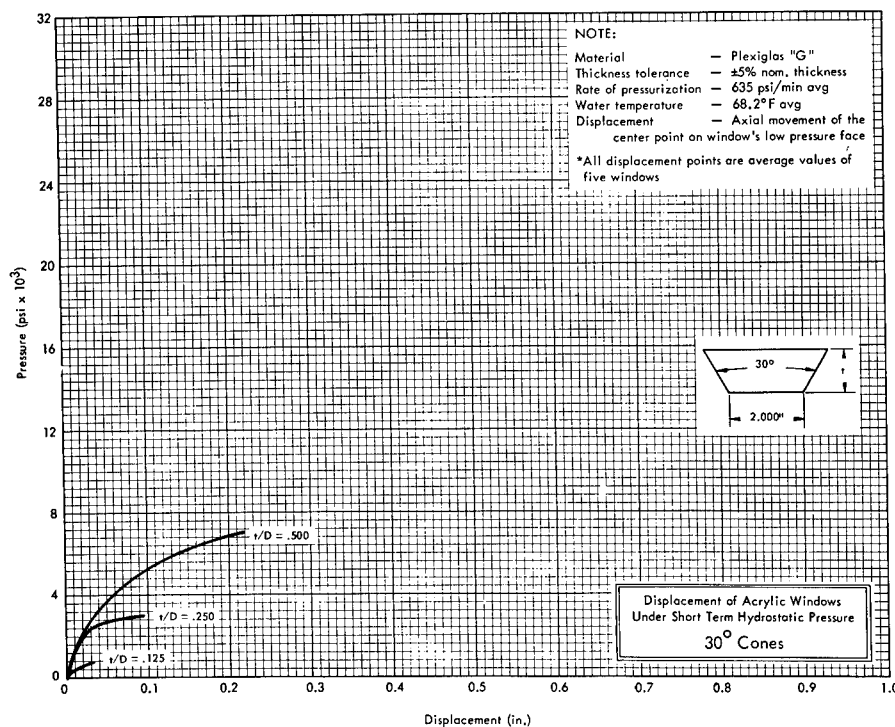


Figure 21. Displacements of 2-inch-diameter, 30° conical acrylic windows under short-term hydrostatic pressure.

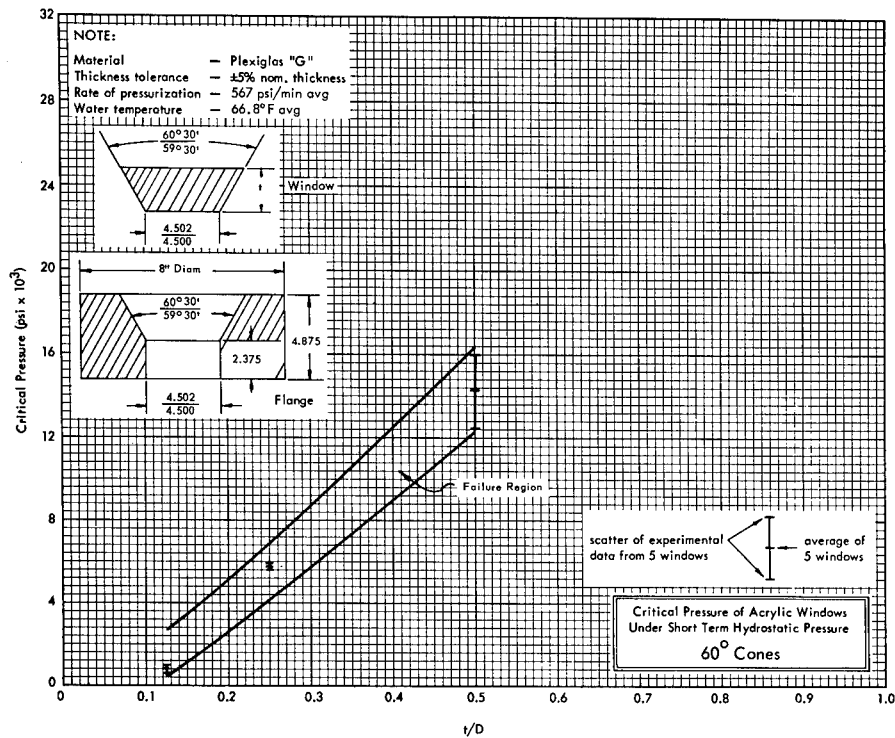


Figure 22. Critical pressures of 4.5-inch-diameter, 60° conical acrylic windows under short-term hydrostatic pressure.

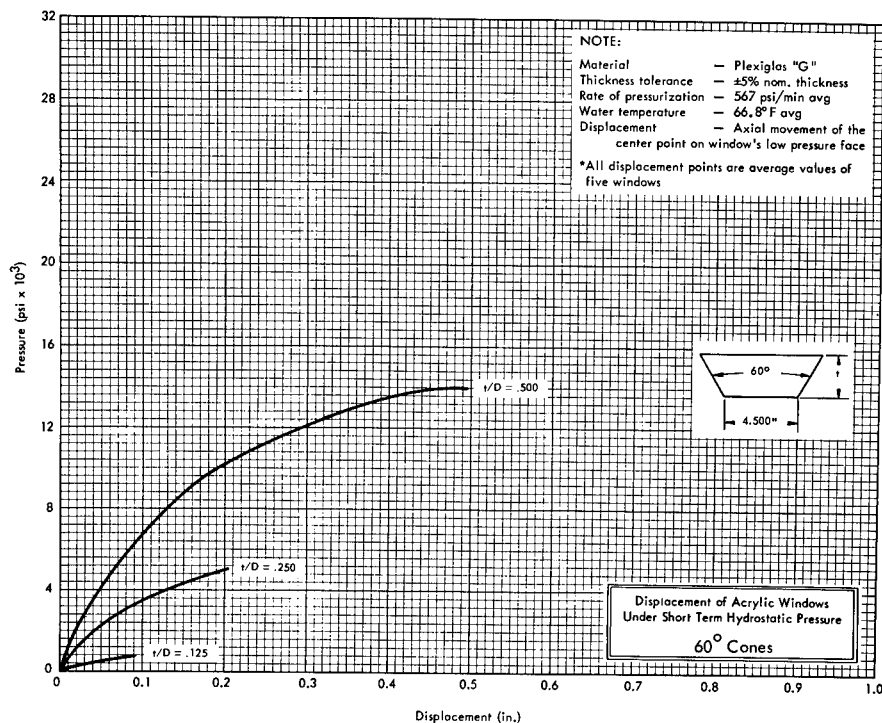


Figure 23. Displacements of 4.5-inch-diameter, 60° conical acrylic windows under short-term hydrostatic pressure.

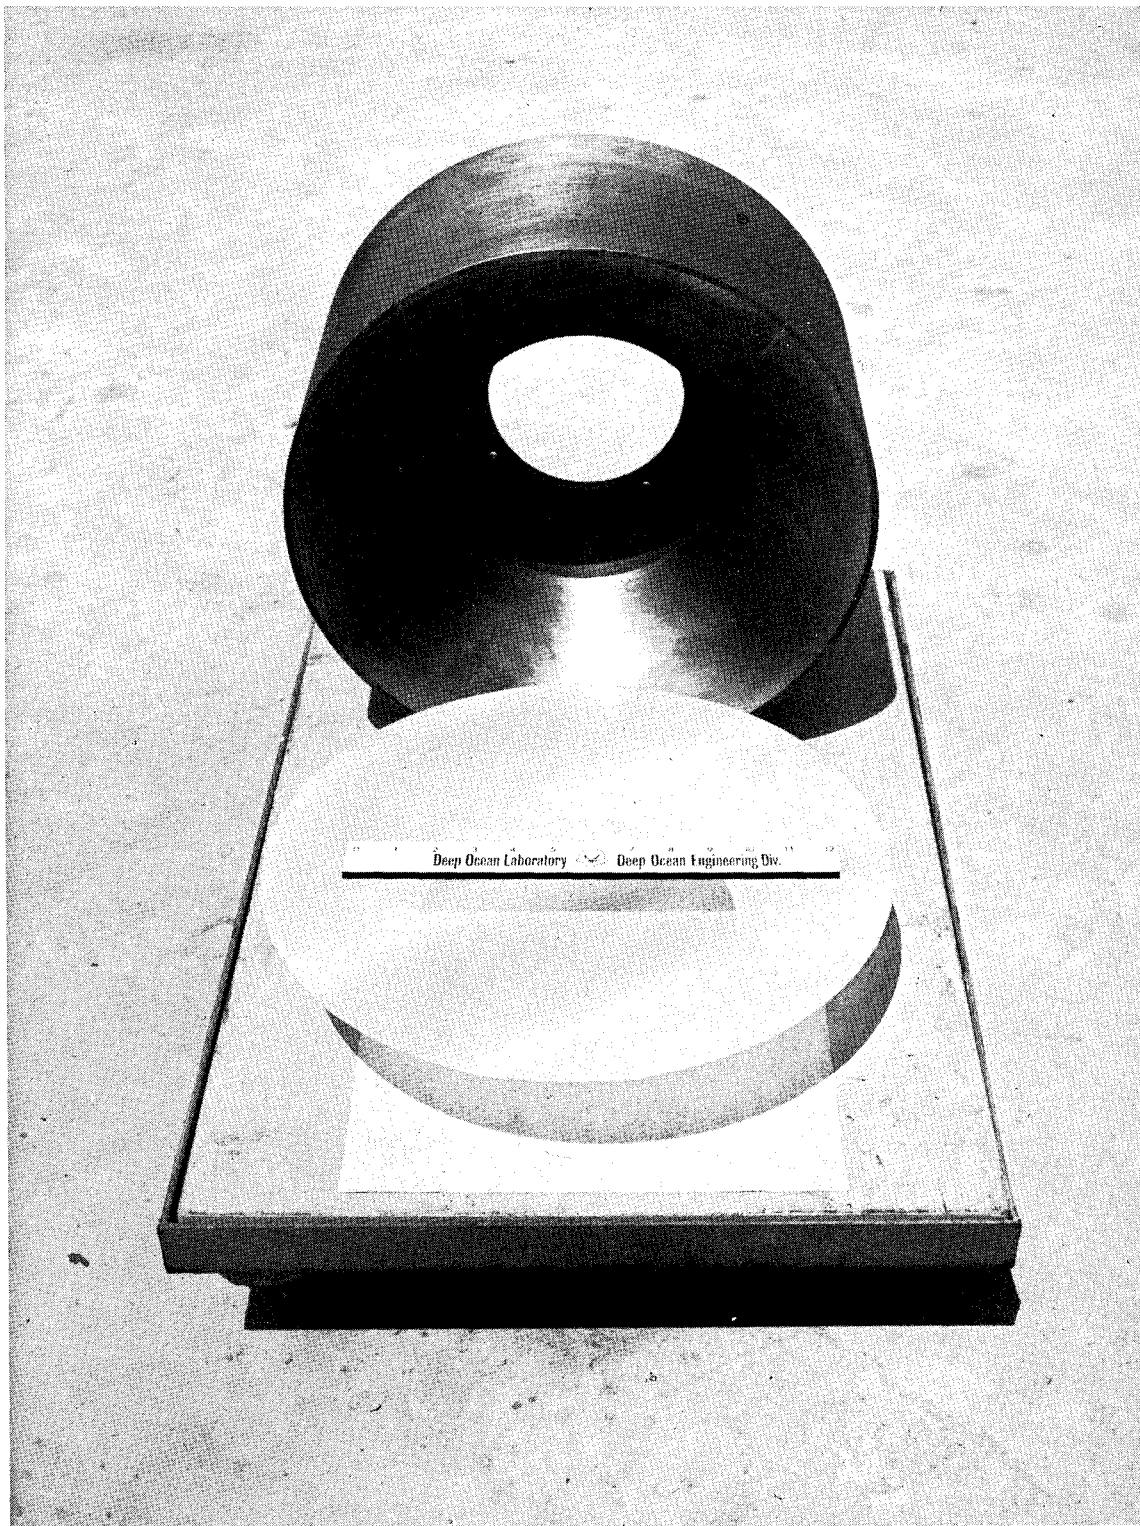


Figure 24. Eight-inch-diameter, 90° conical acrylic window and mounting flange.



Figure 25. End closure assembly for 18-inch-inside-diameter pressure vessel, with 8-inch-diameter, 90° conical acrylic window being secured in mounting flange.

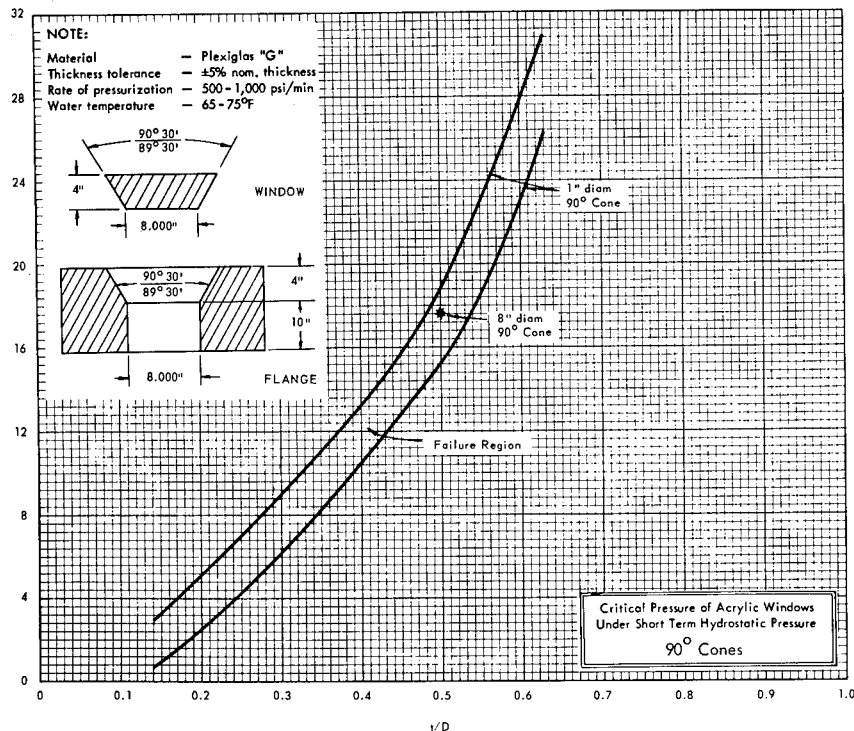


Figure 26. Critical pressure of 8-inch-diameter, 90° conical acrylic window under short-term hydrostatic pressure.

FINDINGS

1. The analysis of experimental data derived from the testing of 1-inch-diameter windows has shown that the displacements of conical acrylic windows larger than 1 inch in diameter, while not directly scalable, can be estimated by application of the proper scaling relationship.
2. The critical pressures of conical acrylic windows in DOL Type I configuration flanges have been found to vary with t/D ratio, as well as the conical angle of the windows. An increase in the t/D ratio is invariably followed by an increase in the window critical pressure, but an increase in the conical angle is not always followed by a critical pressure increase (Figures 27 through 31).
3. The critical pressure of conical acrylic windows under short-term hydrostatic loading increases with a decrease in the temperature of the pressurizing medium. Although sufficient data does not exist to determine accurately how much higher the critical pressure is in the approximately 35° to 40°F than in the approximately 60° to 70°F temperature range, it can be estimated that in all probability it is 10% to 20% higher.
4. The critical pressures of conical acrylic windows with a diameter larger than 1 inch have been found to be the same as those of 1-inch-diameter windows with identical conical angle and t/D ratio.

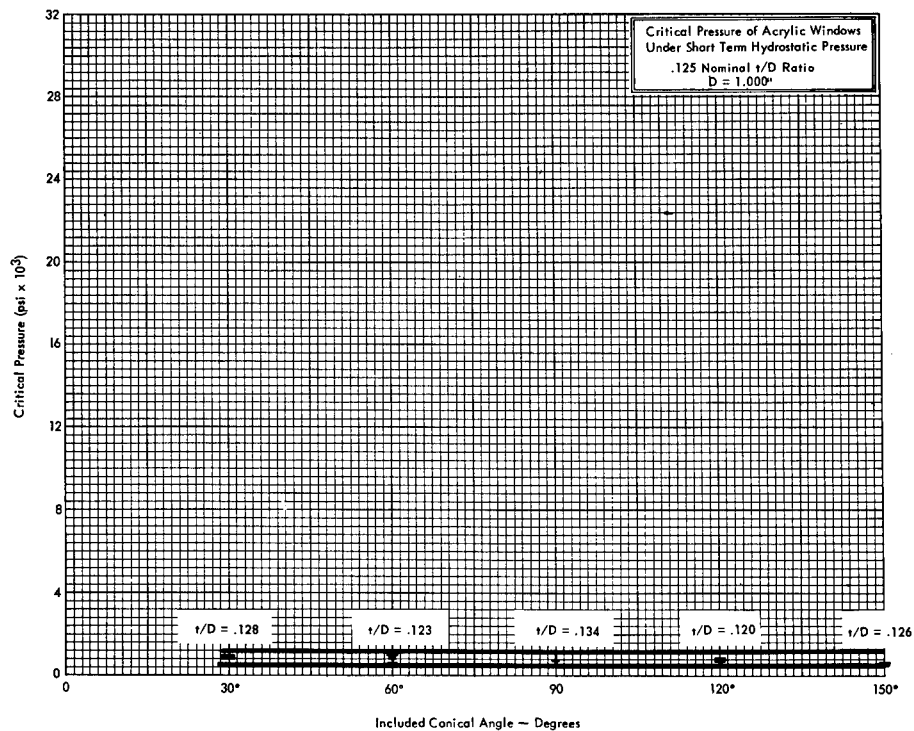


Figure 27. Critical pressures of conical acrylic windows under short-term hydrostatic pressure, 0.125 nominal t/D ratio.

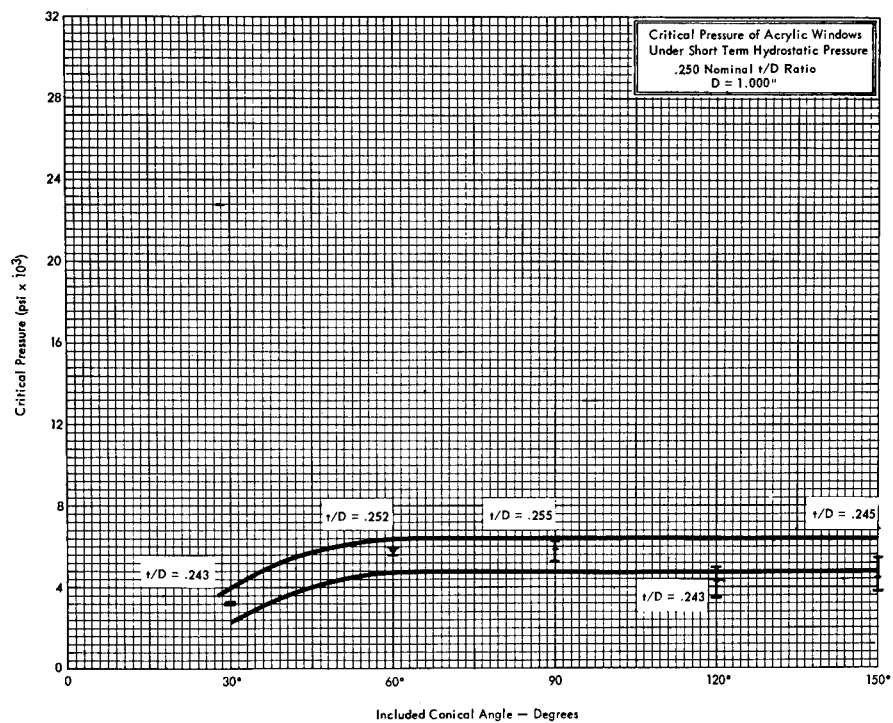


Figure 28. Critical pressures of conical acrylic windows under short-term hydrostatic pressure, 0.25 nominal t/D ratio.

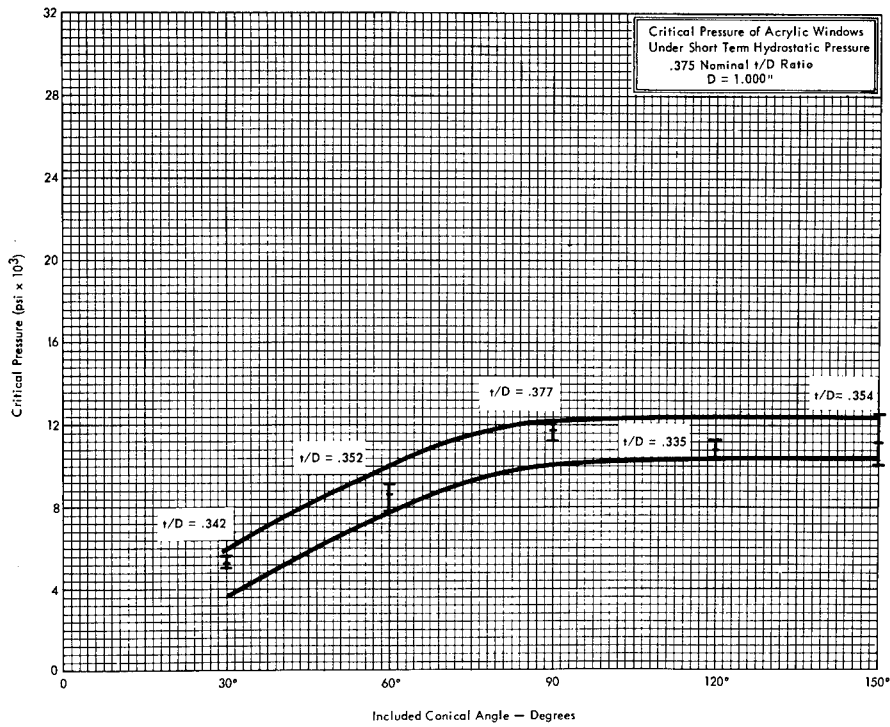


Figure 29. Critical pressures of conical acrylic windows under short-term hydrostatic pressure, 0.375 nominal t/D ratio.

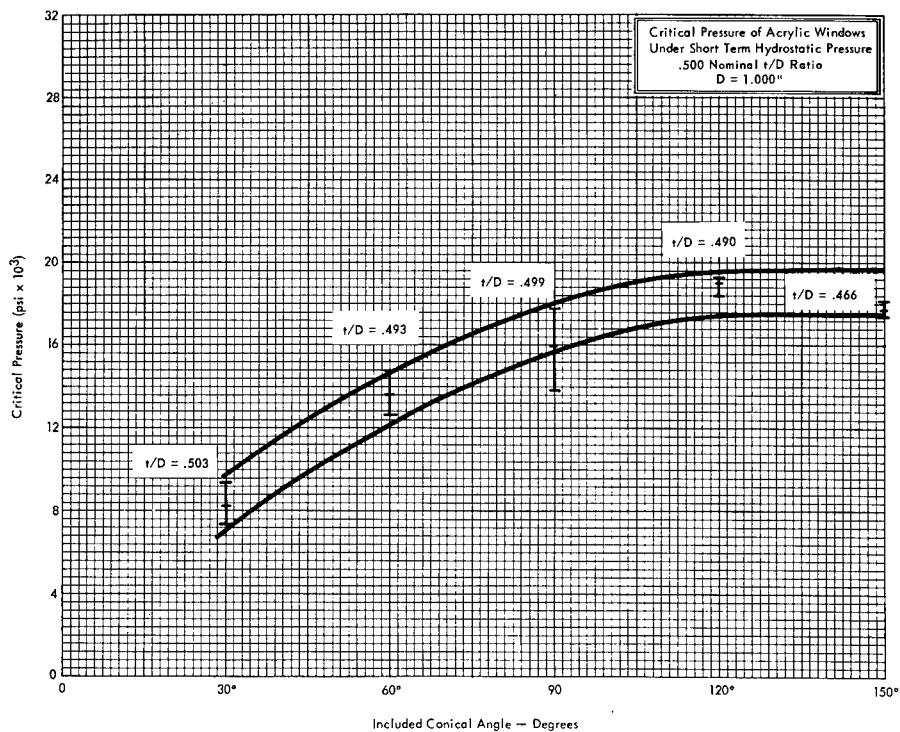


Figure 30. Critical pressures of conical acrylic windows under short-term hydrostatic pressure, 0.5 nominal t/D ratio.

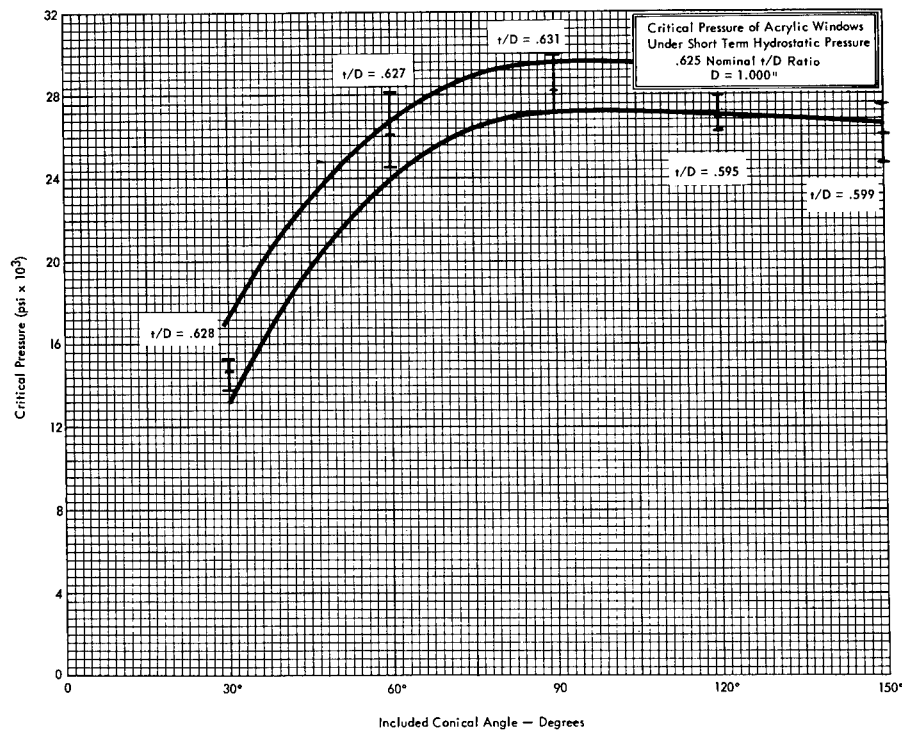


Figure 31. Critical pressures of conical acrylic windows under short-term hydrostatic pressure, 0.625 nominal t/D ratio.

CONCLUSIONS

1. The critical pressures and displacements of the conical acrylic windows presented in this report are valid only for windows mounted in the DOL Type I steel flange. (In this configuration, the pressure-displaced portion of the window has radial support, whatever its extent.) If the DOL Type II steel flange is used to retain the window, much lower critical pressure will result. (The DOL Type II configuration does not provide radial support for the displaced portion.)
2. The critical pressure of large-diameter conical acrylic windows can be predicted directly, with reasonable accuracy, from curves derived from experimental data obtained in the testing of 1-inch-diameter windows provided the larger windows (1) are composed of the same material, (2) have the same t/D ratio and conical angle as the 1-inch-diameter window and, (3) are mounted in a DOL Type I flange.
3. Observation of the material cold flow in the windows tested leads to the conclusion that the optical properties of windows are impaired at pressures considerably below their individual critical pressure. Since optical distortion measurements were not performed with the windows in this study, it is not possible to state quantitatively when the optical distortion of a window progresses to the point where the window loses its value for accurate observation of the hydrospace or the interior of a pressure vessel. Qualitative observations of windows whose testing has been interrupted prior to failure indicate, however, a reasonable assumption to be that the optical properties of windows are not seriously impaired at pressures less than 50% of their critical pressure.

FUTURE STUDIES

Various other studies in the continuing program for investigation of factors which influence the performance of acrylic underwater windows are either in progress or being planned. Studies in progress include the following:

1. Conical acrylic windows under long-term loading (500 to 1,000 hours) at 20,000 psi
2. Short-term critical pressure of flat acrylic windows
3. Short-term critical pressure of spherical acrylic windows

Studies in the planning stage cover:

1. Conical acrylic windows under long-term loading (500 to 1,000 hours) at 10,000 psi
2. Conical acrylic windows under cyclical pressure loading from 0 to 10,000 psi
3. Flat acrylic windows under long-term pressure loading at 20,000 psi
4. Flat acrylic windows under cyclical pressure loading from 0 to 10,000 psi

Appendix A

PHYSICAL PROPERTIES OF GRADE G PLEXIGLAS*

| | |
|---|--------------------------------------|
| Maximum tensile strength | 10, 500 psi |
| Maximum flexure strength | 16, 000 psi |
| Maximum compressive strength | 18, 000 psi |
| Maximum shear strength | 9, 000 psi |
| Modulus of elasticity in tension (at strain less than 1%) | 450, 000 psi |
| Modulus of elasticity in compression (at strain less than 1%) | 450, 000 psi |
| Maximum elongation at rupture in tension | 4.9% |
| Impact strength (Izod milled notch) | 0.4 ft-lb/in. (per inch of notch) |
| Rockwell hardness | M-93 |

*Staff Report, Plexiglas Design and Fabrication Data, Bulletin 229g, Rohm and Haas Co., August 1961.

Appendix B

MODES OF FAILURE OF CONICAL ACRYLIC WINDOWS

In the following descriptions of failure modes for conical acrylic windows, certain terms have special definitions. Cold flow is the plastic deformation of the acrylic window material at room temperature resulting from application of high hydrostatic pressure to the window high-pressure face while the low-pressure face remains at atmospheric pressure. Cratering denotes the formation of a roughly circular depression in the center of the window high-pressure face as a result of cold flow. A fracture cone is a cone-shaped fracture surface inside the body of a window observed at the termination of the test.

In the photographs supplementing the descriptions of the failure modes, the grid pattern seen on many of the high-pressure window faces is the reflection of a grid cast there at the time the photographs were made. This reflection is a device intended to reveal any cratering or other irregularity on the high-pressure face, as a result of cold flow or partial mechanical failure. Any irregularity in the mirrorlike window surface is made apparent by a distorted reflection of the regular square pattern of the grid.

One-Inch-Diameter, 30° Conical Windows

All the 1-inch-diameter, 30° conical windows failed explosively, with all fragments ejected from the pressure vessel. An interesting feature was the lack of deformation on the high-pressure faces of these windows. Examination of a test specimen removed from the flange after being pressurized to approximately 85% of its critical pressure revealed almost no cold-flow cratering on the high-pressure face (Figure B-1) but a considerable amount on the low-pressure face, as evidenced by the moderately long, cylindrical extrusion (Figure B-2). The low-pressure face also exhibited the circumferential cracks typical of low-pressure faces of all conical acrylic windows regardless of their included angle size. Since the deformation was noted at a pressure very close to the critical pressure of the window, it is reasonable to assume that the failure of the 30° window does not result from any deep cratering of the high-pressure face, but propagation of cracks from the bearing surfaces to the interior of the window. When these cracks, already apparent in the specimen examined, penetrate to the window center, fracturing of the window occurs followed by ejection of the fragments from the mounting flange.

One-Inch-Diameter, 60° Conical Windows

The mode of failure of the 1-inch-diameter, 60° conical windows was not as uniform as that of the 30° windows, but varied with the t/D ratio. Windows with low t/D ratios, 0.125 and 0.25, failed by fracturing in such a manner that only the center portion was ejected, with the rest of the window staying in the mounting flange in the form of a continuous ring. The low-pressure face of these windows (Figure B-3) exhibited a conical fracture surface, while the high-pressure face remained flat without trace of cold flow, showing only a round hole with ragged edges in the center (Figure B-4).

The 60° windows with an intermediate t/D ratio (0.375 to 0.625) also fractured in the center, so that only the center portion of the window was ejected, while the other fragments remained in the flange in most cases. The windows with the intermediate t/D ratios had very severe cold-flow symptoms on the high-pressure face (Figures B-5 and B-6). This extensive cold flow was a bona fide indication that the proportions of the window were such that the failure of the material had to occur in the plastic range of its properties. The low-pressure face of the windows with intermediate t/D ratios had the same type of conical fracture cavity as the low t/D ratio, 60° windows (Figure B-7). The cold flow on the high-pressure face, when considered together with the conical fracture cavity on the low-pressure face, indicated that, although the amount of cold flow increased with the increase of t/D ratio, the actual mechanism of fracture was the same.

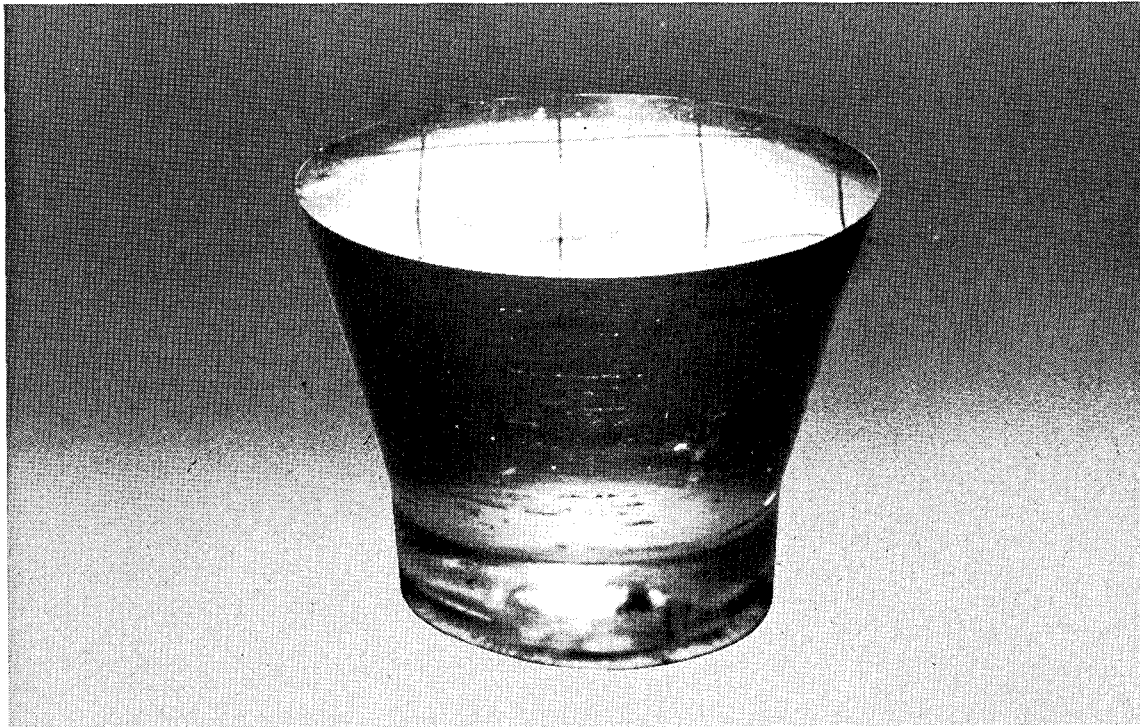


Figure B-1. Arrested failure of 1-inch-diameter, 30° , 1.0 t/D ratio window at 24,000 psi, high-pressure face.

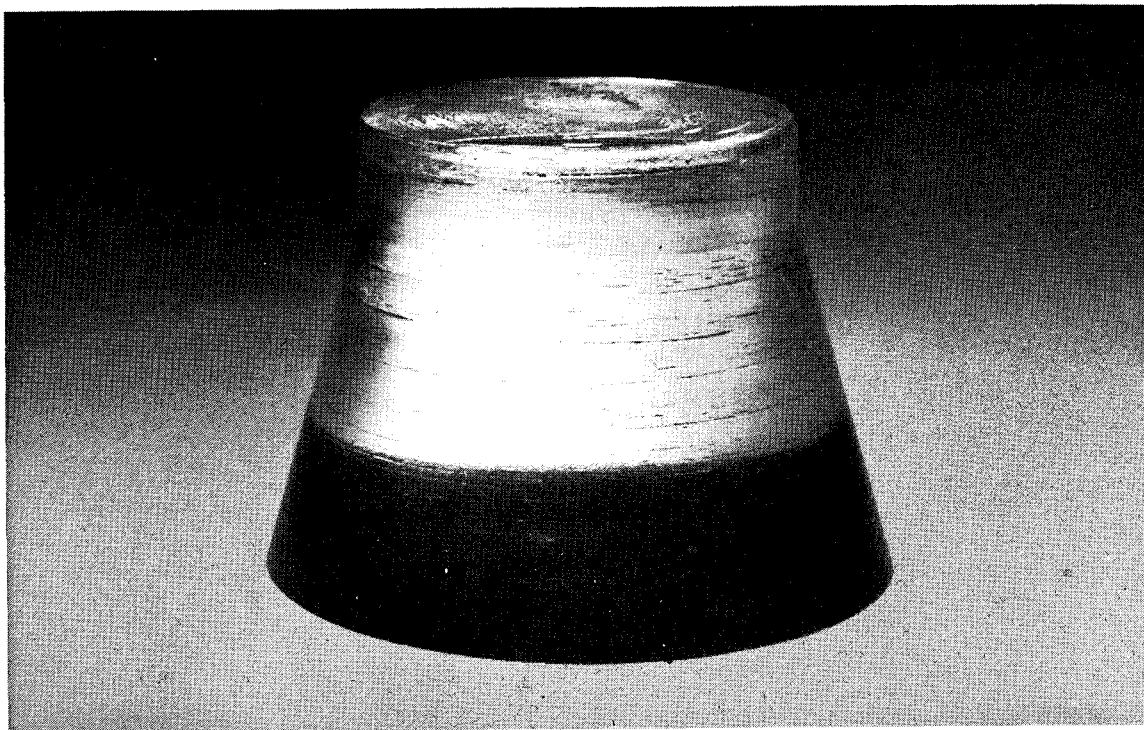


Figure B-2. Arrested failure of 1-inch-diameter, 30° , 1.0 t/D ratio window at 24,000 psi, low-pressure face.

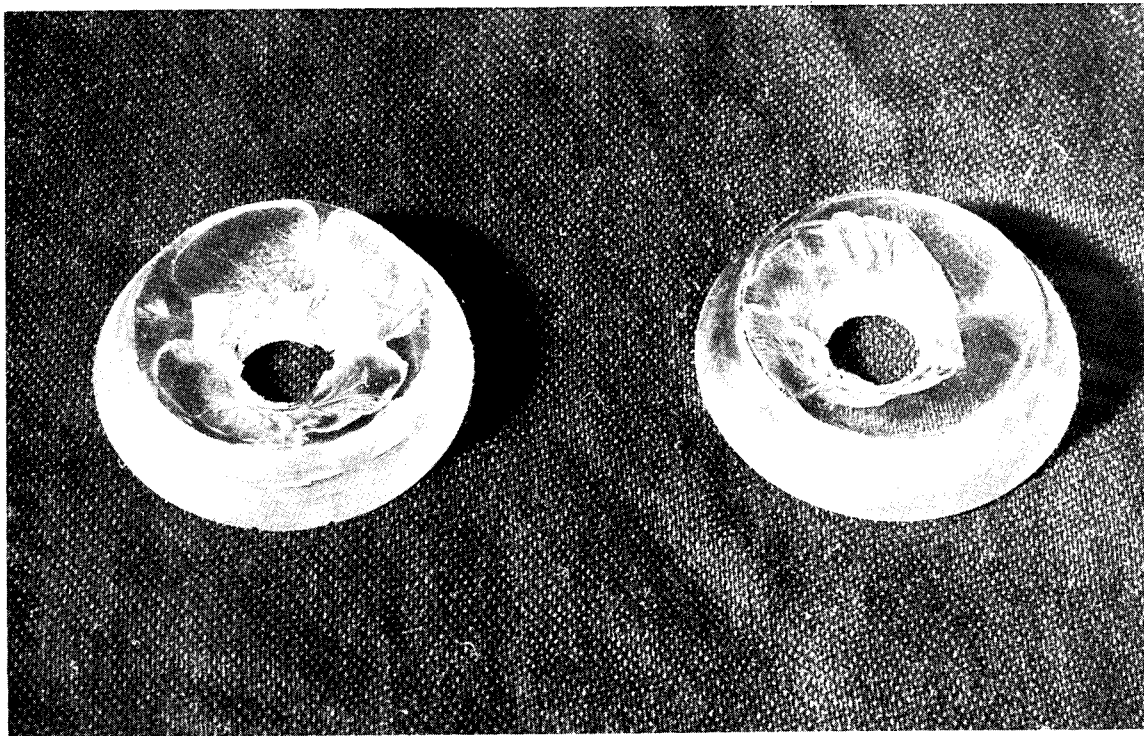


Figure B-3. Failed 1-inch-diameter, 60° , 0.25 t/D ratio windows, low-pressure faces.

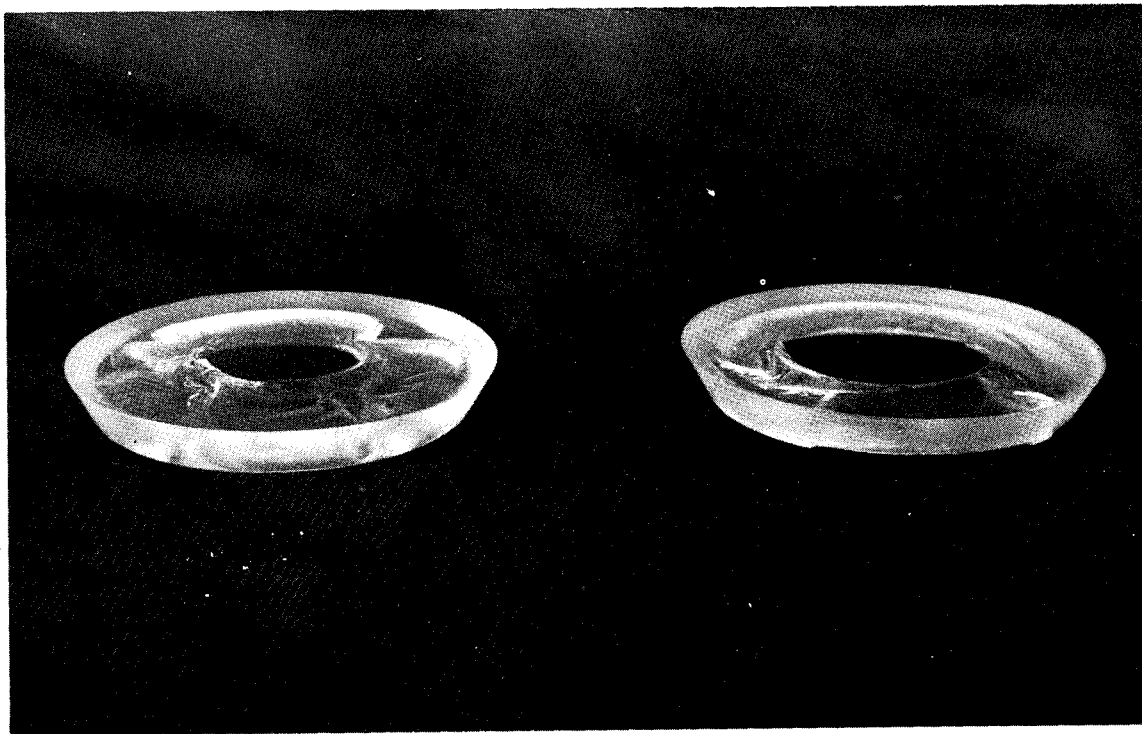


Figure B-4. Failed 1-inch-diameter, 60° , 0.25 t/D ratio windows, high-pressure faces.

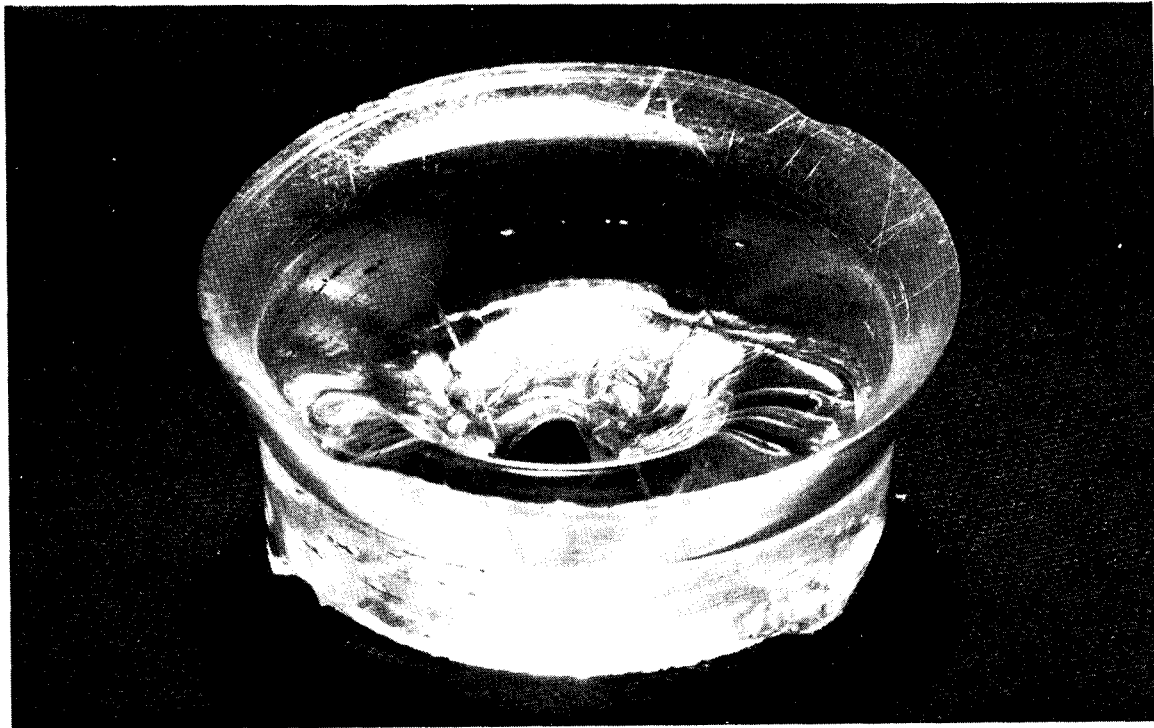


Figure B-5. Failed 1-inch-diameter, 60°, 0.35 t/D ratio window, high-pressure face.



Figure B-6. Arrested failure of 1-inch-diameter, 60°, 0.625 t/D ratio window at 26,600 psi, high-pressure face.

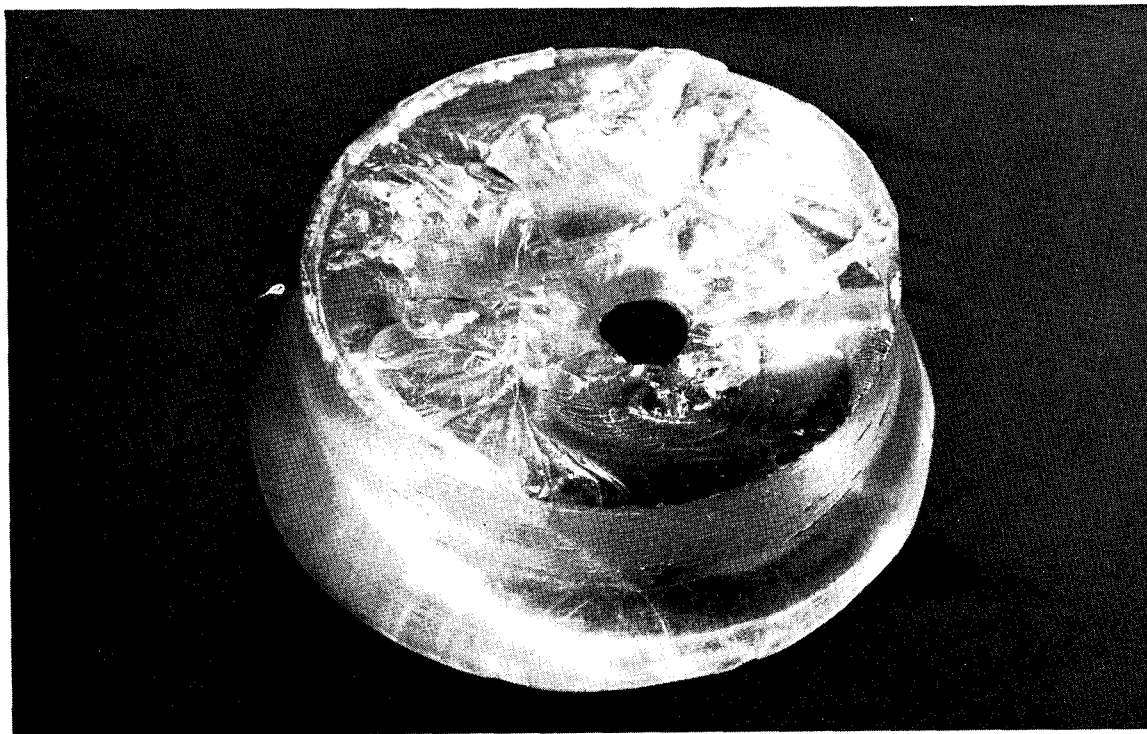


Figure B-7. Failed 1-inch-diameter, 60°, 0.35 t/D ratio window, low-pressure face.

When the 60° windows with high t/D ratios were observed during tests, it was found they behaved in a manner similar to the low and intermediate t/D ratio windows except that no pieces of window remained in the flange after testing. The cold flow, of course, would be more pronounced than in either the low or intermediate ratio windows, as the proportions of the window were such that a cold flow had to occur before a conical fracture on the low-pressure face could be initiated. Even windows pressurized to 30% to 50% below the critical pressure showed considerable extrusion into the cylindrical cavity of the mounting flange (Figure B-8). When the large amount of cold flow on the low-pressure face of the high t/D ratio (1.0) window (Figure B-8) was compared with the small amount of cold flow on the high-pressure face (Figure B-9), the tentative conclusion was reached that the high t/D ratio, 60° window underwent three phases of deformation. The first phase was characterized by the uniform radial compression of the window caused by hydrostatic pressure forcing the acrylic plastic into the cylindrical cavity, resulting in the large amount of extrusion there. Very little, or no cold flow occurred on the high-pressure face of the window during that phase, as the face still remained essentially flat without noticeable crater. The duration of the first phase was probably to 50% of the critical pressure of the window.

The second phase, lasting from approximately 50% of critical pressure to just below the critical pressure, was characterized by extensive cold flow on the low-pressure face (Figure B-10), while the crater on the high-pressure face became noticeable (Figure B-11). Considerable cracking of the window body occurred in the transition zone between the conical and cylindrical sections of the window, as well as on the low-pressure face. The cracks in the transition zone (Figure B-10) extended at an angle from the bearing surface of the window into its interior, forming the incipient conical fracture surface. The cracks on the low-pressure face, on the other hand, extended along the circumference of the face, forming several continuous-crack circles.



Figure B-8. Arrested failure of 1-inch-diameter, 60° , 1.0 t/D ratio window at 22,000 psi, low-pressure face. (Phase 1 of deformation.)

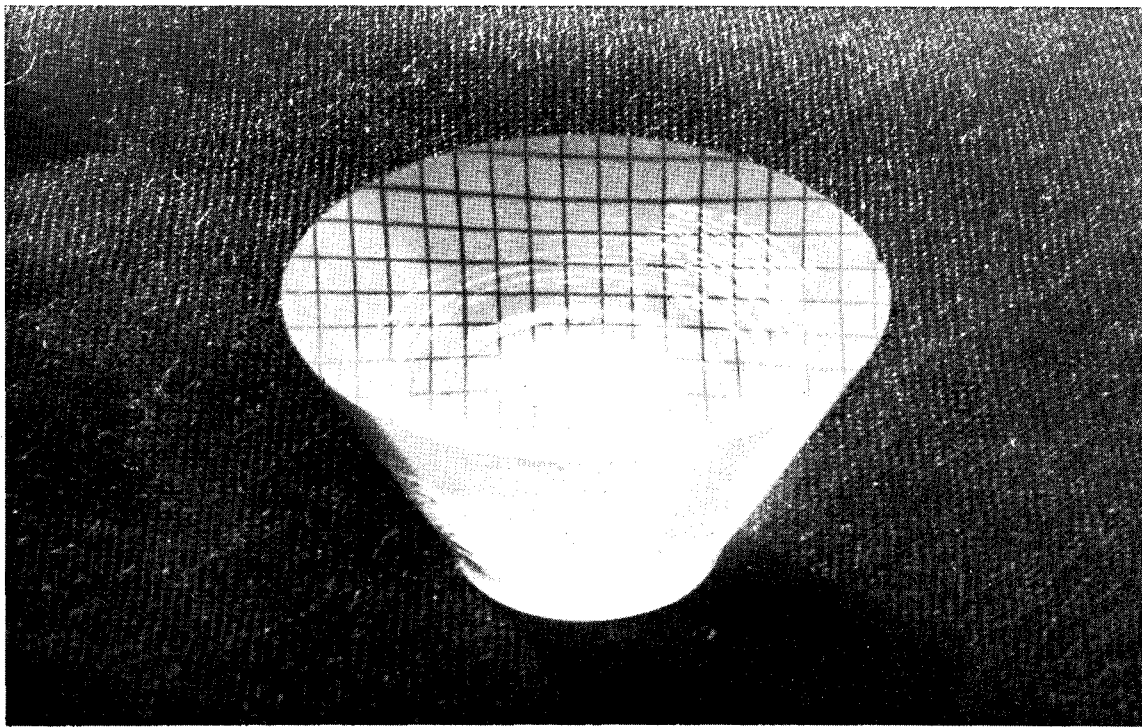


Figure B-9. Arrested failure of 1-inch-diameter, 60° , 1.0 t/D ratio window at 22,000 psi, high-pressure face. (Phase 1 of deformation.)

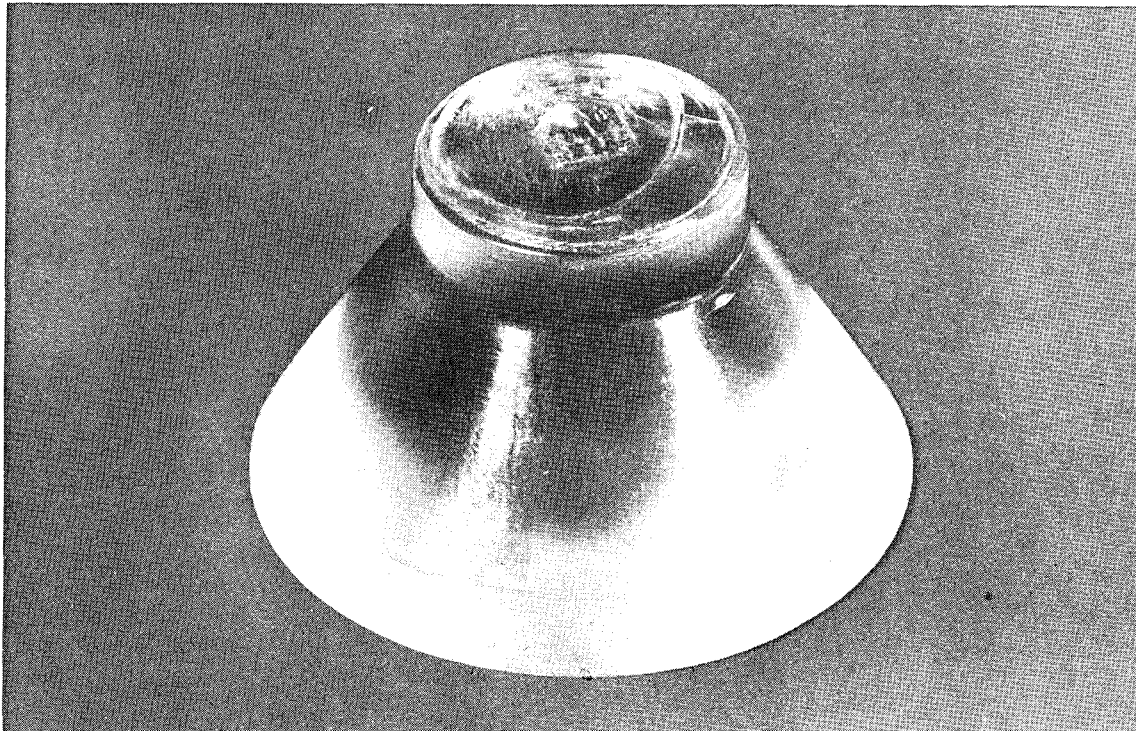


Figure B-10. Arrested failure of 1-inch-diameter, 60° , 1.0 t/D ratio window at 28,000 psi, low-pressure face. (Phase 2 of deformation.)

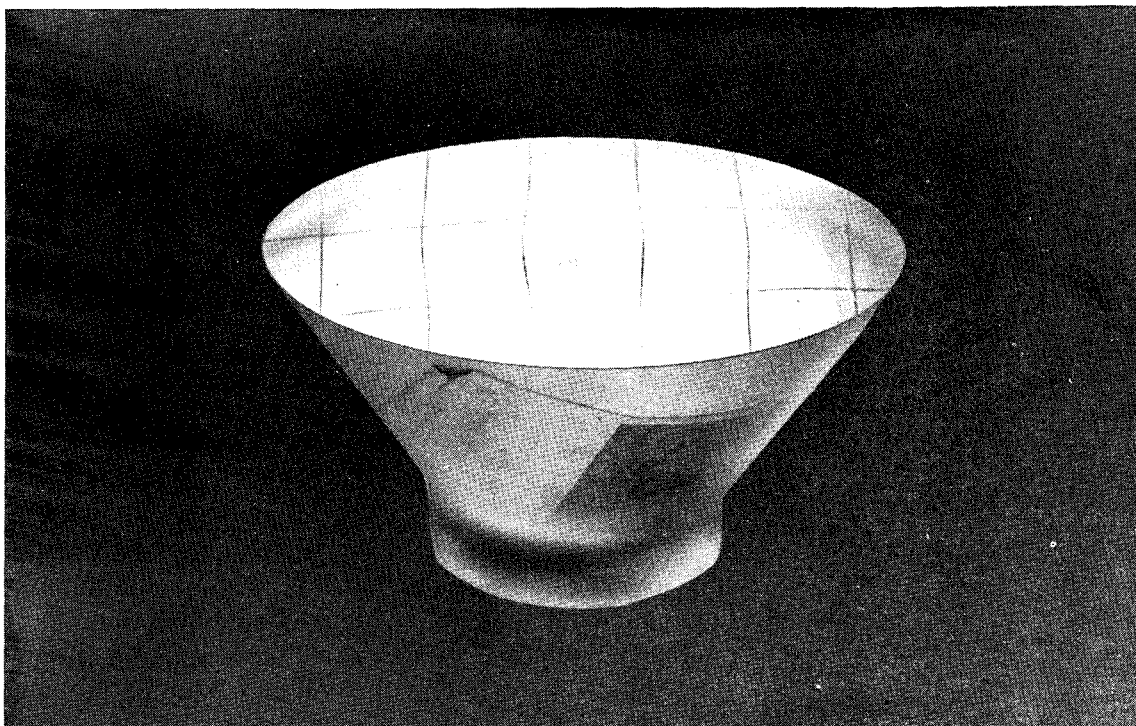


Figure B-11. Arrested failure of 1-inch-diameter, 60° , 1.0 t/D ratio window at 28,000 psi, high-pressure face. (Phase 2 of deformation.)

The third phase of deformation of the high t/D ratio, 60° windows took place at the point of critical pressure. At that time, the cold-flow crater in the high-pressure face had progressed to such a depth of the window body that the small cracks at the bottom of the crater united with the cracks progressing from the window bearing surface at the cone-to-cylinder transition zone, and a conical fracture surface was created. When the conical fracture surface was generated, the center portion of the window was ejected first, followed immediately by the remainder propelled by the high-velocity stream of water.

One-Inch-Diameter, 90° Conical Windows

The 1-inch-diameter, 90° conical windows failed in a manner similar to the 60° windows. The low t/D ratio windows failed by ejection of the center portion of the window with the rest remaining in the flange. The intermediate and high t/D ratio windows in most cases failed by complete fragmentation. The low t/D ratio windows failed without cold flow (Figures B-12 and B-13), while those with intermediate and high t/D ratios exhibited cold flow. The phases of window deformation were the same as in the 60° windows, except that the magnitudes of deformation were different for the same t/D ratios. Again, as in the 60° windows, one could see the minute cold flow on the high- and low-pressure faces in Phase 1 (Figures B-14 and B-15) and the fair amount of cold flow in Phase 2 (Figures B-16 and B-17). The basic difference in Phases 1 and 2 of the 90° windows from the corresponding phases of the 60° windows lay in the amount of cold flow at the same pressure. While the cold flow was extensive for the 60° windows, for the 90° windows only slight indication of it was evident. Thus, when a comparison was made between a 60° and a 90° window from interrupted failure tests, one could see that although both windows had the same t/D ratio (0.625) and both had been pressurized to 26,600 psi prior to removal from the vessel, only the 60° window exhibited cold flow extensively on both the high-pressure and low-pressure faces (Figures B-6 and B-18).

One-Inch-Diameter, 120° Conical Windows

In the $0.125 \leq t/D \leq 0.625$ range of ratios, conical windows failed consistently by fracturing in the middle, so that the center portion was ejected (Figures B-19 through B-24) while the remainder of the window was retained by the mounting flange. This was quite different from the failure of 60° and 90° windows, where the center portion of the window was ejected only in the low and intermediate $0.125 \leq t/D \leq 0.375$ range of ratios, while at the high t/D ratios the whole window was invariably ejected.

During some of the testing (arrested failures) it was possible to retrieve the center portion. Close inspection of this portion revealed that the mechanism of failure of the 120° windows was quite complex, as the center portion exhibited, in addition to the cold-flow crater on the high-pressure face, a conical fracture cavity on the low-pressure face which also showed signs of cold-flow displacement into the cylindrical opening in the mounting flange.

Thus, a typical 120° window, as exemplified by the 0.5 t/D ratio window in Figures B-25 and B-26, had two fracture cones, an inner one and an outer one. The latter surrounded the whole center portion of the window generally ejected from the flange in small fragments. In the example shown of a typical 120° window failure, the center portion, including the inner fracture cone, was not ejected from the flange, but retrieved from a basket hung immediately below it on the high-pressure side of the window. The reason in this case for the center portion of the window not being ejected was probably the fact that the apex of the inner fracture cone on the low-pressure face met the apex of the cold-flow crater on the high-pressure face, creating a passage for the fluid and thus permitting the pressure in the vessel to be relieved a split second before the center portion of the specimen was extruded sufficiently to be ejected through the cylindrical opening in the flange.

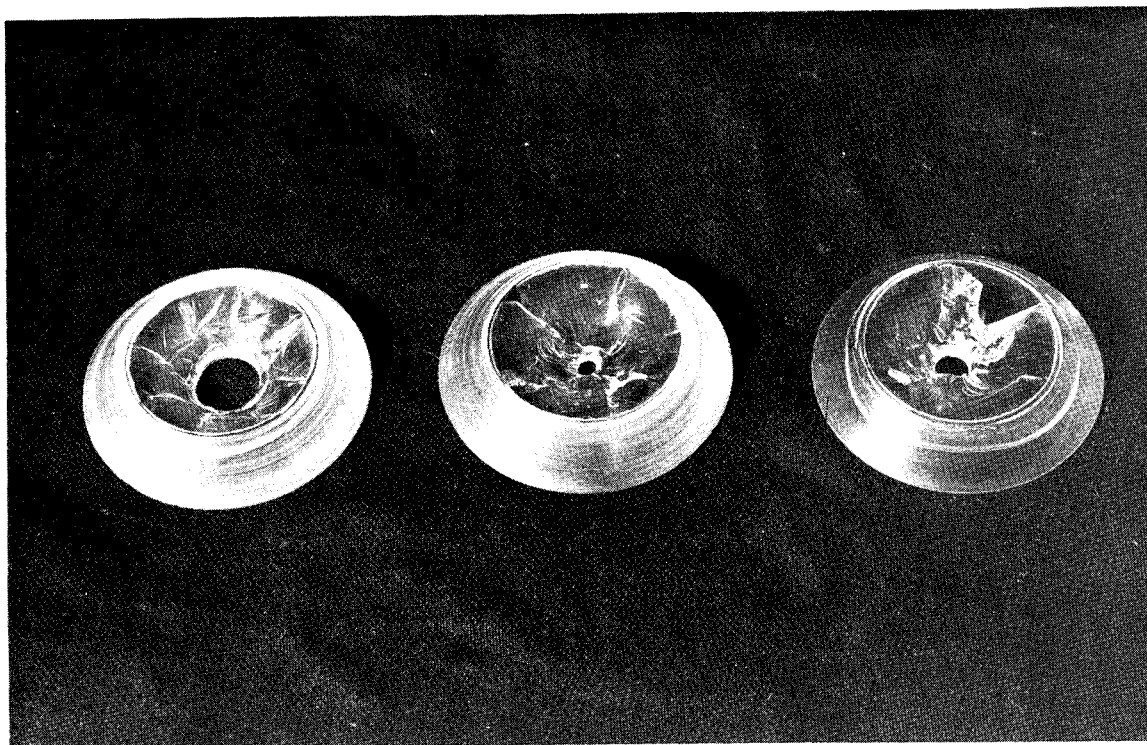


Figure B-12. Failed 1-inch-diameter, 90° , 0.25 t/D ratio windows, low-pressure faces.

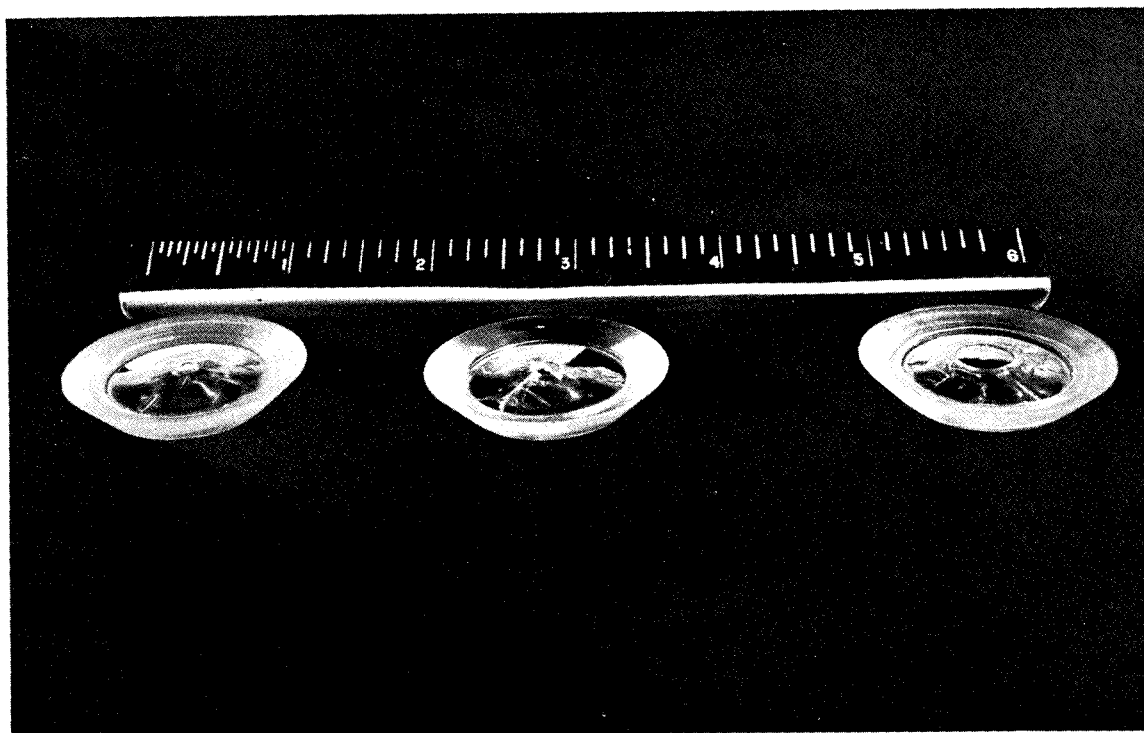


Figure B-13. Failed 1-inch-diameter, 90° , 0.25 t/D ratio windows, high-pressure faces.

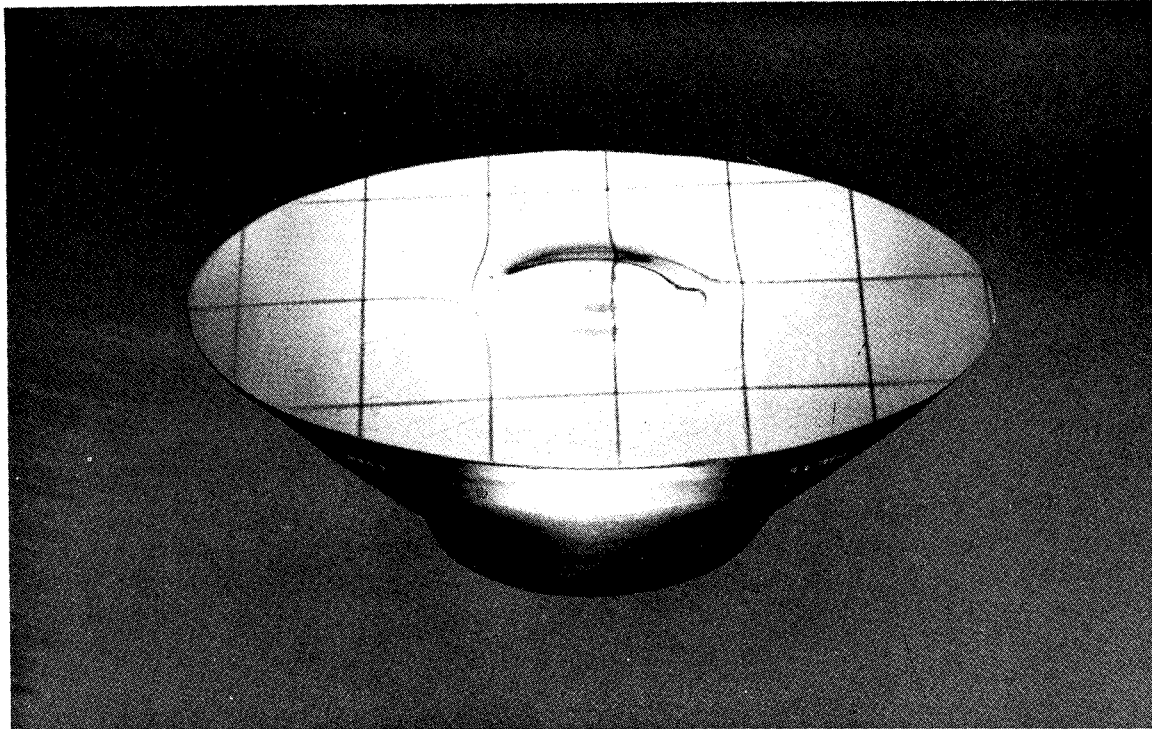


Figure B-14. Arrested failure of 1-inch-diameter, 90° , 0.625 t/D ratio window at 26,500 psi, high-pressure face. (Phase 1 of deformation.)

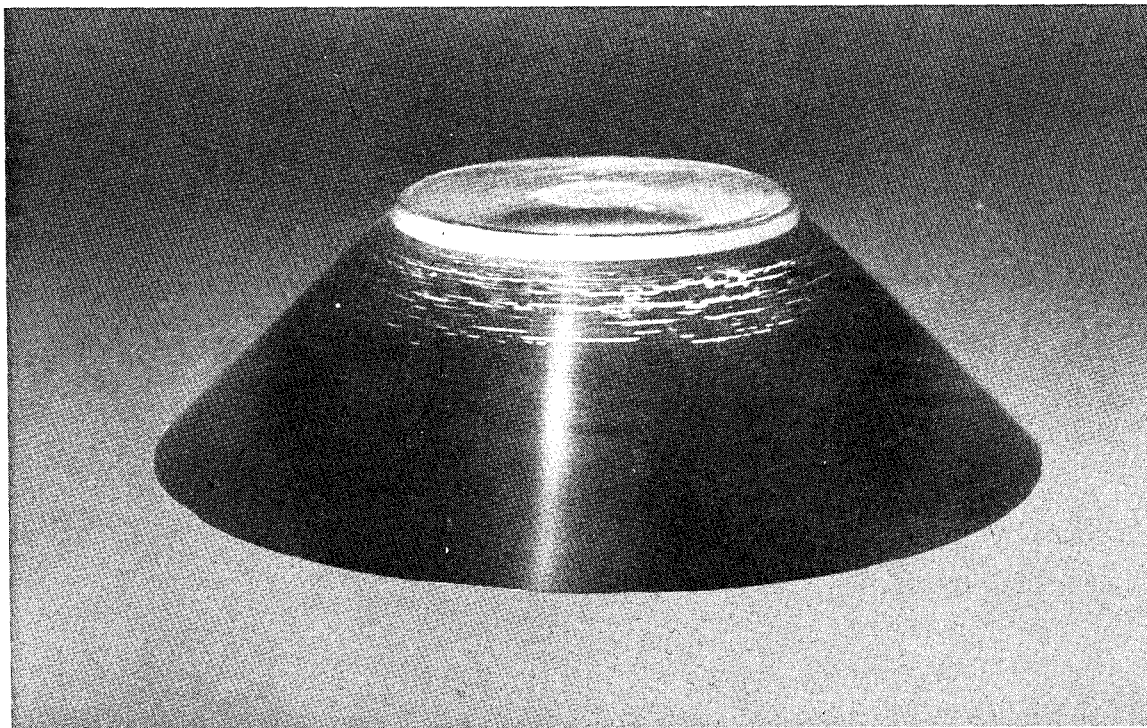


Figure B-15. Arrested failure of 1-inch-diameter, 90° , 0.625 t/D ratio window at 26,500 psi, low-pressure face. (Phase 1 of deformation.)

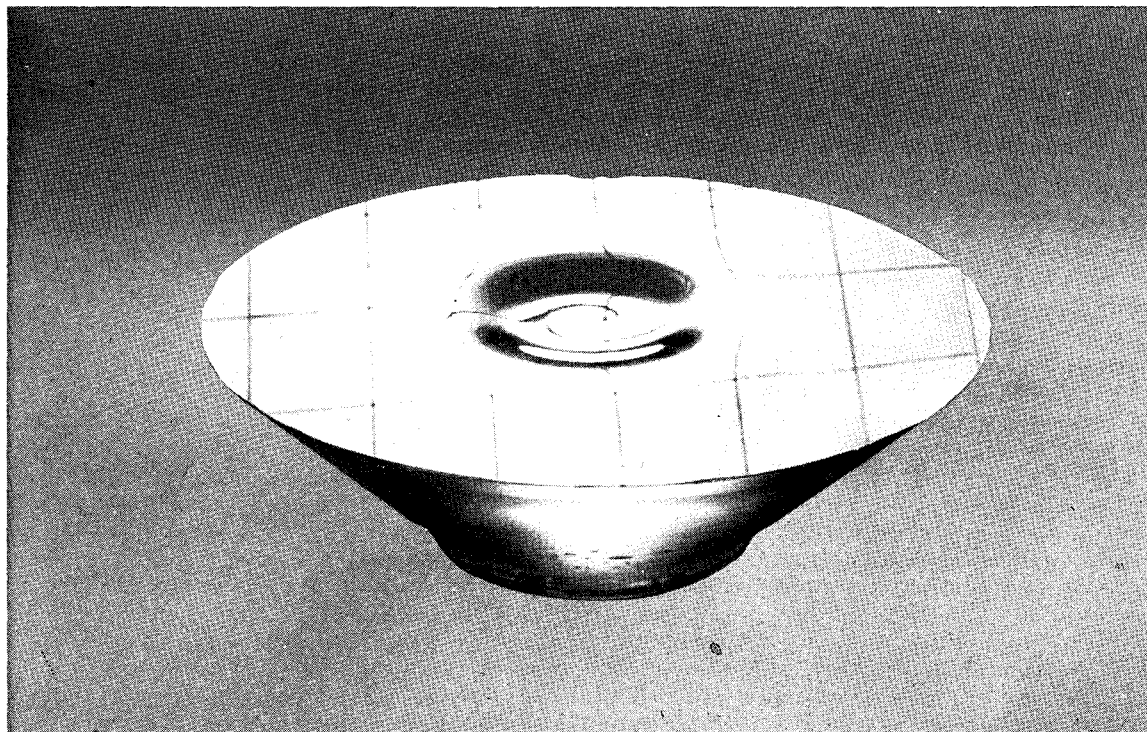


Figure B-16. Arrested failure of 1-inch-diameter, 90° , 0.625 t/D ratio window at 28,600 psi, high-pressure face. (Phase 2 of deformation.)

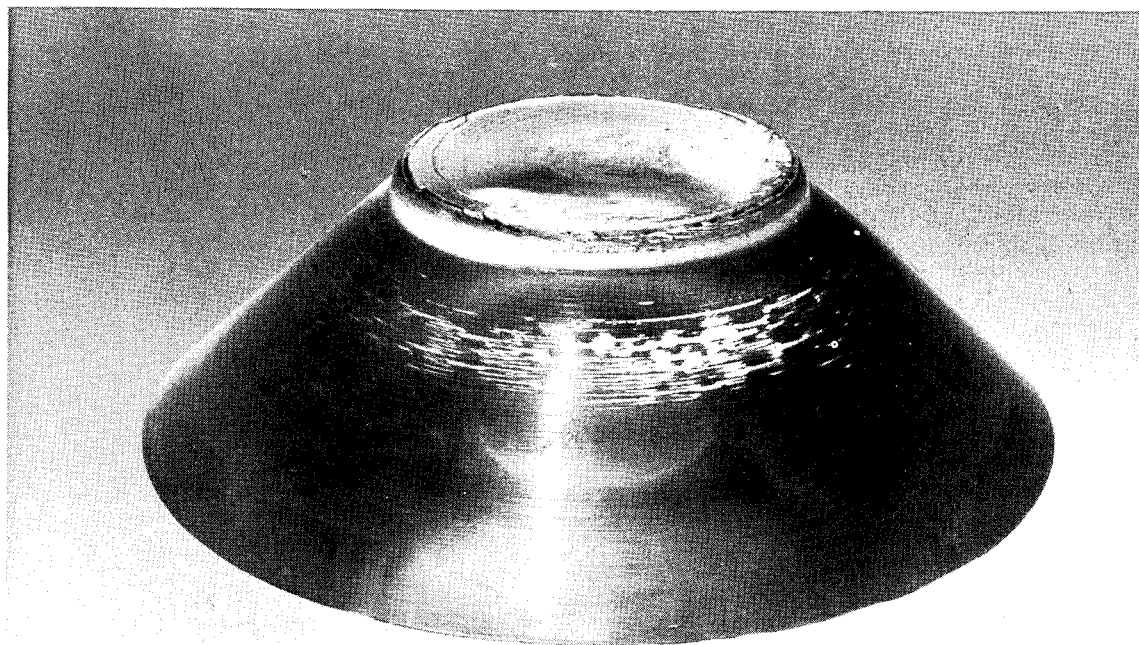


Figure B-17. Arrested failure of 1-inch-diameter, 90° , 0.625 t/D ratio window at 28,600 psi, low-pressure face. (Phase 2 of deformation.)

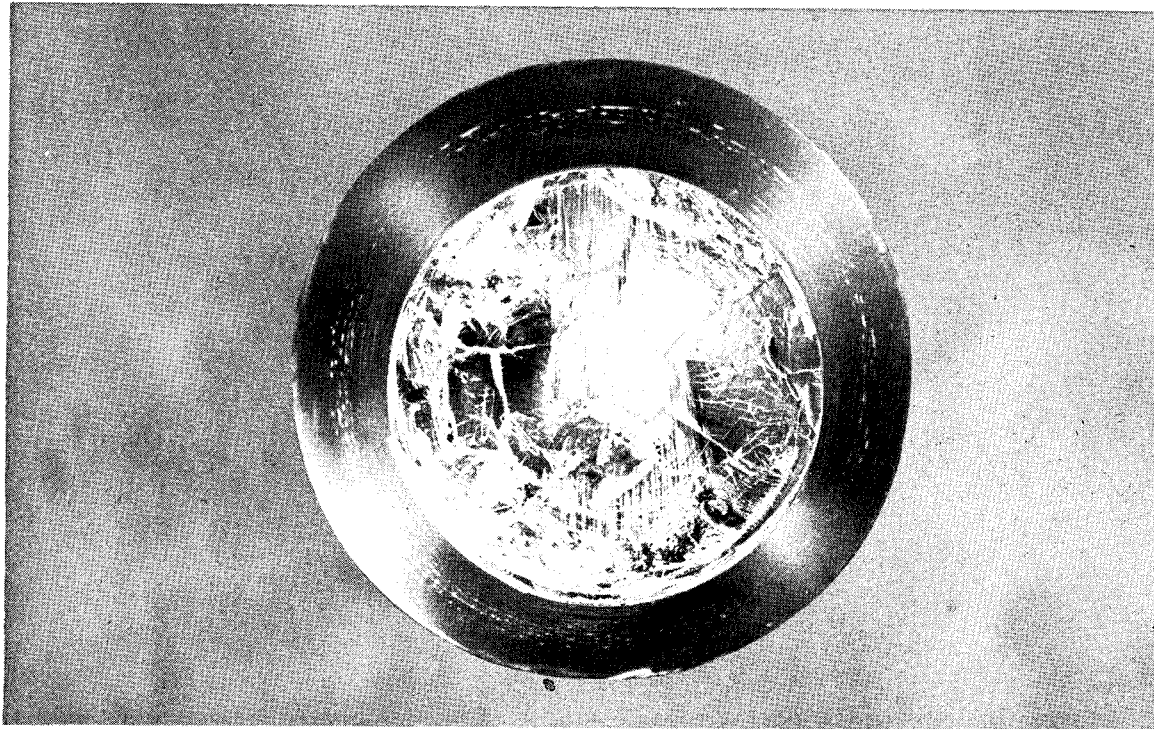


Figure B-18. Arrested failure of 1-inch-diameter, 60° , 0.625 t/D ratio window at 26,600 psi, low-pressure face.

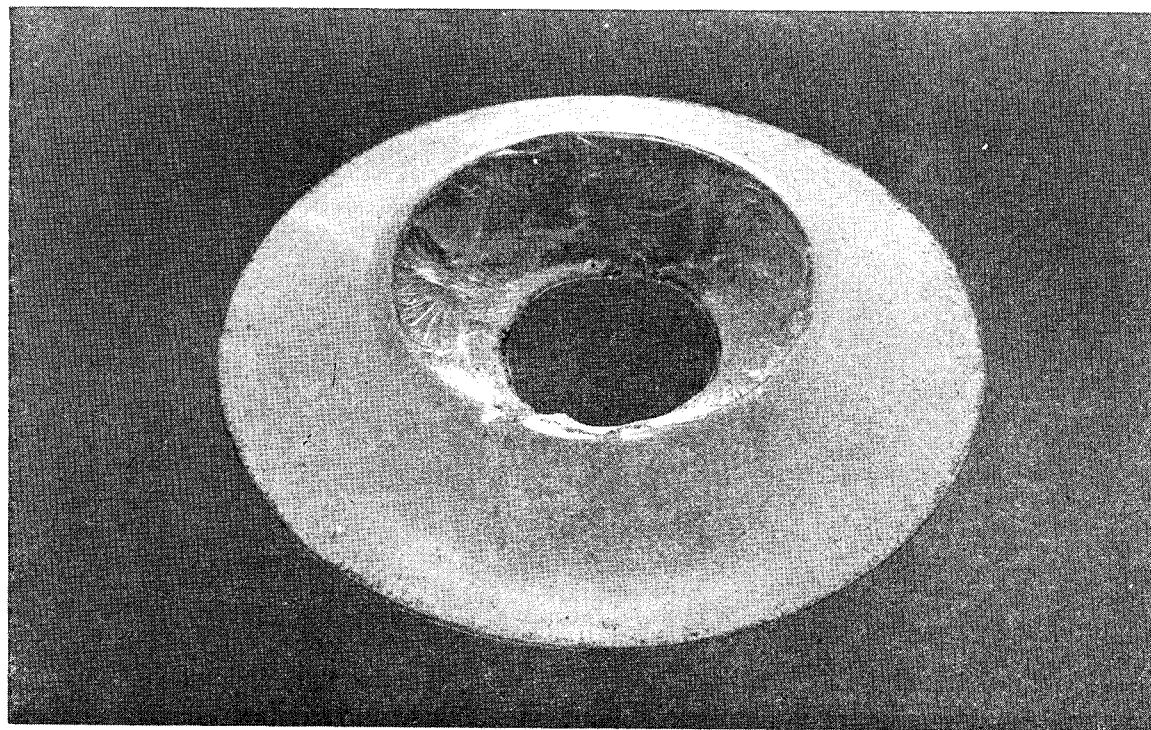


Figure B-19. Failed 1-inch-diameter, 120° , 0.25 t/D ratio window, low-pressure face.

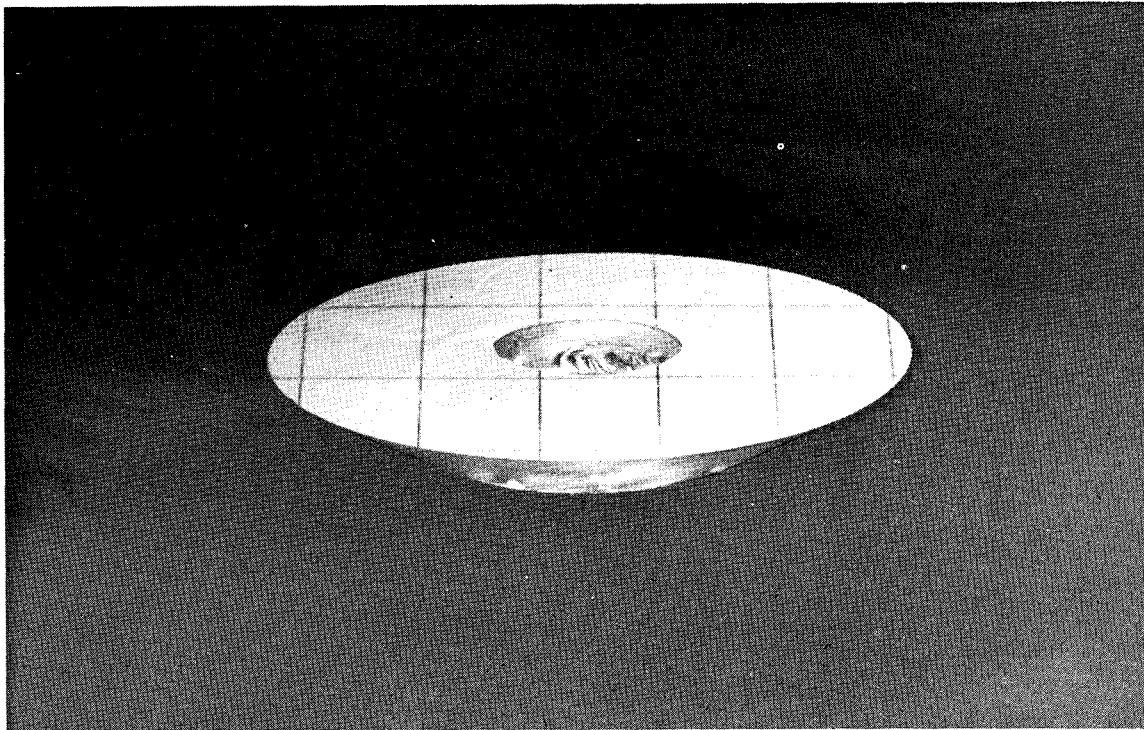


Figure B-20. Failed 1-inch-diameter, 120° , 0.25 t/D ratio window, high-pressure face.

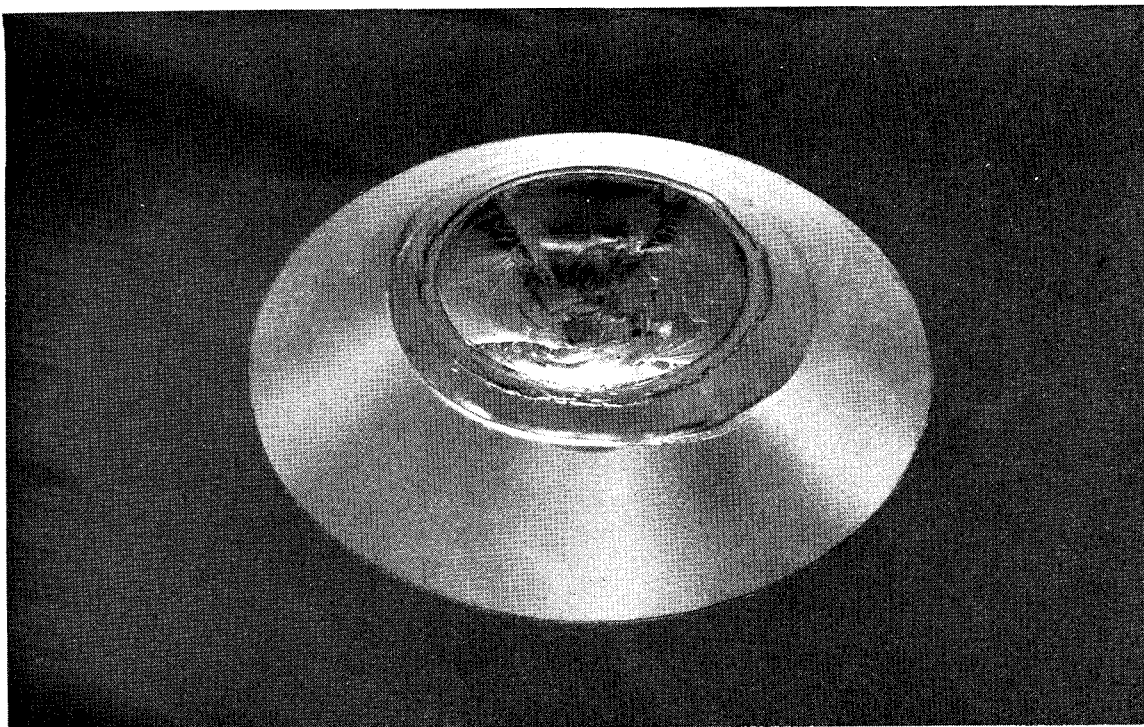


Figure B-21. Failed 1-inch-diameter, 120° , 0.375 t/D ratio window, low-pressure face.

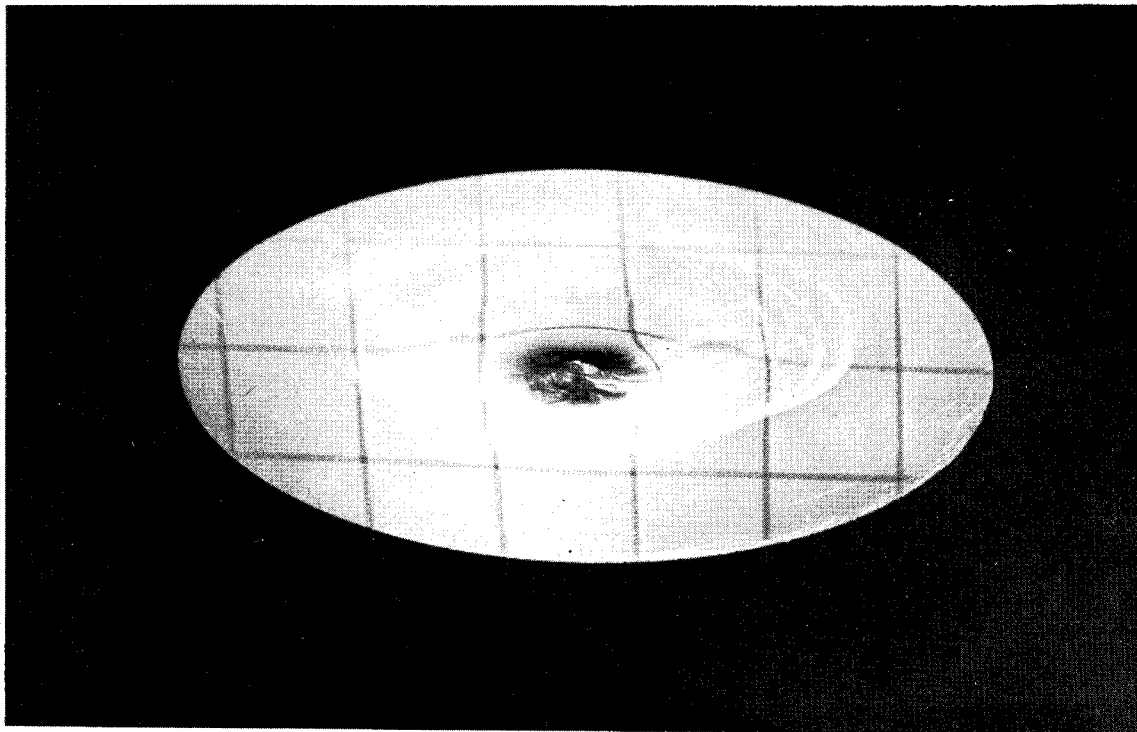


Figure B-22. Failed 1-inch-diameter, 120° , 0.375 t/D ratio window, high-pressure face.

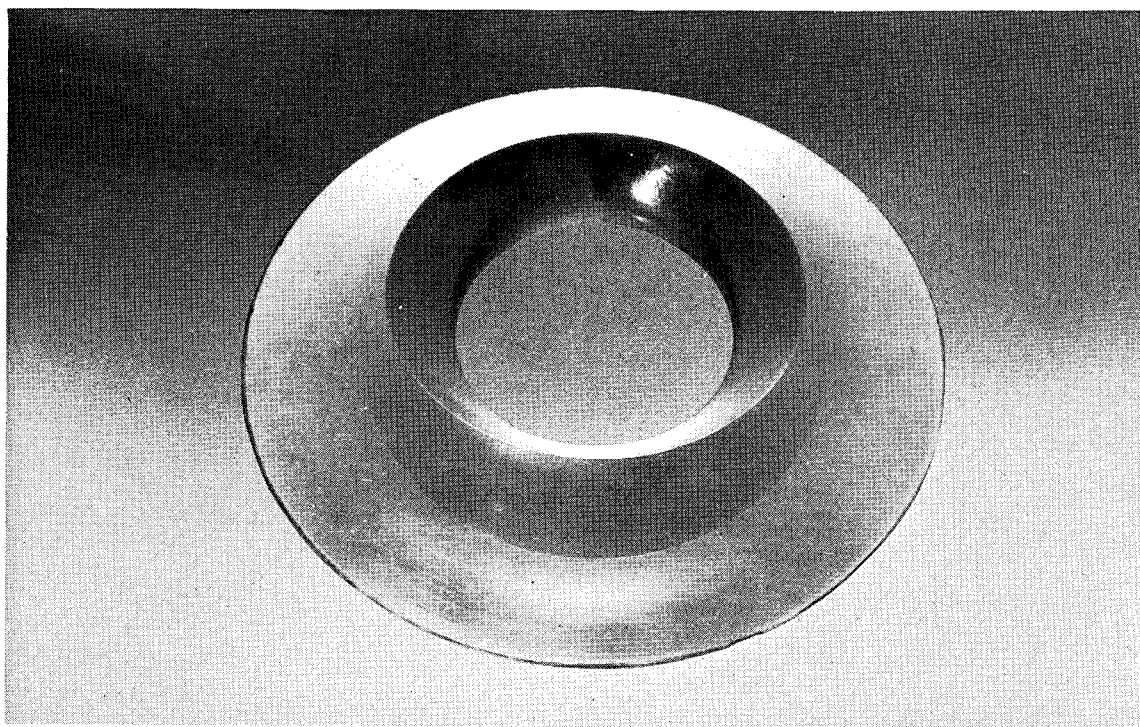


Figure B-23. Failed 1-inch-diameter, 120° , 0.625 t/D ratio window, low-pressure face.

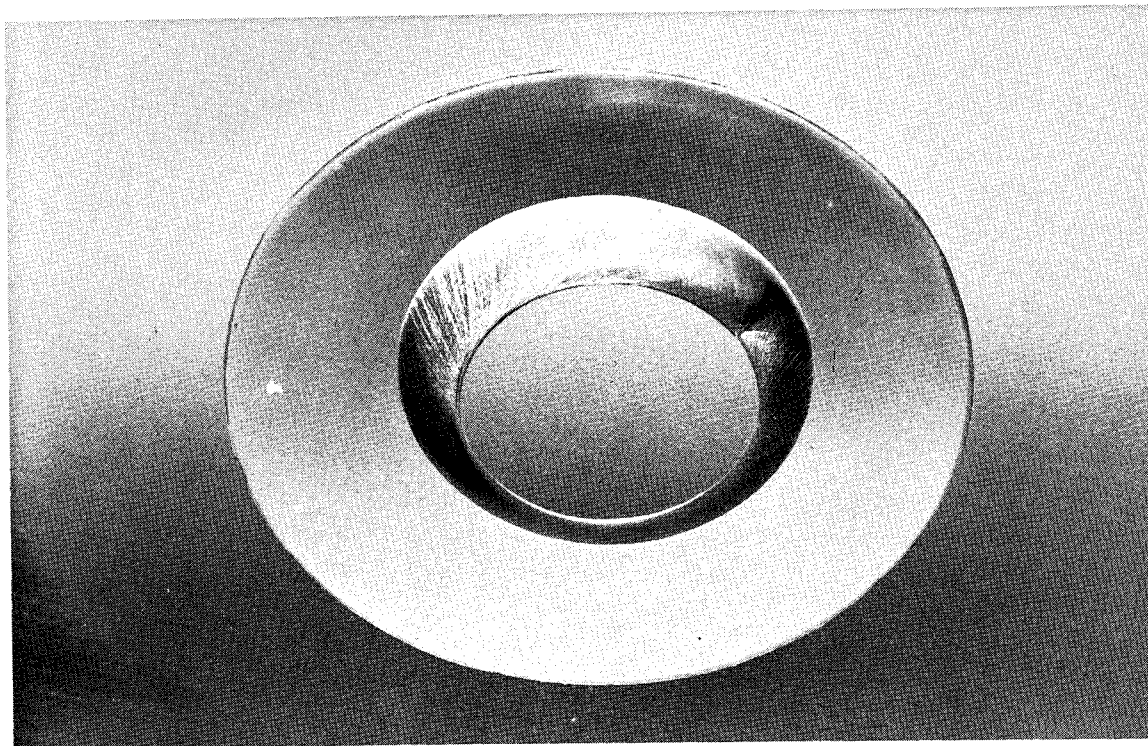


Figure B-24. Failed 1-inch-diameter, 120°, 0.625 t/D ratio window, high-pressure face.

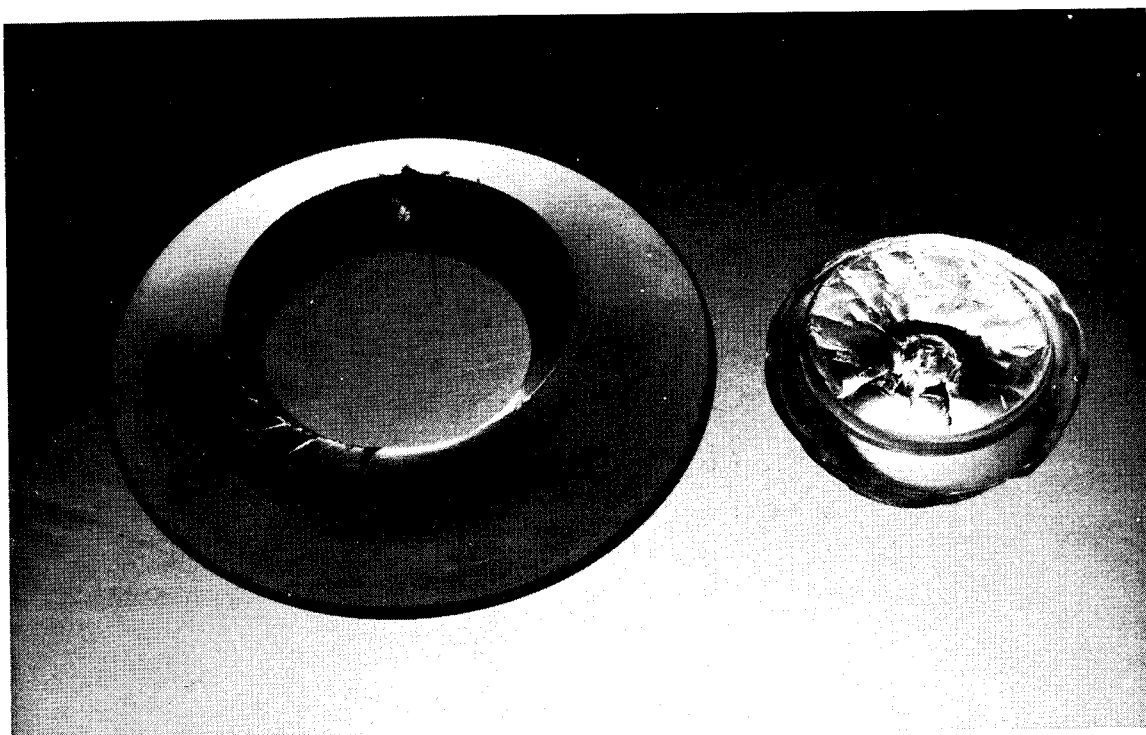


Figure B-25. Failed 1-inch-diameter, 120°, 0.5 t/D ratio window, low-pressure face, with center portion alongside.

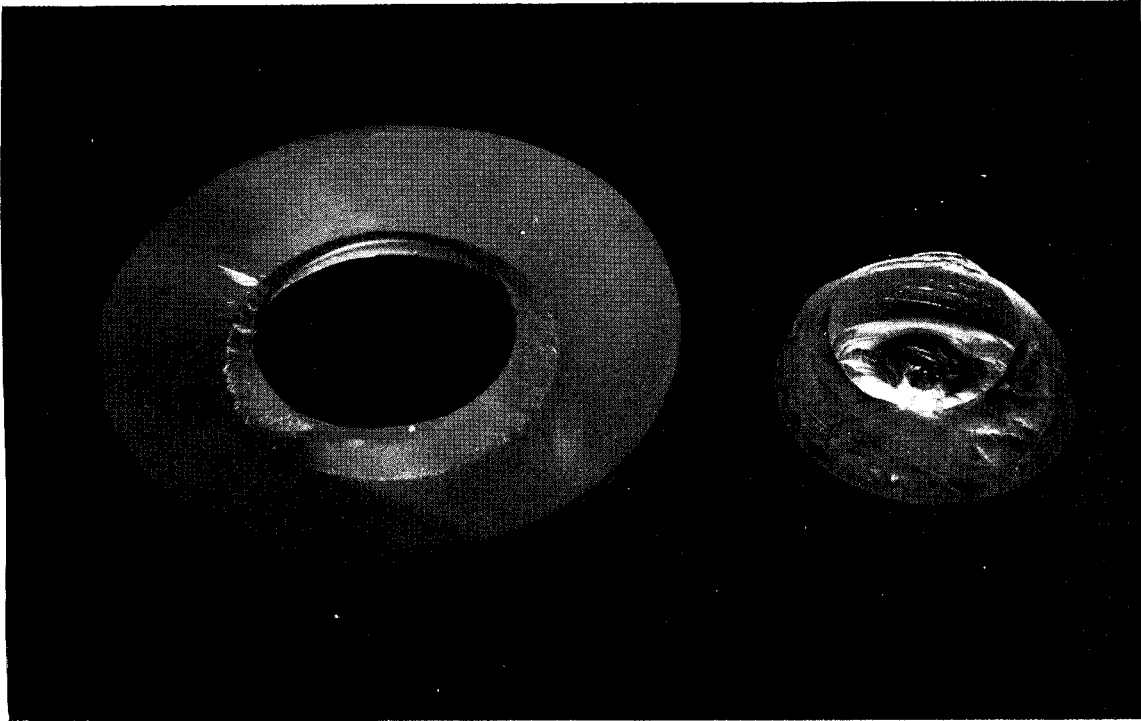


Figure B-26. Failed 1-inch-diameter, 120° , 0.5 t/D ratio window, high-pressure face, with center portion alongside.

From inspection of the retrieved window center portion, and of the outer ring-shaped fragment, as well as other windows whose testing was terminated before ejection, it can be postulated that cracks in the 120° windows were initiated at three locations. The one where cracks first appeared, at approximately 70% of critical pressure, was below the shape-transition zone on the bearing surface of the window (Figures B-27 and B-28). The cracks initiated here were continuous around the circumference of the window, and propagated themselves into the interior of the window body at approximately right angles to the conical surface.

The second location of crack initiation lay on the high-pressure face of the window. The cracks appeared here later than at the shape-transition zone and were not as continuous as those in the first location. The cracks on the high-pressure face were generated on the periphery of the cold-flow crater, which became noticeable in the 120° conical windows only at hydrostatic pressures in excess of 70% of the window critical pressure (Figure B-29).

The third location where cracks were generated was around the circumference of the low-pressure face. These cracks appear only after those in the other locations have grown to considerable proportions. It can be shown that the cracks on the low-pressure face had not yet developed (Figures B-30 and B-31) in windows with $0.5 \leq t/D \leq 0.625$ ratios at approximately 90% of the window critical pressure. Therefore, they must appear at pressures higher than 90% of critical pressure.

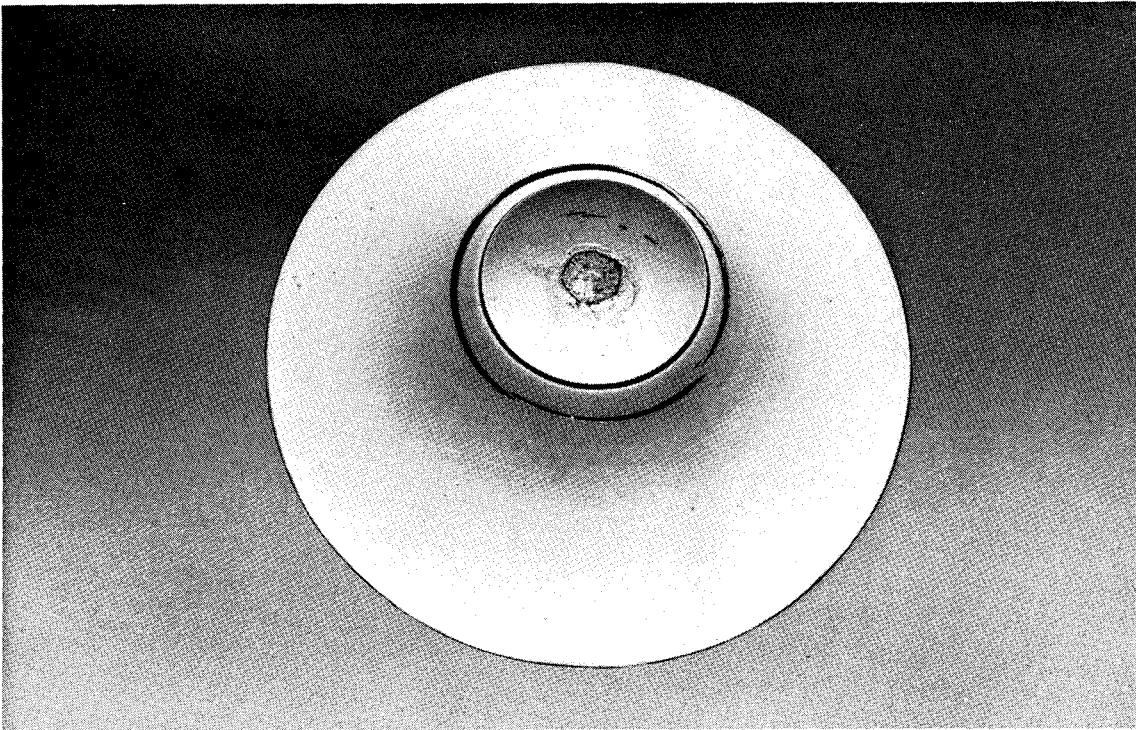


Figure B-27. Arrested failure of 1-inch-diameter, 120° , 0.625 t/D ratio window at 22,500 psi, low-pressure face.

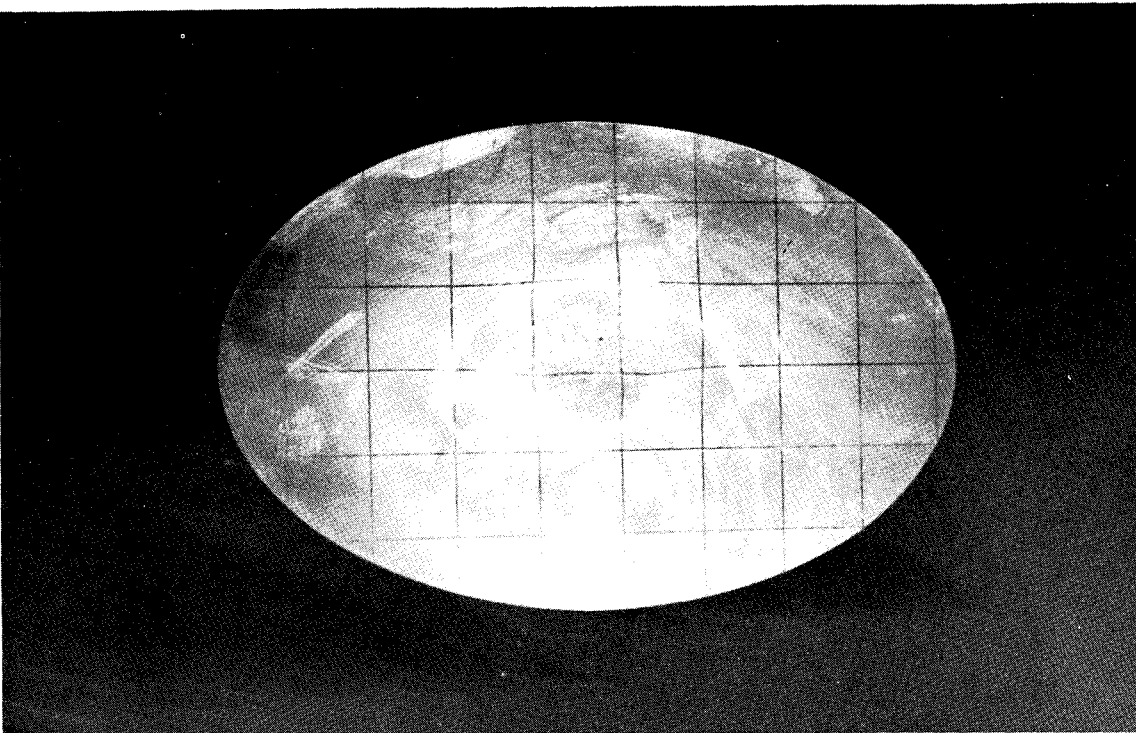


Figure B-28. Arrested failure of 1-inch-diameter, 120° , 0.625 t/D ratio window at 22,500 psi, high-pressure face.

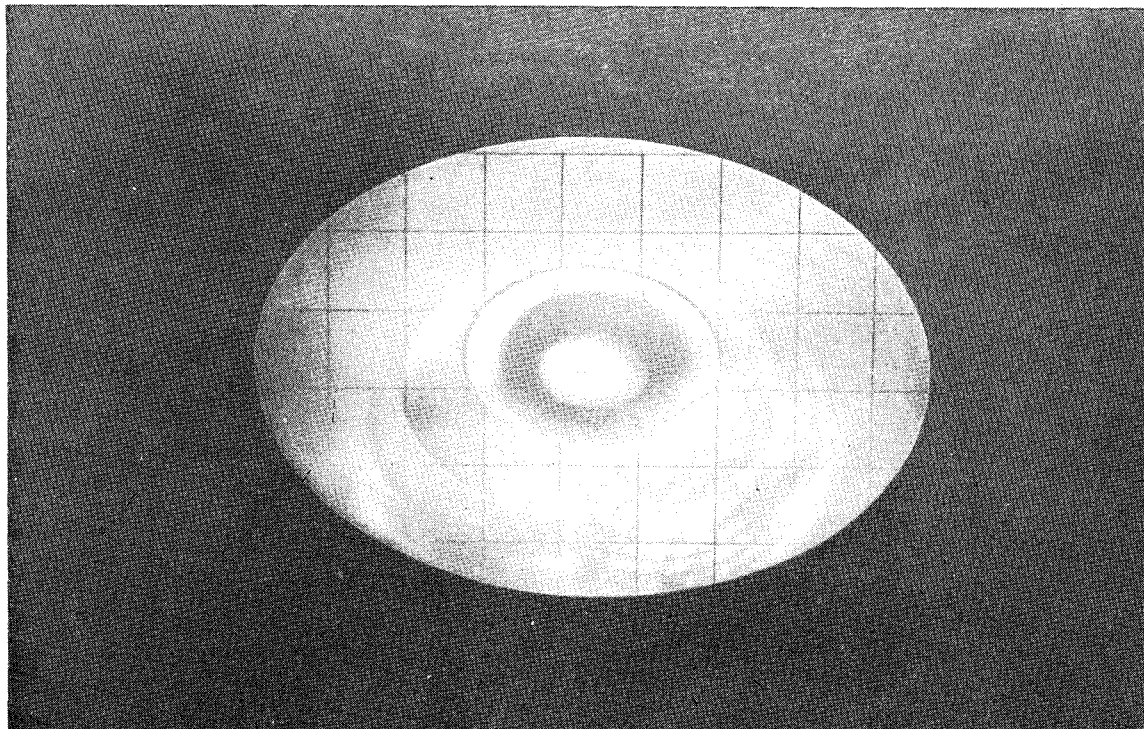


Figure B-29. Arrested failure of 1-inch-diameter, 120° , 0.625 t/D ratio window at 26,000 psi, high-pressure face.

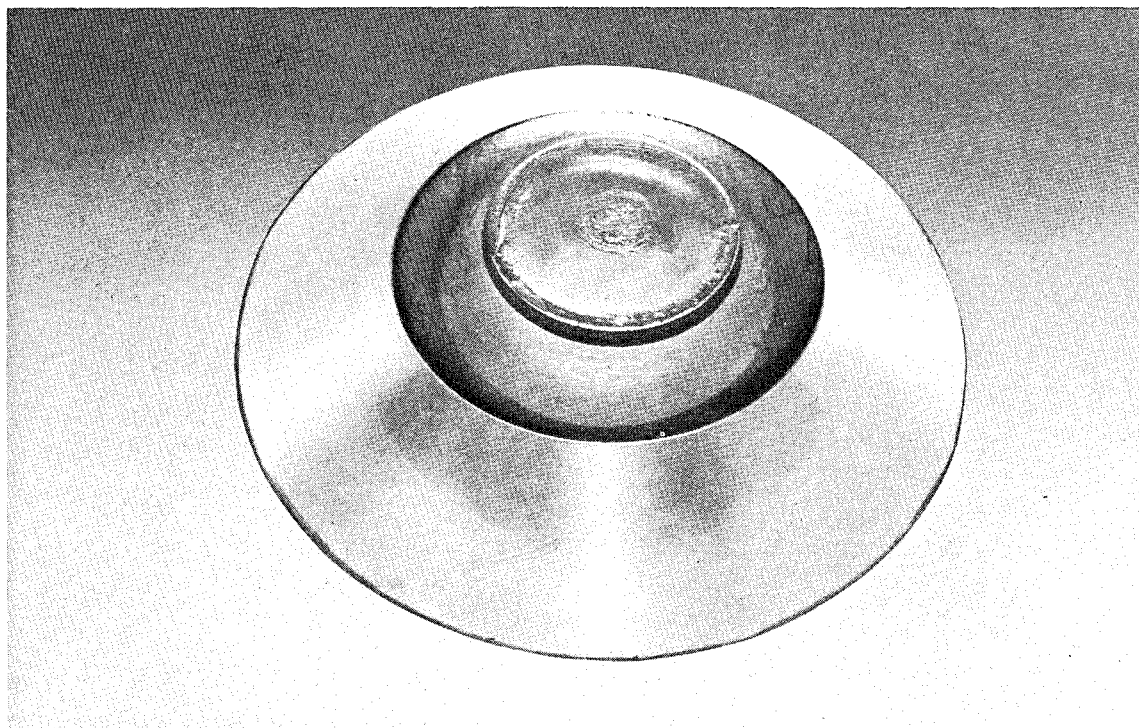


Figure B-30. Arrested failure of 1-inch-diameter, 120° , 0.625 t/D ratio window at 26,000 psi, low-pressure face.

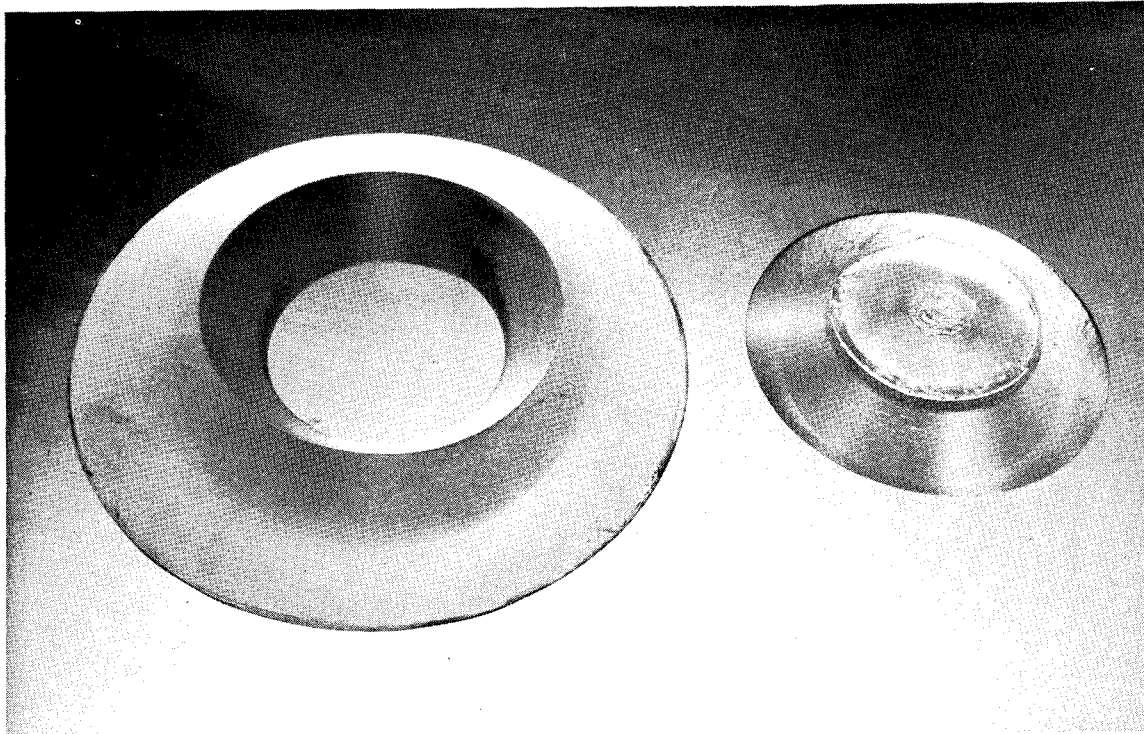


Figure B-31. Arrested failure of 1-inch-diameter, 120° , 0.625 t/D ratio window at 26,000 psi, low-pressure face, with center portion alongside.

The 1-inch-diameter, 150° conical windows failed essentially in the same manner as the 120° windows, by ejection of the center portion, except that the center portions of the 0.125 t/D ratio windows were not ejected when the window critical pressure was reached. The reason for this failure to eject was that upon propagation of cracks in the window (Figures B-32 and B-33) at critical pressure, the center of the window deflected into the flange cylindrical opening to such an extent that the seal between the conical surface of the window and that of the flange cavity was broken, thus relieving the hydrostatic pressure in the vessel. (If the vessel had been of very large capacity, or the window in a structure submerged in the ocean, where infinite hydrostatic energy exists, the center of the 0.125 t/D window would also have ejected, though some leakage around the conical window surface would have occurred just prior to the ejection.)

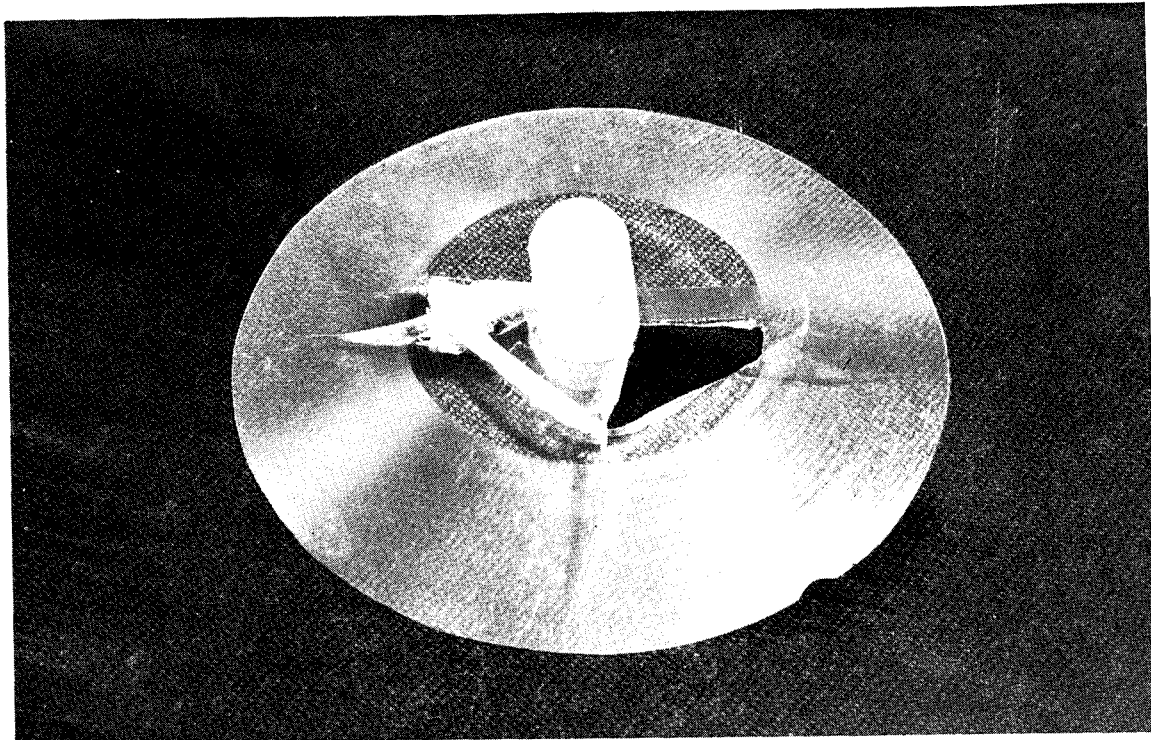


Figure B-32. Failed 1-inch-diameter, 150°, 0.125 t/D ratio window, low-pressure face, with displacement indicator anchor attached.

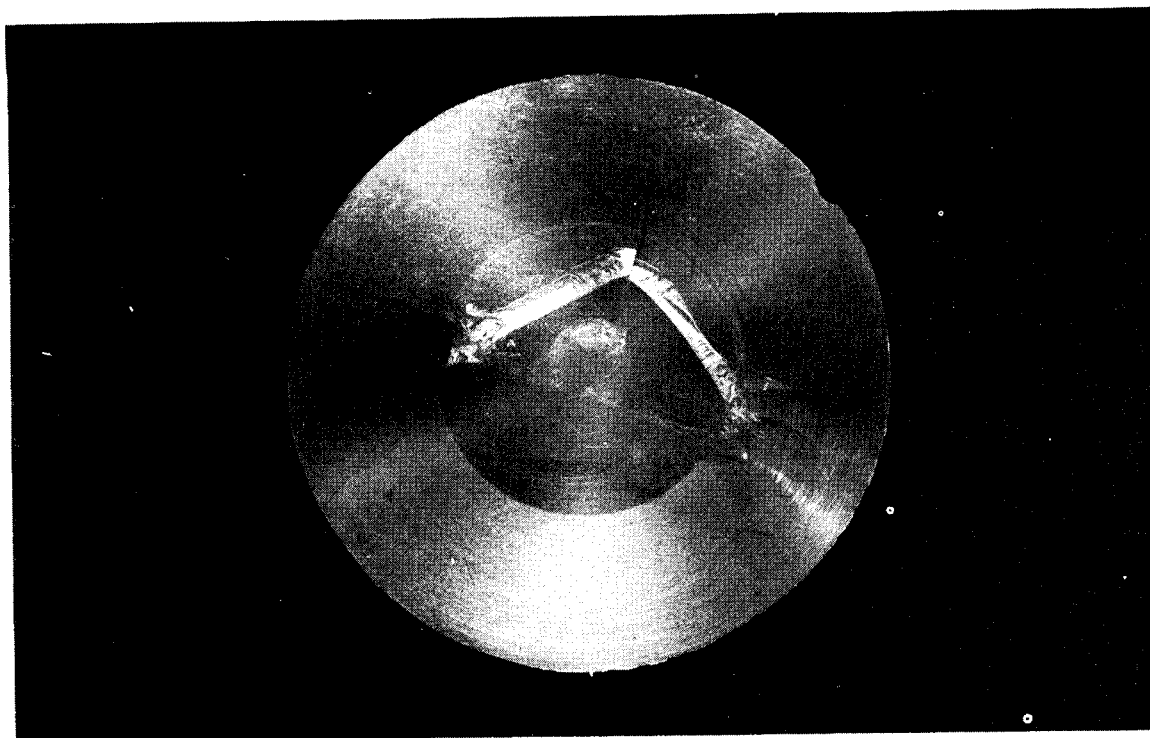


Figure B-33. Failed 1-inch-diameter, 150°, 0.125 t/D ratio window, high-pressure face.

That this was the mechanism of failure for the 0.125 t/D windows was evidenced on 0.25 t/D windows in the transition t/D range between windows whose center was ejected every time in the test, and windows whose center was not ejected because of prior leakage around the conical sealing surfaces. Thus, in 0.25 t/D windows, three different types of failure occurred. One type (Figures B-34 and B-35) was the same as for the 0.125 t/D ratio windows, where the presence of radial cracks in the center of the window permitted it to deflect to such an extent that the seal was lost between window and flange. The second type of failure for the 0.25 t/D ratio windows was a central fracture cone which originated from circumferential cracks on the window low-pressure face. This fracture cone, also previously found in 0.25 t/D windows with 60°, 90° and 120° angles, was characterized by ragged fracture surfaces, and the fact that its outside diameter was approximately 1 inch (the diameter of the window low-pressure face). The third type of failure of 0.25 t/D ratio windows was the presence of two fracture cones in the center portion of the window. The inner one was initiated by the circumferential cracks on the window low-pressure face, while the outer fracture cone started from a circumferential crack on the window bearing surface below (on the conical side) the shape-transition zone. The outer fracture cone, so typical of previously tested 120° conical windows, had a smooth cleavage surface, and its major diameter was invariably larger than the diameter of the low-pressure face.

The 150° windows with t/D ratios larger than 0.25 invariably failed by ejection of the window center portion bounded by the outer fracture cone (Figures B-36 through B-39). The inner fracture cone that started at the low-pressure face was also present in all these windows, except that it generally was not found after window failure, since it lay within the body of material ejected at critical pressure. Close inspection of a 0.625 t/D window which was loaded to only approximately 80% of its critical pressure confirmed this. In this arrested-failure specimen, three fracture cones could actually be seen (Figure B-40). The outer cone fracture had already penetrated the whole thickness of the window body, while the two inner cone fractures had penetrated only partially. The high-pressure face of the window exhibited a well-defined cold-flow crater bounded by the outer fracture cone (Figure B-41). Beyond the boundary of the outer fracture cone the high-pressure face of the window showed no traces of cold-flow cratering (Figure B-42).

Two-Inch-Diameter, 30° Conical Windows

All 2-inch-diameter, 30° conical windows failed by being ejected from the vessel. Their critical pressures were in the same pressure range as the critical pressures of 1-inch-diameter, 30° windows. The displacements for the two types of windows were different. The ratio between the displacements of the 2-inch- and the 1-inch-diameter windows was found to be roughly 2:1. This would seem to indicate that the displacements of 30° conical windows are proportional to their minor diameter.

Four-and-One-Half-Inch-Diameter, 60° Conical Windows

The 4.5-inch-diameter, 60° conical windows, except for the 0.25 t/D ratio specimens, were ejected completely from the mounting flange on failure. When the remains of the 4.5-inch-diameter, 0.25 t/D ratio windows (Figures B-43 and B-44), retained in the flange, were compared to the remains of 1-inch-diameter windows with the same t/D ratio, it became apparent that the mechanisms of failure must have been similar, for the appearance of the retained window fragment was the same in both cases. Since the center portion of the 4.5-inch-diameter, 0.25 t/D ratio window was not ejected from the vessel, due to premature pressure relief through a crack in that section, it was available for observation. The center portion showed deformation of both the high- and low-pressure faces. The deformation of the high-pressure face was a typical cold-flow crater, while the conical cavity on the low-pressure face was generated by fracturing of the material. The whole center portion of the window was separated from the rest of the window body by a shear cone surface. Thus, there were actually two fracture cones, the outer one which permitted the center portion of the window to separate from the ring-shaped fragment retained by the flange, and the inner one which allowed a conical cavity to be created on the low-pressure face of the window.

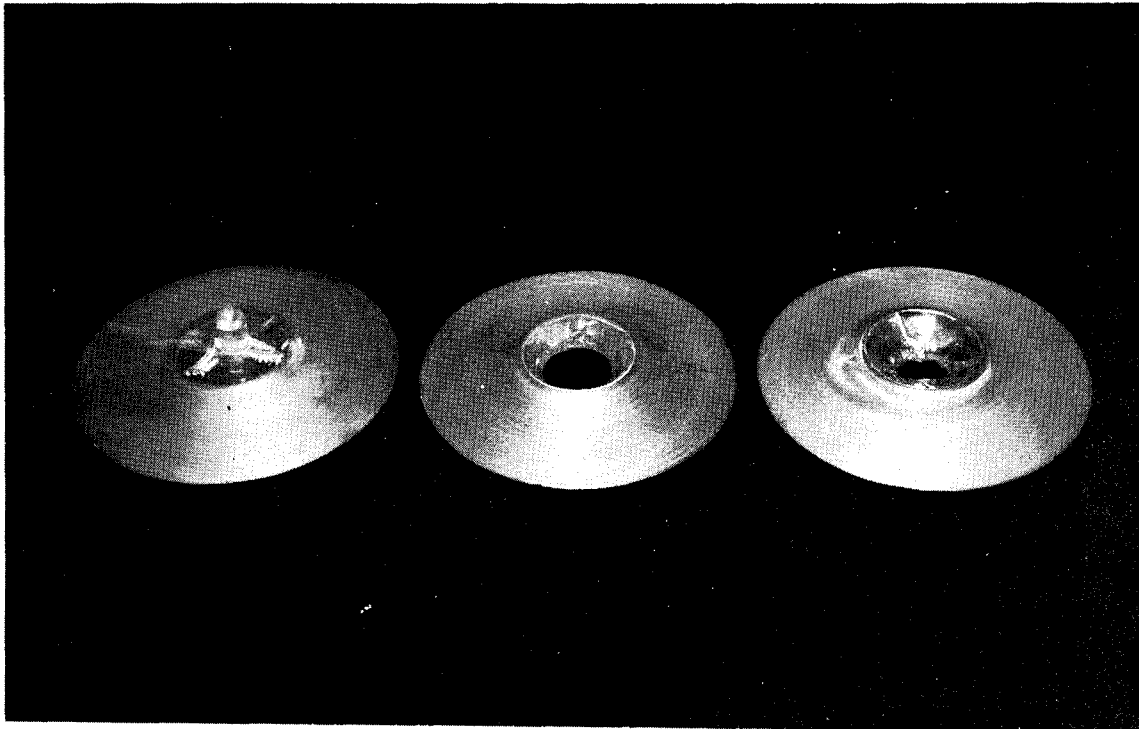


Figure B-34. Failed 1-inch-diameter, 150°, 0.25 t/D ratio windows, low-pressure faces.

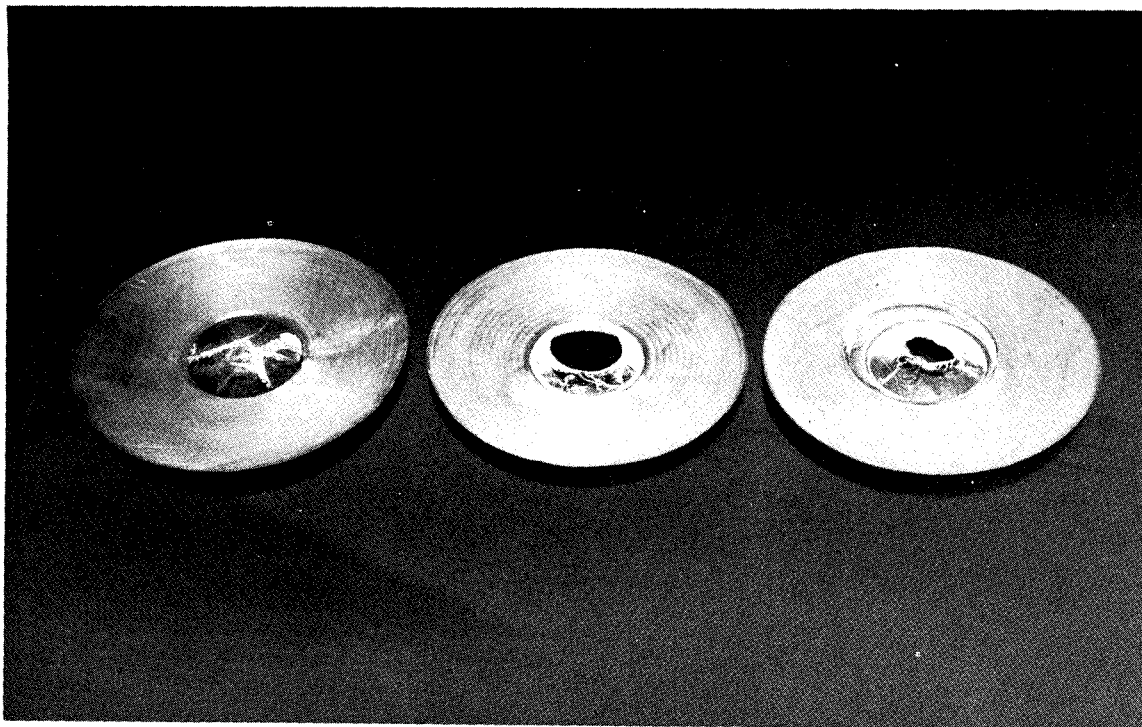


Figure B-35. Failed 1-inch-diameter, 150°, 0.25 t/D ratio windows, high-pressure faces.

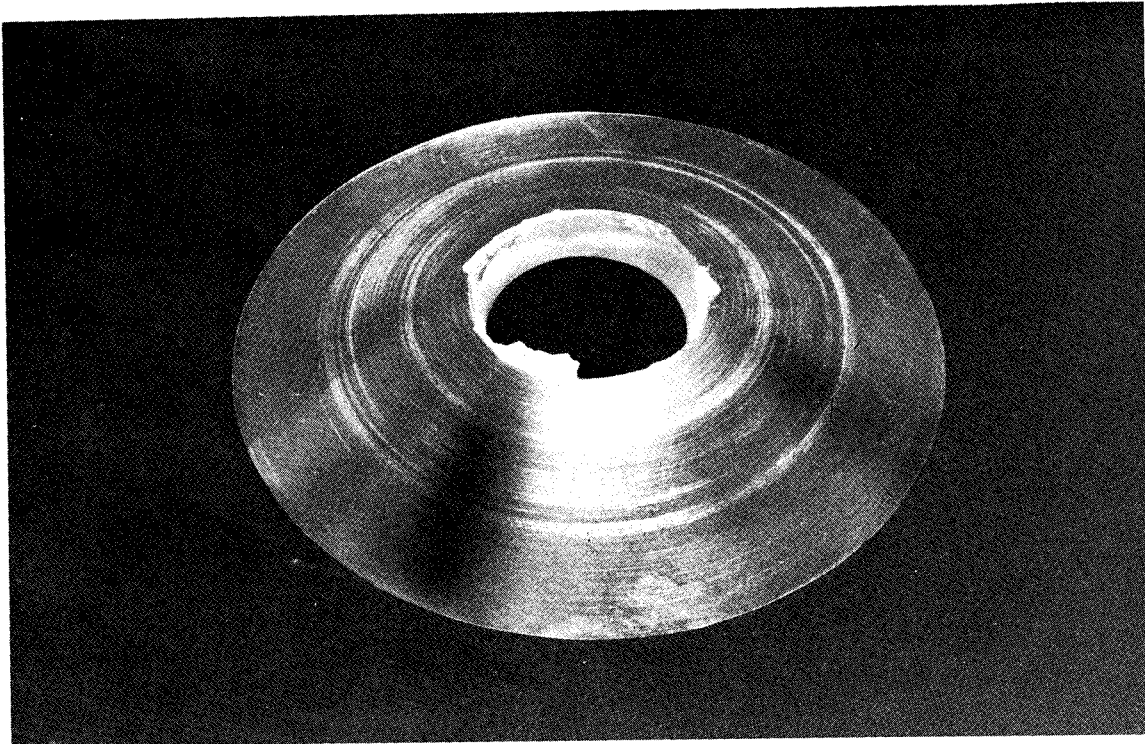


Figure B-36. Failed 1-inch-diameter, 150° , 0.5 t/D ratio window, low-pressure face.

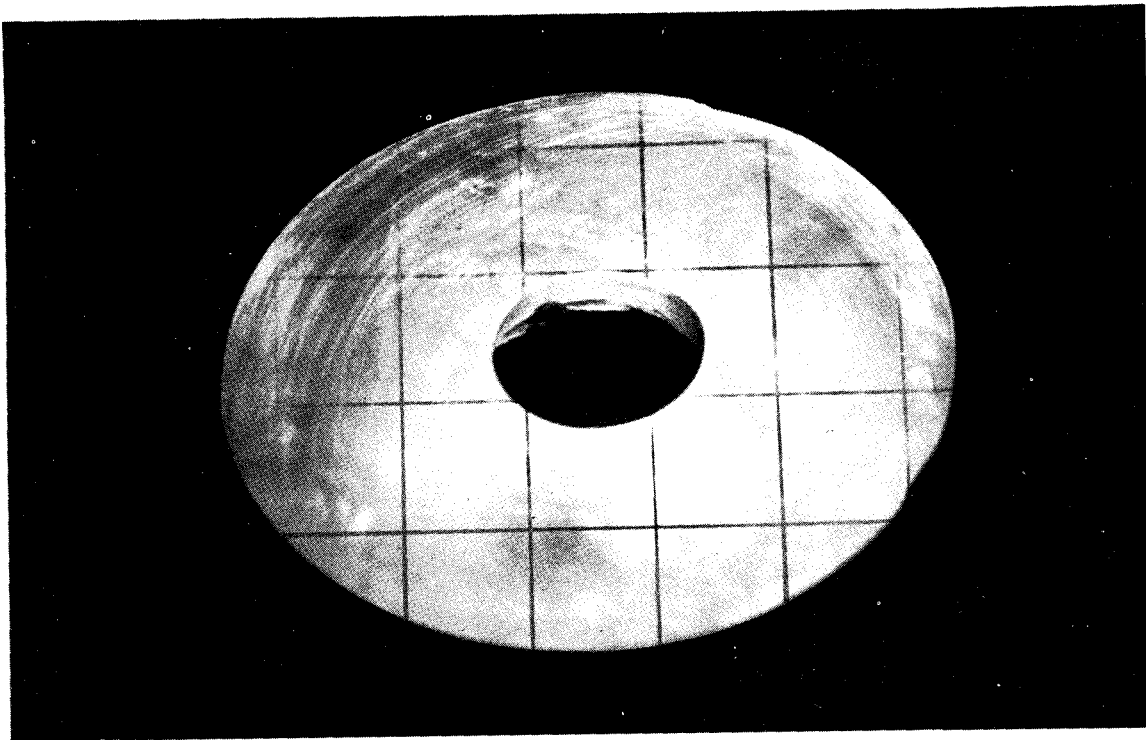


Figure B-37. Failed 1-inch-diameter, 150° , 0.5 t/D ratio window, high-pressure face.

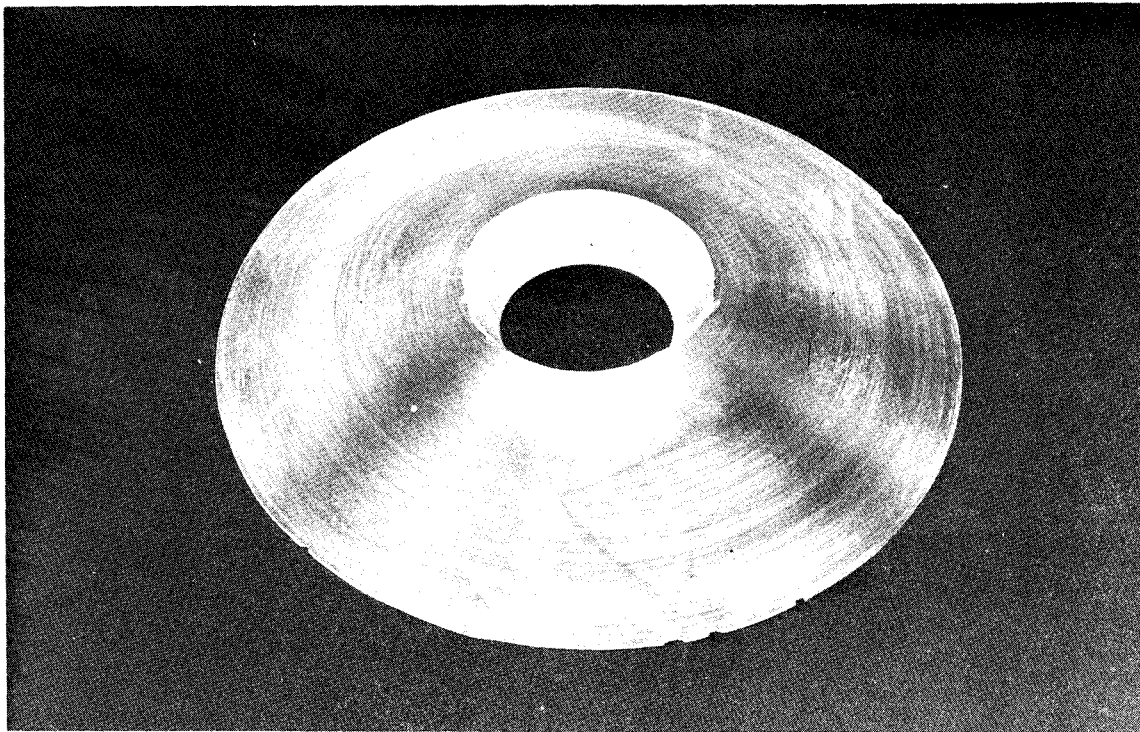


Figure B-38. Failed 1-inch-diameter, 150° , 0.625 t/D ratio window, low-pressure face.

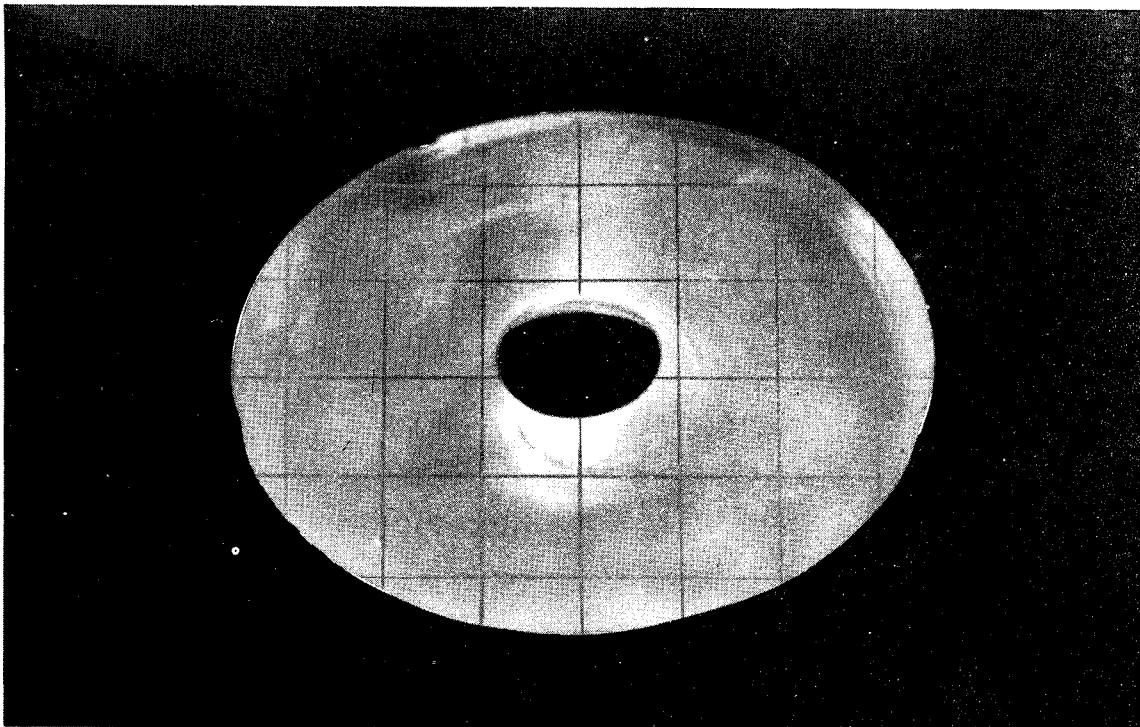


Figure B-39. Failed 1-inch-diameter, 150° , 0.625 t/D ratio window, high-pressure face.

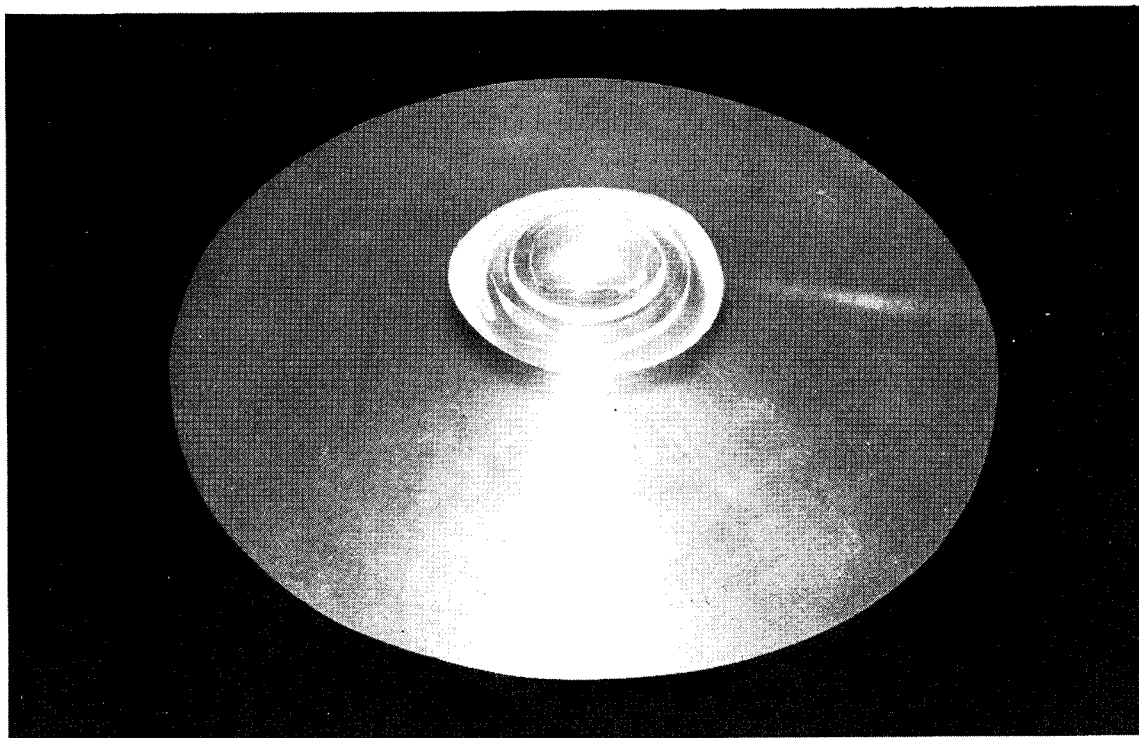


Figure B-40. Arrested failure of 1-inch-diameter, 150° , 0.625 t/D ratio window at 24,000 psi, low-pressure face.

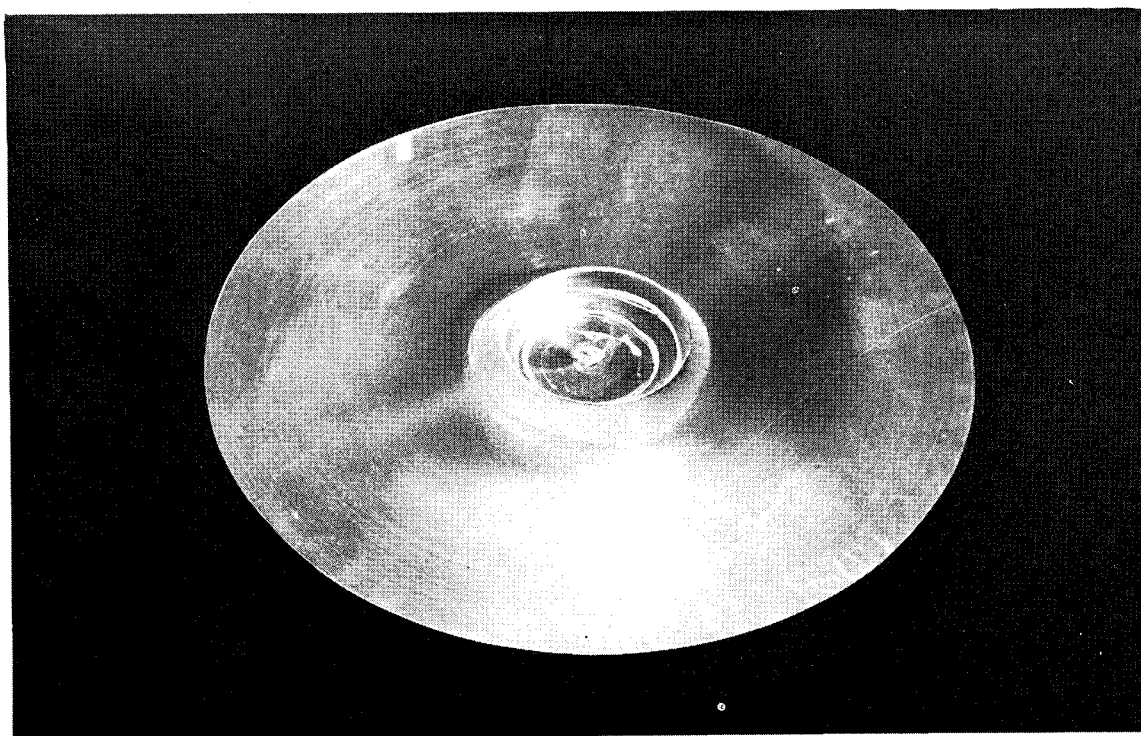


Figure B-41. Arrested failure of 1-inch-diameter, 150° , 0.625 t/D ratio window at 24,000 psi, high-pressure face. (Cold-flow crater bounded by outer fracture cone.)

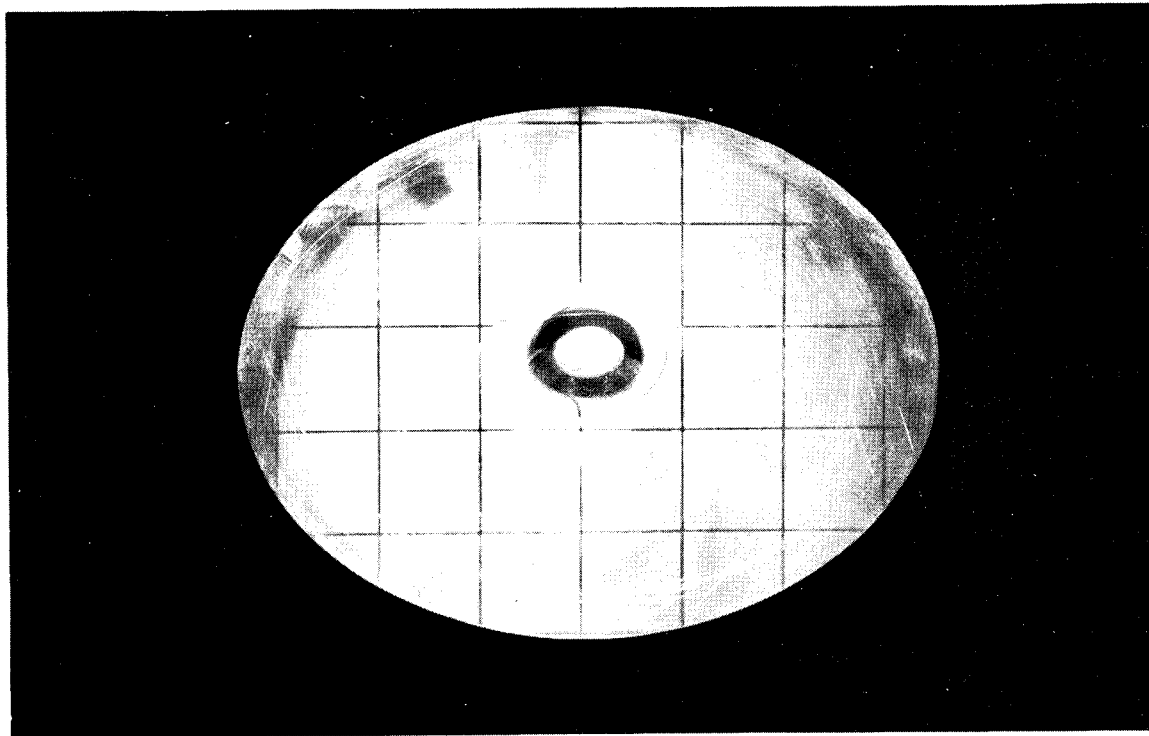


Figure B-42. Arrested failure of 1-inch-diameter, 150° , 0.625 t/D ratio window at 24,000 psi, high-pressure face. (No cold-flow crater beyond outer fracture cone.)

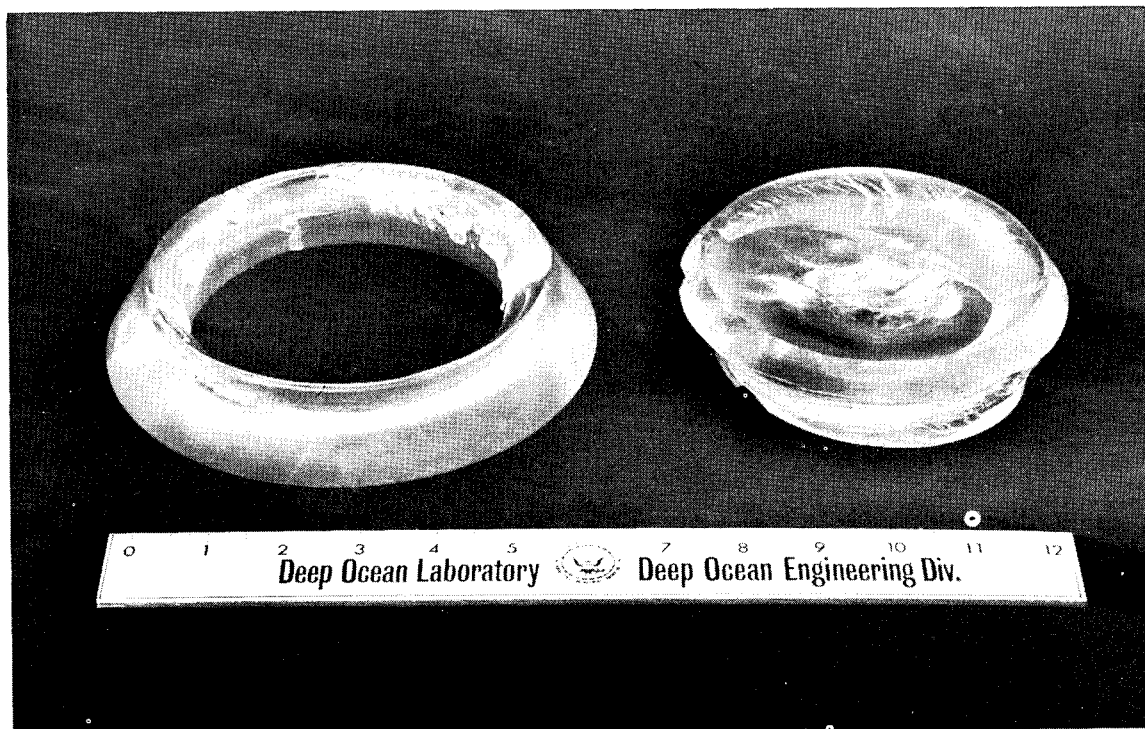


Figure B-43. Failed 4.5-inch-diameter, 60° , 0.25 t/D ratio window, low-pressure face, with center portion alongside.

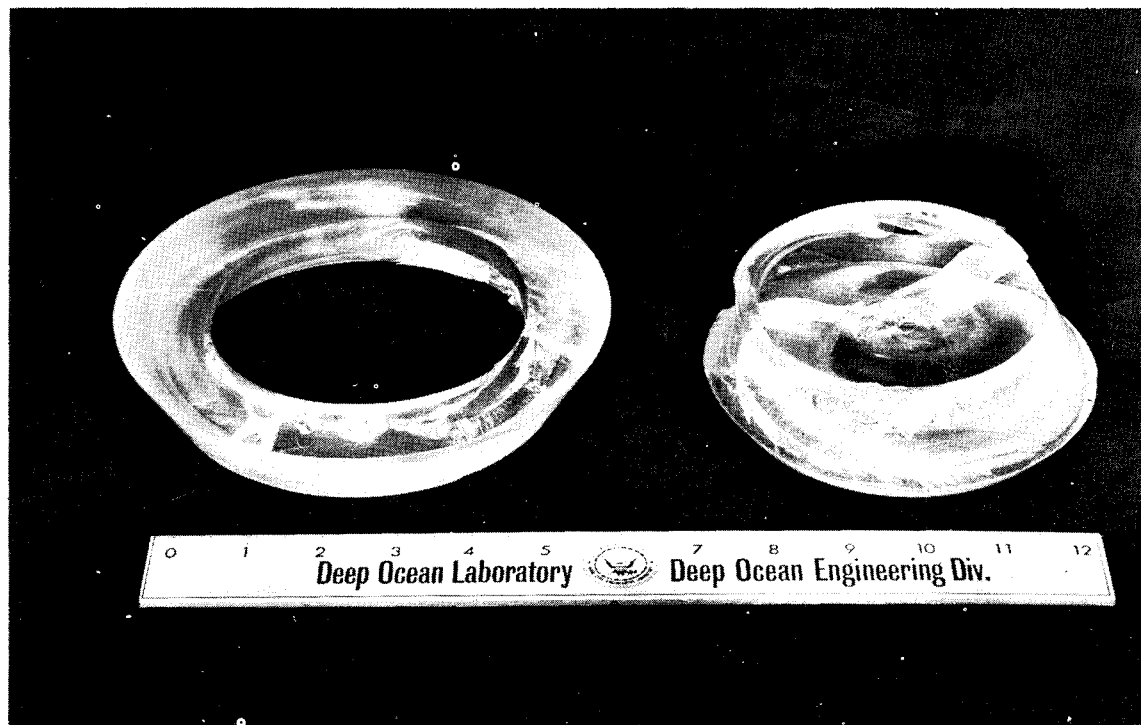


Figure B-44. Failed 4.5-inch-diameter, 60°, 0.25 t/D ratio window, high-pressure face, with center portion alongside.

Eight-Inch-Diameter, 90° Conical Windows

When the 8-inch-diameter, 4-inch-thick conical window with 90° included angle was subjected to increasing hydrostatic pressure, it failed by fracturing (Figure B-45) in a manner similar to 1-inch-diameter windows of the same t/D ratio (0.5) and included angle. The failure of the two types of windows at the same critical pressure lends considerable affirmation to the postulate that the critical pressure data obtained with 1-inch-diameter conical windows is applicable to larger conical windows provided they have the same included angle and t/D ratio.



Figure B-45. Failed 8-inch-diameter, 90°, 0.5 t/D ratio window, high-pressure face, shown in mounting flange.

Appendix C

STATISTICAL EVALUATION OF THE SIZE OF THE SAMPLE GROUPS

To conduct a check as to whether the average of five experimental values is an adequate representation of the experimentally determined variable, ten specimens instead of five were tested for the 30° and 90° conical windows with a 0.5 t/D nominal ratio. The average critical pressure of the first five 30° windows tested was 8,600 psi (Table G-4, Appendix G) while that of the second five windows was 8,270 psi (Table G-5, Appendix G). When statistical methods were applied to determine the significance of the difference between the two means, it was found that the standard error of the difference was 366 psi. Since the difference between the means was 330 psi, and thus less than three standard errors of the difference for these two groups, it evidently resulted from chance and was of no significance.

The same type of analysis of experimental data derived from testing of two groups of 90° windows with five 0.5 t/D ratio windows in each (Tables G-20 and G-21, Appendix G) showed that the difference between the average critical pressures of 16,820 and 15,940 of the two groups was 880 psi, while the standard error of the difference amounted to 700 psi. This indicated that the difference between the average critical pressures of the two 90° window groups was also due solely to chance, since the difference between the average critical pressures of the two groups was less than three standard errors of the difference for these two groups, and hence of no significance. Since the testing of an additional five windows of the same t/D ratio did not produce critical pressures that would be significantly different from the ones obtained by testing a single group of five windows, it can be postulated that the size of the window sample groups of same t/D ratio used in this study was sufficiently large and representative.

Appendix D

TEMPERATURE INFLUENCE EVALUATION TESTS

Besides the special tests performed on the 30° and 90° windows with a 0.5 t/D ratio to determine whether the experimental data produced by groups of five windows was repeatable, if additional groups of five were tested, tests were also performed to determine whether variation in the temperature of the mounting flange and the water adjacent to the window had significant influence on the critical pressure of the windows.

Low-temperature tests were conducted on a group of 30° windows with a 0.5 t/D ratio (Table G-6, Appendix G). The average critical pressure of the windows tested at temperatures of 35° to 40°F was higher than the average critical pressure of identical windows at 64° to 70°F in the standard temperature range (Table G-4, Appendix G) by 1,950 psi. When the standard error of the means was calculated for the critical pressures resulting from the low- and room-temperature tests, it was found to be 417 psi. Since the difference between the means of the low- and the room-temperature critical pressures was 1,950 psi, that difference was indicated as not due to chance but to some variable. Because no other additional variable was introduced into the tests other than temperature, it can be safely assumed that the difference in average critical pressures between the low- and room-temperature groups was caused by the influence of low temperature on the mechanical properties of acrylic plastic.

Appendix E

APPLICABILITY OF 1-INCH-DIAMETER WINDOW TEST DATA TO WINDOWS OF LARGER SIZES

The series of windows for the experimental validation of the t/D scaling ratio consisted of 2-inch-diameter, 30° windows with 0.125, 0.25 and 0.5 t/D ratios; 4.5-inch-diameter, 60° windows with 0.125, 0.25 and 0.5 t/D ratios; and 8-inch-diameter, 90° windows with 0.5 t/D ratios. It was reasoned that if the average critical pressures for these larger windows were approximately the same as for 1-inch-diameter windows of the same shape and t/D ratio, then the assumption that the t/D ratio is a valid scaling ratio would have been substantiated.

For the performance of critical pressure tests on the 2-inch-, 4.5-inch-, and 8-inch-diameter windows, the same experimental arrangement was followed as for the 1-inch-diameter windows except that larger mounting flanges of DOL Type I were used (Figures E-1, E-2, and E-3). Windows were fabricated again from Grade G Plexiglas to the same machining tolerances specified for the 1-inch-diameter windows. After being mounted in the appropriate flanges and subjected to the same experimental testing procedures as the 1-inch windows, the larger diameter windows were pressurized to failure.

A sufficient number of window specimens were so tested and compared in their critical pressures and displacements with 1-inch-diameter windows having the same t/D ratio and angle, that the relationship between the experimentally derived values for different window diameters could be established with reasonable confidence. The critical pressure curves (Figures 10, 12, 14, 16, 18) based on experimental data obtained with 1-inch-diameter windows were found to predict directly with reasonable accuracy the critical pressures of windows with diameters larger than 1 inch (Figures 20 and 22), provided they are composed of the same material, have the same t/D ratio and angle as the 1-inch-diameter windows, and are tested in DOL Type I mounting flanges.

The displacement curves based on experimental data derived from testing 1-inch-diameter windows (Figures 11, 13, 15, 17, and 19) do not predict directly the displacements of windows with a diameter larger than 1 inch (Figures 21 and 23). The displacements of windows with the same t/D ratio and angle but a diameter larger than 1 inch, however, are in the elastic range approximately proportional to the minor diameter of the window.

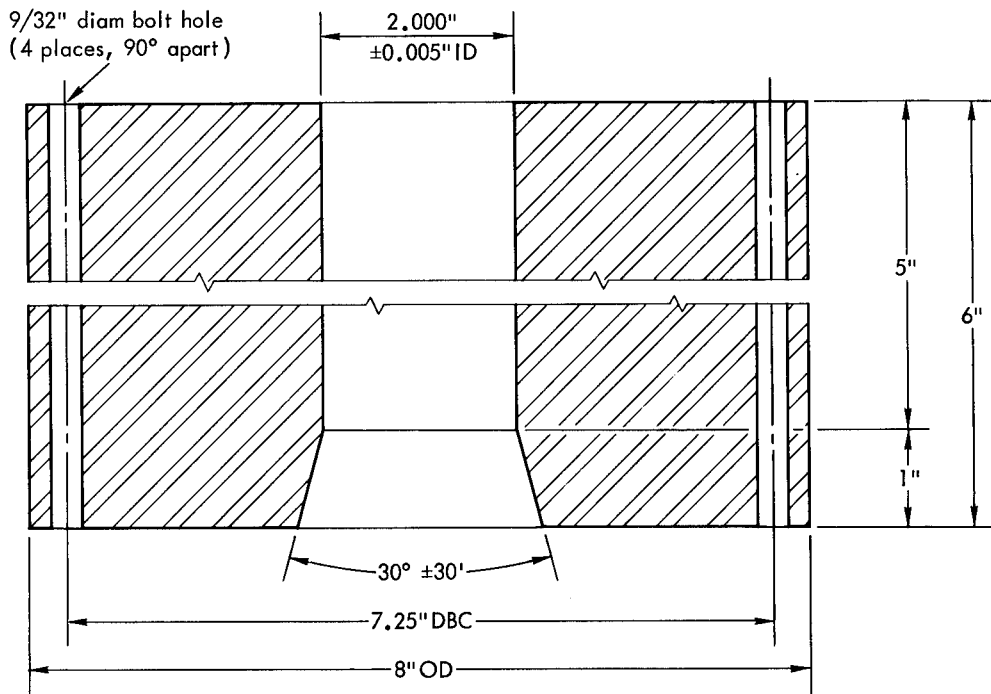


Figure E-1. DOL Type I configuration mounting flange for 2-inch-diameter, 30° conical window scaling factor validation tests.

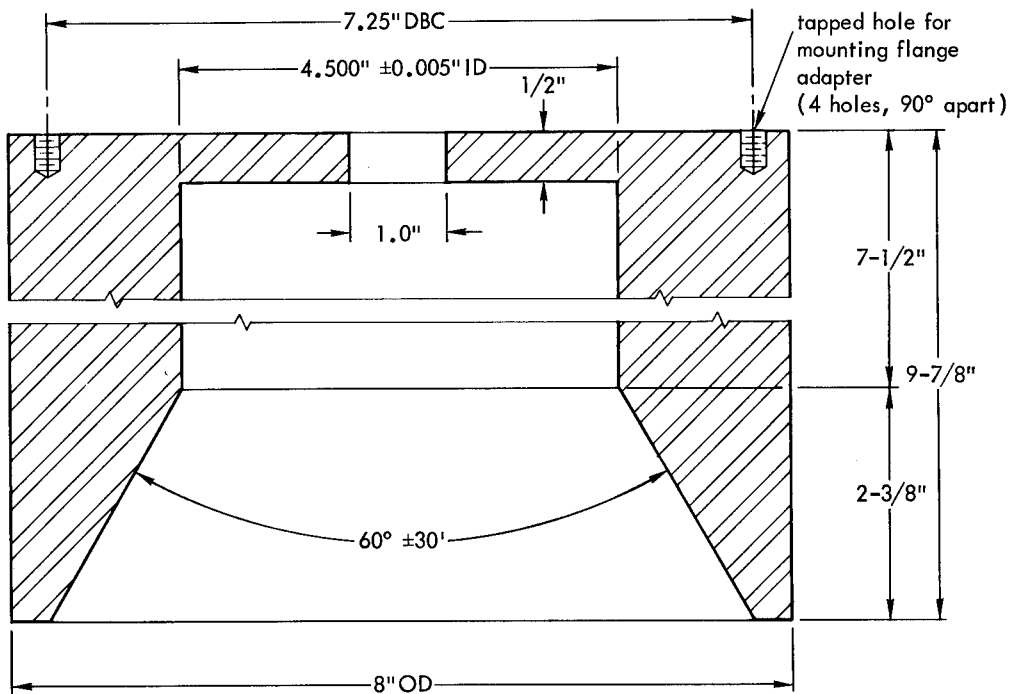


Figure E-2. DOL Type I configuration mounting flange for 4.5-inch-diameter, 60° conical window scaling factor validation tests.

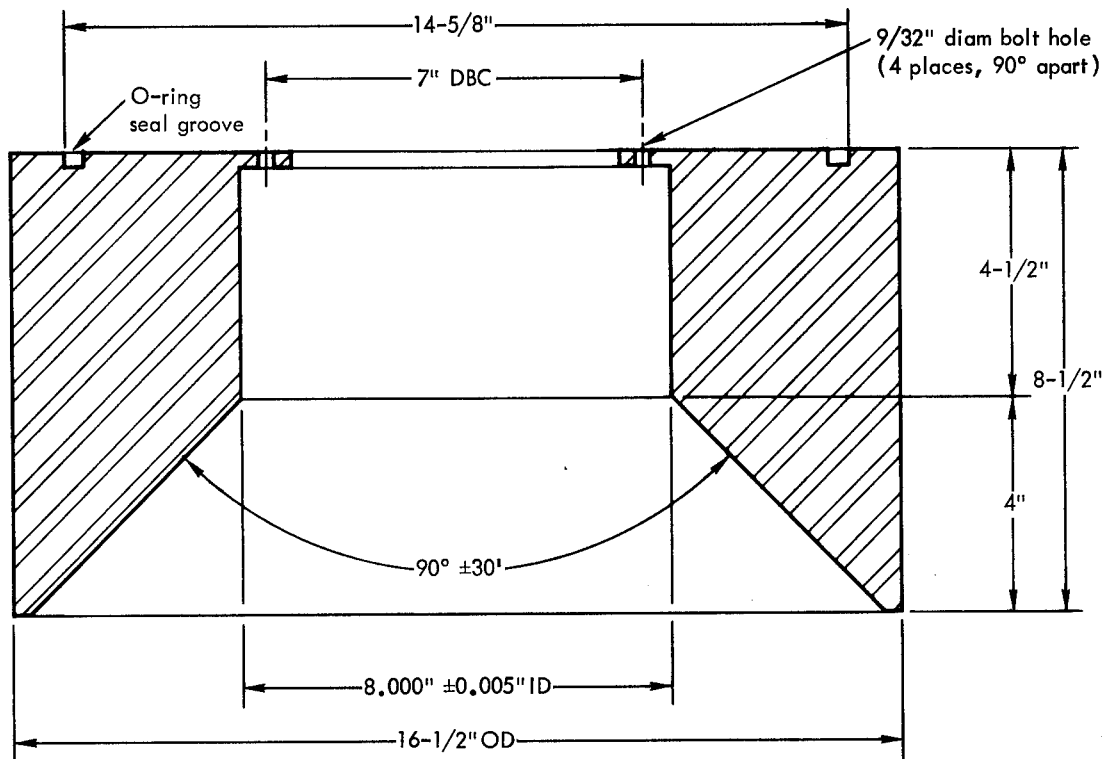


Figure E-3. DOL Type I configuration mounting flange for 8-inch-diameter, 90° conical window scaling factor validation tests.

Appendix F

EVALUATION OF OTHER WINDOW MOUNTING FLANGE CONFIGURATIONS

Since the configuration of the transition zone between the conical and the cylindrical cavities in the mounting flange may have considerable influence on the critical pressure of conical windows, several exploratory tests were conducted to determine whether a departure from the DOL Type I flange cavity configuration would influence greatly the critical pressure of conical windows under short-term hydrostatic loading. Although many flange cavity configurations are feasible for conical windows, only one in addition to the DOL Type I was utilized for exploratory investigation.

The second configuration, called DOL Type II, differed from Type I in only one vital respect. Type I was characterized by a long cylindrical cavity adjoining the conical cavity, with the same diameter as the minor diameter of the conical cavity, to provide the displaced portion of the window with radial support. In the DOL Type II configuration the cavity receiving the displaced portion was flared, with its diameter increasing beyond the juncture of the two cavities (Figure F-1). Thus, the window displaced portion was not provided with any radial support, and tended to separate from the window body retained in the flange conical cavity.

The exploratory tests conducted with 1-inch-diameter, 30° windows in a flange of the DOL Type II configuration showed that the window critical pressures were considerably lower than those obtained from testing the same windows in DOL Type I flanges. A comparison of the critical pressures of the 1-inch-diameter, 30° windows with a t/D of 1.0 in both types of flanges is as follows: DOL Type I - 27,600 psi; DOL Type II - 22,169 psi. Complete data on windows tested in DOL Type II configuration flanges are presented in Tables G-11 and G-37, Appendix G.

Since the flange configuration has such a pronounced effect on the critical pressure of the window, it is mandatory that whenever a designer wishes to apply critical pressure data from this report to a full-size window in deep submergence structure or pressure vessel, he must provide it with a DOL Type I flange. In order to achieve maximum critical pressure, the length of the cylindrical cavity in a full-size window flange must be equal to or greater than the maximum displacement that the particular window would experience prior to failure. The magnitude of the window displacements for 1-inch-diameter windows (Tables G-1 through G-10 and G-12 through G-33, Appendix G) would have to be scaled to the diameter of the window used in an actual application. The method for approximate scaling of displacements is presented in Appendix E.

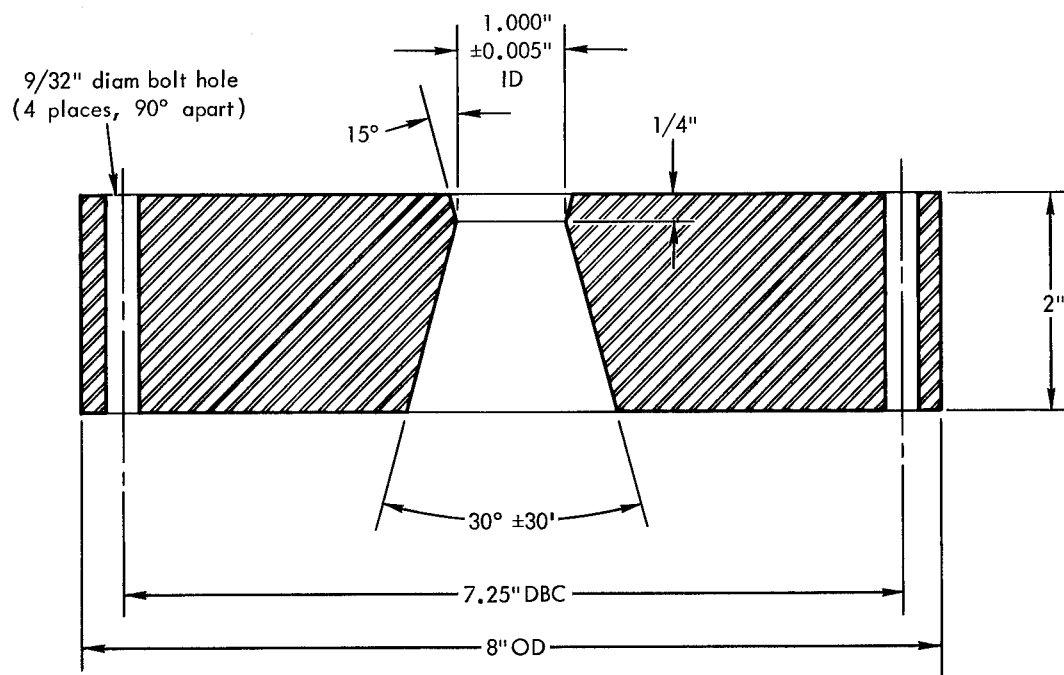


Figure F-1. DOL Type II configuration mounting flange for 1-inch-diameter, 30° conical window exploratory tests.

Appendix G

DATA FROM THE TESTING OF CONICAL ACRYLIC WINDOWS

(Tables G-1 Through G-40)

Table G-1. Test Data on 1-Inch-Diameter, 30° Windows With t/D Ratio of 0.125, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 1 | 2 | 3 | 4 | 5 | | | |
| Thickness, t (in.) | 0.129 | 0.137 | 0.135 | 0.140 | 0.153 | 0.153 | 0.138 | 0.129 |
| Temperature (°F) | 65 | 69 | 68 | 68 | 66 | 69 | 67 | 66 |
| Pressurization Rate (psi/min) | 750 | 555 | 500 | 600 | 800 | 800 | 642 | 500 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| — | ← (All failed at pressures below 1,000 psi) → | | | | | | | |
| Pressure at Failure (psi) | 800 | 850 | 850 | 750 | 880 | 850 | 826 | 750 |

Table G-2. Test Data on 1-Inch-Diameter, 30° Windows With t/D Ratio of 0.25 in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 6 | 7 | 8 | 9 | 10 | | | |
| Thickness, t (in.) | 0.250 | 0.253 | 0.250 | 0.250 | 0.251 | 0.253 | 0.251 | 0.250 |
| Temperature (°F) | 65 | 61 | 63 | 66 | 67 | 67 | 65 | 61 |
| Pressurization Rate (psi/min) | 800 | 680 | 700 | 740 | 680 | 800 | 720 | 680 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.009 | 0.011 | 0.009 | 0.011 | 0.012 | 0.009 | 0.010 | 0.012 |
| 2,000 | 0.020 | 0.025 | 0.025 | 0.030 | 0.030 | 0.020 | 0.026 | 0.030 |
| 3,000 | 0.042 | 0.050 | 0.050 | 0.054 | 0.053 | 0.042 | 0.050 | 0.054 |
| Pressure at Failure (psi) | 4,200 | 3,900 | 3,850 | 3,900 | 3,750 | 4,200 | 3,900 | 3,750 |

Table G-3. Test Data on 1-Inch-Diameter, 30° Windows With t/D Ratio of 0.375, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 11 | 12 | 13 | 14 | 15 | | | |
| Thickness, t (in.) | 0.344 | 0.348 | 0.340 | 0.338 | 0.340 | 0.348 | 0.342 | 0.338 |
| Temperature (°F) | 62 | 68.5 | 64 | 66 | 64.5 | 68.5 | 65 | 62 |
| Pressurization Rate (psi/min) | 560 | 570 | 630 | 690 | 650 | 690 | 615 | 560 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.011 | 0.021 | 0.020 | 0.012 | 0.013 | 0.021 | 0.015 | 0.011 |
| 2,000 | 0.025 | 0.027 | 0.034 | 0.026 | 0.029 | 0.034 | 0.030 | 0.025 |
| 3,000 | 0.041 | 0.047 | 0.044 | 0.042 | 0.045 | 0.047 | 0.044 | 0.041 |
| 4,000 | 0.062 | 0.065 | 0.068 | 0.062 | 0.069 | 0.069 | 0.065 | 0.062 |
| 5,000 | 0.124 | 0.135 | 0.100 | 0.100 | 0.130 | 0.135 | 0.118 | 0.100 |
| Pressure at Failure (psi) | 5,200 | 5,250 | 5,600 | 5,100 | 5,300 | 5,600 | 5,300 | 5,100 |

Table G-4. Test Data on 1-Inch-Diameter, 30° Windows With t/D Ratio of 0.5, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 16 | 17 | 18 | 19 | 20 | | | |
| Thickness, t (in.) | 0.510 | 0.490 | 0.480 | 0.488 | 0.488 | 0.510 | 0.490 | 0.480 |
| Temperature (°F) | 68.5 | 69.9 | 70.0 | 66.0 | 64.0 | 70 | 68 | 64 |
| Pressurization Rate (psi/min) | 610 | 620 | 675 | 780 | 905 | 975 | 720 | 610 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.005 | 0.005 | 0.006 | 0.005 | 0.005 | 0.006 | 0.005 | 0.005 |
| 2,000 | 0.015 | 0.011 | 0.014 | 0.010 | 0.010 | 0.015 | 0.012 | 0.010 |
| 3,000 | 0.028 | 0.020 | 0.019 | 0.015 | 0.015 | 0.028 | 0.020 | 0.015 |
| 4,000 | 0.040 | 0.031 | 0.034 | 0.020 | 0.020 | 0.040 | 0.031 | 0.020 |
| 5,000 | 0.053 | 0.044 | 0.055 | 0.034 | 0.029 | 0.055 | 0.042 | 0.029 |
| 6,000 | 0.072 | 0.060 | 0.073 | 0.058 | 0.045 | 0.073 | 0.060 | 0.045 |
| 7,000 | 0.092 | 0.079 | 0.095 | 0.130 | 0.070 | 0.130 | 0.093 | 0.070 |
| 8,000 | 0.116 | 0.110 | 0.135 | | 0.120 | 0.135 | 0.120 | 0.110 |
| Pressure at Failure (psi) | 9,200 | 8,800 | 8,700 | 7,700 | 8,600 | 9,200 | 8,600 | 8,300 |

Table G-5. Test Data on 1-Inch-Diameter, 30° Windows With t/D Ratio of 0.5, in DOL Type I Flange: Sample Group Size Validation Tests

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 21 | 22 | 23 | 24 | 25 | | | |
| Thickness, t (in.) | 0.500 | 0.490 | 0.512 | 0.497 | 0.515 | 0.515 | 0.503 | 0.490 |
| Temperature (°F) | 66 | 70 | 73 | 72 | 72 | 73 | 70 | 66 |
| Pressurization Rate (psi/min) | 980 | 740 | 1,000 | 940 | 332 | 1,000 | 800 | 332 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.010 | 0.003 | 0.010 | 0.005 | 0.004 | 0.010 | 0.006 | 0.003 |
| 2,000 | 0.020 | 0.009 | 0.015 | 0.010 | 0.008 | 0.020 | 0.012 | 0.009 |
| 3,000 | 0.030 | 0.020 | 0.027 | 0.026 | 0.012 | 0.030 | 0.023 | 0.012 |
| 4,000 | 0.042 | 0.032 | 0.040 | 0.035 | 0.026 | 0.042 | 0.035 | 0.026 |
| 5,000 | 0.055 | 0.048 | 0.050 | 0.047 | 0.048 | 0.055 | 0.050 | 0.047 |
| 6,000 | 0.075 | 0.072 | 0.071 | 0.069 | 0.080 | 0.080 | 0.073 | 0.069 |
| 7,000 | 0.110 | 0.150 | 0.105 | 0.130 | 0.150 | 0.150 | 0.129 | 0.105 |
| 8,000 | | | | | 0.310 | | | |
| Pressure at Failure (psi) | 8,300 | 7,400 | 8,000 | 9,400 | 8,300 | 9,400 | 8,270 | 7,400 |

Table G-6. Test Data on 1-Inch Diameter, 30° Windows With t/D Ratio of 0.5, in DOL Type I Flange: Low-Temperature Tests

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|--------|--------|--------|-------|---------------|---------------|---------------|
| | 26 | 27 | 28 | 29 | 30 | | | |
| Thickness, t (in.) | 0.512 | 0.494 | 0.498 | 0.489 | 0.514 | 0.514 | 0.501 | 0.489 |
| Temperature (°F) | 38 | 36 | 35 | 40 | 40 | 40 | 38 | 35 |
| Pressurization Rate (psi/min) | 625 | 500 | 600 | 713 | 653 | 713 | 619 | 500 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.006 | 0.005 | 0.006 | 0.010 | 0.005 | 0.010 | 0.006 | 0.005 |
| 2,000 | 0.009 | 0.015 | 0.016 | 0.015 | 0.008 | 0.016 | 0.013 | 0.008 |
| 3,000 | 0.014 | 0.019 | 0.025 | 0.020 | 0.014 | 0.025 | 0.018 | 0.014 |
| 4,000 | 0.022 | 0.031 | 0.039 | 0.030 | 0.030 | 0.039 | 0.030 | 0.022 |
| 5,000 | 0.041 | 0.039 | 0.050 | 0.040 | 0.035 | 0.050 | 0.041 | 0.035 |
| 6,000 | 0.045 | 0.048 | 0.057 | 0.050 | 0.054 | 0.057 | 0.051 | 0.045 |
| 7,000 | 0.060 | 0.060 | 0.075 | 0.070 | 0.075 | 0.075 | 0.068 | 0.060 |
| 8,000 | 0.081 | 0.083 | 0.090 | 0.090 | 0.080 | 0.090 | 0.085 | 0.080 |
| 9,000 | 0.117 | 0.108 | 0.112 | 0.125 | 0.095 | 0.125 | 0.112 | 0.095 |
| 10,000 | 0.250 | 0.110 | 0.148 | 0.250 | 0.130 | 0.250 | 0.178 | 0.110 |
| 11,000 | | | 0.200 | | | | | |
| 12,000 | | | 0.350 | | | | | |
| Pressure at Failure (psi) | 10,000 | 10,600 | 12,200 | 10,200 | 9,800 | 12,200 | 10,550 | 9,800 |

Table G-7. Test Data on 1-Inch-Diameter, 30° Windows With t/D Ratio of 0.625, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|--------|--------|--------|--------|---------------|---------------|---------------|
| | 31 | 32 | 33 | 34 | 35 | | | |
| Thickness, t (in.) | 0.624 | 0.632 | 0.627 | 0.630 | 0.625 | 0.632 | 0.628 | 0.624 |
| Temperature (°F) | 67 | 67 | 67 | 66 | 62 | 67 | 65 | 62 |
| Pressurization Rate (psi/min) | 650 | 665 | 700 | 590 | 630 | 705 | 650 | 590 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.015 | 0.008 | 0.012 | 0.011 | 0.018 | 0.018 | 0.013 | 0.008 |
| 2,000 | 0.024 | 0.012 | 0.021 | 0.022 | 0.026 | 0.026 | 0.021 | 0.012 |
| 3,000 | 0.032 | 0.020 | 0.030 | 0.031 | 0.036 | 0.036 | 0.030 | 0.020 |
| 4,000 | 0.043 | 0.028 | 0.039 | 0.040 | 0.047 | 0.047 | 0.039 | 0.028 |
| 5,000 | 0.052 | 0.040 | 0.049 | 0.049 | 0.054 | 0.054 | 0.049 | 0.040 |
| 6,000 | 0.063 | 0.046 | 0.058 | 0.060 | 0.065 | 0.065 | 0.058 | 0.046 |
| 7,000 | 0.077 | 0.058 | 0.069 | 0.072 | 0.076 | 0.077 | 0.070 | 0.058 |
| 8,000 | 0.092 | 0.070 | 0.082 | 0.087 | 0.090 | 0.092 | 0.084 | 0.070 |
| 9,000 | 0.110 | 0.088 | 0.098 | 0.104 | 0.104 | 0.104 | 0.098 | 0.088 |
| 10,000 | 0.140 | 0.106 | 0.118 | 0.130 | 0.123 | 0.140 | 0.123 | 0.106 |
| 11,000 | 0.175 | 0.121 | 0.145 | 0.162 | 0.150 | 0.162 | 0.151 | 0.121 |
| 12,000 | 0.235 | 0.165 | 0.183 | 0.205 | 0.189 | 0.235 | 0.195 | 0.165 |
| 13,000 | 0.355 | 0.221 | 0.235 | 0.280 | 0.250 | 0.355 | 0.269 | 0.221 |
| 14,000 | | 0.340 | 0.340 | 0.370 | 0.380 | 0.380 | 0.357 | 0.340 |
| Pressure at Failure (psi) | 13,800 | 14,800 | 14,900 | 15,300 | 14,900 | 15,300 | 14,700 | 13,800 |

Table G-8. Test Data on 1-Inch-Diameter, 30° Windows with t/D ratio of 0.75, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|--------|--------|--------|--------|---------------|---------------|---------------|
| | 36 | 37 | 38 | 39 | 40 | | | |
| Thickness, t (in.) | 0.727 | 0.726 | 0.721 | 0.740 | 0.730 | 0.740 | 0.728 | 0.726 |
| Temperature (°F) | 70 | 68 | 74 | 65 | 68 | 74 | 69 | 65 |
| Pressurization Rate (psi/min) | 590 | 635 | 770 | 740 | 630 | 770 | 670 | 630 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.003 | 0.005 | 0.007 | 0.015 | 0.011 | 0.003 | 0.008 | 0.015 |
| 2,000 | 0.008 | 0.011 | 0.015 | 0.025 | 0.021 | 0.008 | 0.016 | 0.025 |
| 3,000 | 0.014 | 0.016 | 0.018 | 0.033 | 0.030 | 0.014 | 0.022 | 0.033 |
| 4,000 | 0.022 | 0.025 | 0.022 | 0.041 | 0.040 | 0.022 | 0.030 | 0.041 |
| 5,000 | 0.032 | 0.033 | 0.028 | 0.050 | 0.049 | 0.028 | 0.039 | 0.050 |
| 6,000 | 0.041 | 0.043 | 0.037 | 0.057 | 0.060 | 0.037 | 0.048 | 0.060 |
| 7,000 | 0.053 | 0.055 | 0.046 | 0.066 | 0.071 | 0.053 | 0.058 | 0.071 |
| 8,000 | 0.067 | 0.068 | 0.059 | 0.078 | 0.085 | 0.067 | 0.072 | 0.078 |
| 9,000 | 0.084 | 0.082 | 0.075 | 0.095 | 0.100 | 0.075 | 0.087 | 0.100 |
| 10,000 | 0.104 | 0.099 | 0.095 | 0.115 | 0.121 | 0.099 | 0.107 | 0.121 |
| 11,000 | 0.130 | 0.121 | 0.118 | 0.132 | 0.150 | 0.118 | 0.130 | 0.150 |
| 12,000 | 0.160 | 0.147 | 0.160 | 0.153 | 0.190 | 0.147 | 0.162 | 0.190 |
| 13,000 | 0.197 | 0.179 | 0.230 | 0.179 | 0.245 | 0.179 | 0.206 | 0.245 |
| 14,000 | 0.251 | 0.210 | 0.330 | 0.209 | 0.328 | 0.210 | 0.265 | 0.330 |
| 15,000 | 0.335 | 0.257 | 0.440 | 0.250 | 0.415 | 0.250 | 0.339 | 0.440 |
| Pressure at Failure (psi) | 16,100 | 17,650 | 16,000 | 17,750 | 16,000 | 17,750 | 16,680 | 16,000 |

Table G-9. Test Data on 1-Inch-Diameter, 30° Windows With
t/D Ratio of 0.875, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 41 | 42 | 43 | 44 | 45 | | | |
| Thickness, t (in.) | 0.889 | 0.878 | 0.879 | 0.880 | 0.877 | 0.889 | 0.860 | 0.877 |
| Temperature (°F) | 70 | 70 | 64 | 68 | 64 | 70 | 66 | 64 |
| Pressurization Rate (psi/min) | 935 | 725 | 642 | 712 | 696 | 935 | 742 | 642 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.003 | 0.000 | 0.004 | 0.000 | 0.000 | 0.004 | 0.002 | 0.000 |
| 2,000 | 0.004 | 0.010 | 0.007 | 0.005 | 0.006 | 0.010 | 0.005 | 0.004 |
| 3,000 | 0.008 | 0.017 | 0.010 | 0.010 | 0.014 | 0.017 | 0.012 | 0.008 |
| 4,000 | 0.014 | 0.019 | 0.014 | 0.015 | 0.021 | 0.021 | 0.017 | 0.014 |
| 5,000 | 0.019 | 0.024 | 0.022 | 0.020 | 0.032 | 0.032 | 0.023 | 0.019 |
| 6,000 | 0.025 | 0.030 | 0.030 | 0.029 | 0.042 | 0.042 | 0.032 | 0.025 |
| 7,000 | 0.033 | 0.048 | 0.039 | 0.031 | 0.046 | 0.048 | 0.039 | 0.031 |
| 8,000 | 0.042 | 0.053 | 0.049 | 0.042 | 0.055 | 0.055 | 0.048 | 0.042 |
| 9,000 | 0.062 | 0.059 | 0.059 | 0.055 | 0.067 | 0.067 | 0.060 | 0.059 |
| 10,000 | 0.065 | 0.068 | 0.072 | 0.068 | 0.076 | 0.076 | 0.070 | 0.065 |
| 11,000 | 0.077 | 0.083 | 0.086 | 0.078 | 0.096 | 0.096 | 0.084 | 0.077 |
| 12,000 | 0.094 | 0.105 | 0.102 | 0.098 | 0.109 | 0.109 | 0.102 | 0.094 |
| 13,000 | 0.118 | 0.125 | 0.120 | 0.120 | 0.124 | 0.124 | 0.121 | 0.118 |
| 14,000 | 0.153 | 0.160 | 0.142 | 0.152 | 0.142 | 0.160 | 0.143 | 0.142 |
| 15,000 | 0.203 | 0.197 | 0.165 | 0.190 | 0.164 | 0.203 | 0.183 | 0.164 |
| 16,000 | 0.253 | 0.245 | 0.194 | 0.231 | 0.198 | 0.253 | 0.225 | 0.194 |
| 17,000 | 0.297 | 0.288 | 0.224 | 0.280 | 0.242 | 0.297 | 0.267 | 0.224 |
| 18,000 | 0.337 | 0.328 | 0.262 | 0.320 | 0.302 | 0.337 | 0.310 | 0.262 |
| 19,000 | 0.398 | 0.376 | 0.300 | 0.372 | 0.347 | 0.399 | 0.359 | 0.300 |
| 20,000 | 0.550 | 0.455 | 0.328 | 0.460 | 0.390 | 0.550 | 0.437 | 0.328 |
| 21,000 | | 0.940 | 0.358 | 0.840 | 0.460 | 0.940 | 0.518 | 0.358 |
| Pressure at Failure (psi) | 20,300 | 21,800 | 23,300 | 21,000 | 22,500 | 23,300 | 21,800 | 20,300 |

Table G-10. Test Data on 1-Inch-Diameter, 30° Windows With
t/D Ratio of 1.0, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 46 | 47 | 48 | 49 | 50 | | | |
| Thickness, t (in.) | 0.950 | 0.978 | 0.977 | 0.980 | 0.969 | 0.980 | 0.970 | 0.950 |
| Temperature (° F) | 61 | 65 | 72 | 72 | 73 | 73 | 69 | 61 |
| Pressurization Rate (psi/min) | 500 | 610 | 715 | 600 | 640 | 715 | 613 | 500 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.005 | 0.006 | 0.004 | 0.005 | 0.007 | 0.007 | 0.005 | 0.004 |
| 2,000 | 0.008 | 0.007 | 0.008 | 0.009 | 0.010 | 0.010 | 0.008 | 0.007 |
| 3,000 | 0.016 | 0.009 | 0.011 | 0.011 | 0.013 | 0.016 | 0.012 | 0.011 |
| 4,000 | 0.025 | 0.015 | 0.014 | 0.014 | 0.017 | 0.025 | 0.017 | 0.014 |
| 5,000 | 0.034 | 0.023 | 0.024 | 0.019 | 0.025 | 0.034 | 0.025 | 0.019 |
| 6,000 | 0.041 | 0.032 | 0.026 | 0.025 | 0.030 | 0.041 | 0.031 | 0.025 |
| 7,000 | 0.048 | 0.043 | 0.035 | 0.032 | 0.040 | 0.048 | 0.040 | 0.032 |
| 8,000 | 0.058 | 0.045 | 0.047 | 0.038 | 0.042 | 0.058 | 0.046 | 0.038 |
| 9,000 | 0.069 | 0.056 | 0.061 | 0.047 | 0.054 | 0.069 | 0.057 | 0.047 |
| 10,000 | 0.083 | 0.066 | 0.071 | 0.057 | 0.062 | 0.083 | 0.068 | 0.057 |
| 11,000 | 0.097 | 0.079 | 0.088 | 0.066 | 0.080 | 0.097 | 0.082 | 0.066 |
| 12,000 | 0.107 | 0.100 | 0.105 | 0.077 | 0.096 | 0.107 | 0.097 | 0.090 |
| 13,000 | 0.117 | 0.116 | 0.116 | 0.090 | 0.115 | 0.117 | 0.110 | 0.096 |
| 14,000 | 0.128 | 0.133 | 0.137 | 0.104 | 0.125 | 0.137 | 0.125 | 0.104 |
| 15,000 | 0.138 | 0.159 | 0.151 | 0.117 | 0.140 | 0.159 | 0.141 | 0.117 |
| 16,000 | 0.154 | 0.193 | 0.174 | 0.134 | 0.180 | 0.193 | 0.167 | 0.134 |
| 17,000 | 0.169 | 0.218 | 0.195 | 0.150 | 0.198 | 0.218 | 0.186 | 0.150 |
| 18,000 | 0.187 | 0.253 | 0.211 | 0.176 | 0.238 | 0.253 | 0.213 | 0.176 |
| 19,000 | 0.207 | 0.290 | 0.236 | 0.203 | 0.247 | 0.290 | 0.236 | 0.203 |
| 20,000 | 0.231 | 0.307 | 0.257 | 0.232 | 0.300 | 0.307 | 0.265 | 0.232 |
| 21,000 | 0.263 | 0.325 | 0.293 | 0.263 | 0.310 | 0.325 | 0.291 | 0.263 |
| 22,000 | 0.302 | 0.340 | 0.307 | 0.300 | 0.331 | 0.340 | 0.316 | 0.300 |
| 23,000 | 0.360 | 0.363 | 0.364 | 0.321 | 0.358 | 0.364 | 0.353 | 0.321 |
| 24,000 | 0.463 | 0.398 | 0.490 | 0.345 | 0.400 | 0.490 | 0.419 | 0.345 |
| 25,000 | 0.515 | 0.466 | 0.520 | 0.480 | 0.471 | 0.520 | 0.490 | 0.466 |
| 26,000 | 0.548 | | 0.570 | 0.550 | 0.562 | 0.570 | 0.557 | 0.548 |
| 27,000 | 0.640 | | 0.670 | 0.650 | 0.660 | 0.670 | 0.655 | 0.640 |
| Pressure at Failure (psi) | 29,100 | 26,100 | 27,600 | 28,200 | 27,000 | 29,100 | 27,600 | 26,100 |

Table G-11. Test Data on 1-Inch-Diameter, 30° Windows With t/D Ratio of 1.00, in DOL Type II Flange: Exploratory Tests

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|--------|--------|--------|-------|---------------|---------------|---------------|
| | 51 | 52 | 53 | 54 | 55 | | | |
| Thickness, t (in.) | 0.969 | 0.960 | 0.964 | 0.962 | 0.969 | 0.969 | 0.964 | 0.960 |
| Temperature (°F) | 64 | 65 | 65 | 65 | | 65 | 65 | 64 |
| Pressurization Rate (psi/min) | 791 | 741 | 656 | 783 | | 791 | 743 | 656 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.001 | 0.002 | 0.001 | 0.002 | | 0.002 | 0.002 | 0.001 |
| 2,000 | 0.009 | 0.011 | 0.009 | 0.010 | | 0.001 | 0.008 | 0.009 |
| 3,000 | 0.016 | 0.016 | 0.017 | 0.016 | | 0.017 | 0.016 | 0.016 |
| 4,000 | 0.019 | 0.022 | 0.024 | 0.023 | | 0.024 | 0.022 | 0.019 |
| 5,000 | 0.027 | 0.030 | 0.030 | 0.030 | | 0.030 | 0.029 | 0.027 |
| 6,000 | 0.040 | 0.036 | 0.037 | 0.036 | | 0.040 | 0.037 | 0.036 |
| 7,000 | 0.049 | 0.044 | 0.044 | 0.042 | | 0.049 | 0.045 | 0.042 |
| 8,000 | 0.057 | 0.050 | 0.053 | 0.051 | | 0.057 | 0.053 | 0.050 |
| 9,000 | 0.068 | 0.062 | 0.062 | 0.060 | | 0.068 | 0.063 | 0.060 |
| 10,000 | 0.079 | 0.069 | 0.070 | 0.069 | | 0.079 | 0.072 | 0.069 |
| 11,000 | 0.093 | 0.078 | 0.082 | 0.080 | | 0.093 | 0.083 | 0.078 |
| 12,000 | 0.108 | 0.089 | 0.095 | 0.091 | | 0.108 | 0.096 | 0.089 |
| 13,000 | 0.125 | 0.099 | 0.107 | 0.103 | | 0.125 | 0.109 | 0.099 |
| 14,000 | 0.144 | 0.110 | 0.125 | 0.112 | | 0.144 | 0.123 | 0.110 |
| 15,000 | 0.165 | 0.122 | 0.141 | 0.130 | | 0.165 | 0.140 | 0.122 |
| 16,000 | 0.194 | 0.136 | 0.158 | 0.146 | | 0.194 | 0.159 | 0.136 |
| 17,000 | 0.223 | 0.152 | 0.181 | 0.162 | | 0.223 | 0.180 | 0.162 |
| 18,000 | 0.280 | 0.172 | 0.204 | 0.180 | | 0.280 | 0.209 | 0.172 |
| 19,000 | | 0.195 | 0.231 | 0.199 | | 0.195 | 0.208 | 0.195 |
| 20,000 | | 0.217 | 0.273 | 0.219 | | 0.217 | 0.236 | 0.217 |
| 21,000 | | 0.250 | 0.325 | 0.245 | | 0.325 | 0.273 | 0.245 |
| 22,000 | | 0.285 | | 0.277 | | 0.285 | 0.281 | 0.277 |
| 23,000 | | 0.415 | | 0.351 | | 0.415 | 0.383 | 0.351 |
| Pressure at Failure (psi) | 20,575 | 23,000 | 21,300 | 23,500 | | 23,500 | 22,169 | 20,575 |

Table G-12. Test Data on 1-Inch-Diameter, 60° Windows With
t/D Ratio of 0.125, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|-------|-------|-------|--------|------------------|------------------|------------------|
| | 56 | 57 | 58 | 50 | 60 | | | |
| Thickness, t (in.) | 0.138 | 0.136 | 0.127 | 0.141 | 0.132 | 0.141 | 0.135 | 0.127 |
| Temperature (°F) | 68 | 69 | 69.5 | 67.5 | 70 | 70 | 69 | 68 |
| Pressurization Rate (psi/min) | 581 | 671 | 750 | 674 | 635 | 750 | 662 | 581 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | (Failed) | 0.047 | 0.038 | 0.037 | 0.0752 | 0.0752 | 0.049 | 0.037 |
| Pressure at Failure (psi) | 1,000 | 1,175 | 1,350 | 1,200 | 1,150 | 1,350 | 1,175 | 1,000 |

Table G-13. Test Data on 1-Inch-Diameter, 60° Windows With
t/D Ratio of 0.25, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|-------|-------|-------|------------------|------------------|------------------|
| | 61 | 62 | 63 | 64 | 65 | | | |
| Thickness, t (in.) | 0.246 | 0.247 | 0.245 | 0.247 | 0.246 | 0.247 | 0.246 | 0.245 |
| Temperature (°F) | 71 | 68 | 70 | 65 | 68 | 71 | 68 | 65 |
| Pressurization Rate (psi/min) | 651 | 645 | 638 | 630 | 640 | 651 | 641 | 630 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.004 | 0.0035 | 0.005 | 0.004 | 0.004 | 0.005 | 0.004 | 0.0035 |
| 2,000 | 0.015 | 0.008 | 0.008 | 0.007 | 0.010 | 0.015 | 0.010 | 0.007 |
| 3,000 | 0.028 | 0.017 | 0.012 | 0.015 | 0.015 | 0.028 | 0.017 | 0.012 |
| 4,000 | 0.044 | 0.030 | 0.027 | 0.028 | 0.020 | 0.044 | 0.030 | 0.020 |
| 5,000 | 0.105 | 0.068 | 0.053 | 0.057 | 0.040 | 0.105 | 0.064 | 0.040 |
| Pressure at Failure (psi) | 5,100 | 5,325 | 5,450 | 5,500 | 5,270 | 5,500 | 5,280 | 5,100 |

Table G-14. Test Data on 1-Inch-Diameter, 60° Windows With t/D Ratio of 0.375, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 66 | 67 | 68 | 69 | 70 | | | |
| Thickness, t (in.) | 0.356 | 0.327 | 0.361 | 0.366 | 0.355 | 0.366 | 0.352 | 0.327 |
| Temperature (°F) | 67 | 68 | 70 | 72 | 64 | 72 | 68 | 64 |
| Pressurization Rate (psi/min) | 664 | 709 | 665 | 780 | 633 | 780 | 690 | 633 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.004 | 0.003 | 0.004 | 0.003 | 0.004 | 0.004 | 0.0035 | 0.003 |
| 2,000 | 0.005 | 0.005 | 0.007 | 0.004 | 0.006 | 0.007 | 0.005 | 0.004 |
| 3,000 | 0.007 | 0.008 | 0.010 | 0.006 | 0.009 | 0.009 | 0.008 | 0.006 |
| 4,000 | 0.008 | 0.010 | 0.012 | 0.007 | 0.010 | 0.012 | 0.009 | 0.007 |
| 5,000 | 0.010 | 0.012 | 0.014 | 0.011 | 0.012 | 0.014 | 0.012 | 0.010 |
| 6,000 | 0.012 | 0.014 | 0.016 | 0.020 | 0.013 | 0.020 | 0.015 | 0.012 |
| 7,000 | 0.026 | 0.030 | 0.020 | 0.035 | 0.018 | 0.035 | 0.026 | 0.018 |
| 8,000 | 0.040 | 0.045 | 0.025 | 0.055 | 0.024 | 0.055 | 0.038 | 0.024 |
| Pressure at Failure (psi) | 8,800 | 7,800 | 9,150 | 8,850 | 8,500 | 9,150 | 8,620 | 7,800 |

Table G-15. Test Data on 1-Inch-Diameter, 60° Windows With
t/D Ratio of 0.5, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 71 | 72 | 73 | 74 | 75 | | | |
| Thickness, t (in.) | 0.492 | 0.493 | 0.494 | 0.492 | 0.490 | 0.494 | 0.493 | 0.490 |
| Temperature (°F) | 66 | 69 | 69 | 69 | 67 | 69 | 68 | 66 |
| Pressurization Rate (psi/min) | 669 | 675 | 672 | 684 | 985 | 985 | 736 | 669 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.004 | 0.007 | 0.005 | 0.004 | 0.001 | 0.007 | 0.005 | 0.001 |
| 2,000 | 0.005 | 0.010 | 0.007 | 0.005 | 0.0025 | 0.010 | 0.006 | 0.0025 |
| 3,000 | 0.007 | 0.012 | 0.008 | 0.008 | 0.005 | 0.012 | 0.008 | 0.005 |
| 4,000 | 0.008 | 0.013 | 0.010 | 0.010 | 0.006 | 0.013 | 0.009 | 0.006 |
| 5,000 | 0.009 | 0.015 | 0.011 | 0.015 | 0.007 | 0.015 | 0.011 | 0.007 |
| 6,000 | 0.010 | 0.016 | 0.013 | 0.020 | 0.0075 | 0.020 | 0.015 | 0.0075 |
| 7,000 | 0.012 | 0.019 | 0.015 | 0.026 | 0.022 | 0.026 | 0.019 | 0.012 |
| 8,000 | 0.014 | 0.022 | 0.017 | 0.032 | 0.028 | 0.032 | 0.023 | 0.014 |
| 9,000 | 0.016 | 0.034 | 0.023 | 0.041 | 0.036 | 0.041 | 0.030 | 0.016 |
| 10,000 | 0.022 | 0.046 | 0.033 | 0.055 | 0.046 | 0.055 | 0.040 | 0.022 |
| 11,000 | 0.038 | 0.064 | 0.044 | 0.079 | 0.048 | 0.079 | 0.055 | 0.038 |
| 12,000 | 0.073 | 0.107 | 0.068 | 0.210 | 0.059 | 0.210 | 0.103 | 0.059 |
| 13,000 | 0.260 | | 0.113 | | 0.079 | 0.260 | 0.150 | 0.079 |
| 14,000 | | | 0.610 | | 0.137 | 0.610 | 0.373 | 0.137 |
| Pressure at Failure (psi) | 13,350 | 13,000 | 14,450 | 12,600 | 14,750 | 14,750 | 13,650 | 12,600 |

Table G-16. Test Data on 1-Inch-Diameter, 60° Windows With
t/D Ratio of 0.625, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 76 | 77 | 78 | 79 | 80 | | | |
| Thickness, t (in.) | 0.626 | 0.632 | 0.627 | 0.626 | 0.623 | 0.632 | 0.627 | 0.623 |
| Temperature (°F) | 68 | 70 | 70 | 65 | 73 | 73 | 69 | 65 |
| Pressurization Rate (psi/min) | 669 | 497 | 651 | 612 | 668 | 669 | 619 | 497 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.012 | 0.010 | 0.010 | 0.006 | 0.004 | 0.012 | 0.008 | 0.004 |
| 2,000 | 0.014 | 0.012 | 0.014 | 0.008 | 0.005 | 0.014 | 0.012 | 0.005 |
| 3,000 | 0.016 | 0.014 | 0.018 | 0.010 | 0.007 | 0.018 | 0.013 | 0.007 |
| 4,000 | 0.018 | 0.016 | 0.022 | 0.012 | 0.008 | 0.022 | 0.015 | 0.008 |
| 5,000 | 0.018 | 0.025 | 0.026 | 0.014 | 0.010 | 0.026 | 0.019 | 0.010 |
| 6,000 | 0.021 | 0.030 | 0.029 | 0.015 | 0.011 | 0.030 | 0.021 | 0.011 |
| 7,000 | 0.023 | 0.032 | 0.033 | 0.017 | 0.013 | 0.033 | 0.024 | 0.013 |
| 8,000 | 0.027 | 0.037 | 0.037 | 0.019 | 0.015 | 0.037 | 0.027 | 0.015 |
| 9,000 | 0.031 | 0.043 | 0.041 | 0.024 | 0.017 | 0.043 | 0.031 | 0.017 |
| 10,000 | 0.035 | 0.047 | 0.046 | 0.038 | 0.018 | 0.047 | 0.037 | 0.018 |
| 11,000 | 0.040 | 0.055 | 0.051 | 0.040 | 0.021 | 0.055 | 0.041 | 0.021 |
| 12,000 | 0.045 | 0.060 | 0.057 | 0.042 | 0.024 | 0.060 | 0.046 | 0.024 |
| 13,000 | 0.052 | 0.067 | 0.062 | 0.050 | 0.028 | 0.067 | 0.052 | 0.028 |
| 14,000 | 0.060 | 0.073 | 0.068 | 0.053 | 0.033 | 0.073 | 0.057 | 0.033 |
| 15,000 | 0.068 | 0.083 | 0.077 | 0.058 | 0.044 | 0.083 | 0.066 | 0.044 |
| 16,000 | 0.078 | 0.094 | 0.086 | 0.066 | 0.054 | 0.094 | 0.076 | 0.054 |
| 17,000 | 0.088 | 0.104 | 0.097 | 0.077 | 0.067 | 0.104 | 0.087 | 0.067 |
| 18,000 | 0.103 | 0.120 | 0.110 | 0.088 | 0.083 | 0.120 | 0.101 | 0.083 |
| 19,000 | 0.119 | 0.147 | 0.134 | 0.109 | 0.108 | 0.147 | 0.122 | 0.108 |
| 20,000 | 0.146 | 0.177 | 0.174 | 0.133 | 0.153 | 0.177 | 0.157 | 0.146 |
| 21,000 | 0.205 | 0.220 | 0.246 | 0.173 | 0.250 | 0.250 | 0.219 | 0.173 |
| 22,000 | 0.330 | 0.280 | 0.305 | 0.247 | 0.358 | 0.358 | 0.304 | 0.247 |
| 23,000 | 0.440 | 0.355 | 0.347 | 0.347 | 0.405 | 0.440 | 0.379 | 0.347 |
| 24,000 | 0.518 | 0.410 | 0.390 | 0.391 | 0.452 | 0.518 | 0.432 | 0.390 |
| 25,000 | | 0.435 | 0.415 | 0.415 | | 0.435 | 0.422 | 0.415 |
| 26,000 | | 0.478 | 0.438 | 0.459 | | 0.478 | 0.485 | 0.458 |
| 27,000 | | | | 0.494 | | 0.484 | 0.484 | 0.484 |
| 28,000 | | | | 0.498 | | 0.498 | 0.497 | 0.489 |
| Pressure at Failure (psi) | 24,850 | 26,600 | 26,400 | 28,100 | 24,500 | 28,100 | 26,090 | 24,500 |

Table G-17. Test Data on 1-Inch-Diameter, 90° Windows With t/D Ratio of 0.125, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|--------------------------|---------------|---------------|---------------|
| | 81 | 82 | 83 | 84 | 85 | | | |
| Thickness, t (in.) | 0.147 | 0.134 | 0.140 | 0.138 | 0.110 | 0.147 | 0.134 | 0.110 |
| Temperature (°F) | 74.3 | 73.4 | 72.5 | 72.5 | 72.5 | 74.3 | 73.2 | 72.5 |
| Pressurization Rate (psi/min) | 700 | 708 | 620 | 665 | 625 | 708 | 664 | 620 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | (Failed below 1,000 psi) | | | 0.018 | (Failed below 1,000 psi) | | | |
| Pressure at Failure (psi) | 1,000 | 800 | 800 | 1,150 | 600 | 1,150 | 870 | 600 |

Table G-18. Test Data on 1-Inch-Diameter, 90° Windows With t/D Ratio of 0.25, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 86 | 87 | 88 | 89 | 90 | | | |
| Thickness, t (in.) | 0.260 | 0.258 | 0.248 | 0.255 | 0.254 | 0.260 | 0.255 | 0.248 |
| Temperature (°F) | 69.5 | 67.5 | 68.0 | 69.0 | 70.5 | 69.5 | 68.9 | 67.5 |
| Pressurization Rate (psi/min) | 679 | 658 | 638 | 675 | 650 | 679 | 660 | 638 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.005 | 0.003 | 0.003 | 0.007 | 0.002 | 0.007 | 0.004 | 0.002 |
| 2,000 | 0.014 | 0.006 | 0.006 | 0.010 | 0.005 | 0.014 | 0.008 | 0.005 |
| 3,000 | 0.022 | 0.012 | 0.008 | 0.013 | 0.010 | 0.022 | 0.013 | 0.008 |
| 4,000 | 0.031 | 0.022 | 0.012 | 0.017 | 0.024 | 0.031 | 0.021 | 0.012 |
| 5,000 | 0.073 | 0.034 | 0.022 | 0.022 | 0.050 | 0.073 | 0.040 | 0.022 |
| 6,000 | | 0.067 | 0.095 | 0.060 | | 0.095 | 0.074 | 0.060 |
| Pressure at Failure (psi) | 5,300 | 6,300 | 6,100 | 6,200 | 5,300 | 6,300 | 5,840 | 5,300 |

Figure G-19. Test Data on 1-Inch-Diameter, 90° Windows With t/D Ratio of 0.375, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|--------|--------|--------|--------|---------------|---------------|---------------|
| | 91 | 92 | 93 | 94 | 95 | | | |
| Thickness, t (in.) | 0.381 | 0.370 | 0.374 | 0.379 | 0.380 | 0.381 | 0.377 | 0.370 |
| Temperature (° F) | 75.2 | 71.6 | 76.1 | 75.2 | 73.4 | 76.1 | 74.3 | 71.6 |
| Pressurization Rate (psi/min) | 661 | 674 | 673 | 672 | 668 | 674 | 670 | 661 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.009 | 0.008 | 0.010 | 0.006 | 0.005 | 0.010 | 0.008 | 0.005 |
| 2,000 | 0.011 | 0.012 | 0.012 | 0.007 | 0.010 | 0.012 | 0.010 | 0.007 |
| 3,000 | 0.013 | 0.014 | 0.014 | 0.009 | 0.013 | 0.014 | 0.012 | 0.009 |
| 4,000 | 0.014 | 0.016 | 0.016 | 0.010 | 0.017 | 0.017 | 0.015 | 0.010 |
| 5,000 | 0.015 | 0.019 | 0.018 | 0.013 | 0.022 | 0.022 | 0.017 | 0.013 |
| 6,000 | 0.017 | 0.022 | 0.020 | 0.016 | 0.027 | 0.027 | 0.022 | 0.016 |
| 7,000 | 0.037 | 0.028 | 0.022 | 0.020 | 0.033 | 0.037 | 0.028 | 0.020 |
| 8,000 | 0.039 | 0.036 | 0.025 | 0.026 | 0.039 | 0.039 | 0.033 | 0.025 |
| 9,000 | 0.042 | 0.043 | 0.030 | 0.033 | 0.047 | 0.047 | 0.039 | 0.030 |
| 10,000 | 0.046 | 0.055 | 0.043 | 0.045 | 0.060 | 0.060 | 0.050 | 0.043 |
| 11,000 | 0.075 | 0.078 | 0.118 | 0.067 | 0.090 | 0.118 | 0.086 | 0.067 |
| Pressure at Failure (psi) | 11,850 | 12,150 | 11,250 | 11,900 | 11,500 | 12,150 | 11,730 | 11,250 |

Table G-20. Test Data on 1-Inch-Diameter, 90° Windows With
t/D Ratio of 0.5, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 96 | 97 | 98 | 99 | 100 | | | |
| Thickness, t (in.) | 0.511 | 0.516 | 0.490 | 0.480 | 0.481 | 0.516 | 0.496 | 0.480 |
| Temperature (°F) | 71.6 | 68.4 | 65.3 | 63.5 | 69.8 | 71.6 | 67.7 | 63.5 |
| Pressurization Rate (psi/min) | 657 | 664 | 662 | 667 | 675 | 675 | 665 | 657 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.004 | 0.003 | 0.002 | 0.002 | 0.002 | 0.004 | 0.003 | 0.002 |
| 2,000 | 0.008 | 0.007 | 0.004 | 0.003 | 0.004 | 0.008 | 0.005 | 0.003 |
| 3,000 | 0.012 | 0.011 | 0.007 | 0.003 | 0.005 | 0.012 | 0.008 | 0.003 |
| 4,000 | 0.015 | 0.015 | 0.008 | 0.005 | 0.007 | 0.015 | 0.010 | 0.005 |
| 5,000 | 0.018 | 0.018 | 0.010 | 0.007 | 0.009 | 0.018 | 0.012 | 0.007 |
| 6,000 | 0.021 | 0.021 | 0.011 | 0.009 | 0.012 | 0.021 | 0.015 | 0.009 |
| 7,000 | 0.024 | 0.025 | 0.013 | 0.013 | 0.017 | 0.025 | 0.018 | 0.013 |
| 8,000 | 0.027 | 0.028 | 0.015 | 0.016 | 0.020 | 0.028 | 0.021 | 0.015 |
| 9,000 | 0.031 | 0.032 | 0.017 | 0.020 | 0.026 | 0.032 | 0.025 | 0.017 |
| 10,000 | 0.035 | 0.036 | 0.019 | 0.024 | 0.031 | 0.036 | 0.029 | 0.019 |
| 11,000 | 0.039 | 0.041 | 0.023 | 0.029 | 0.037 | 0.041 | 0.034 | 0.023 |
| 12,000 | 0.045 | 0.046 | 0.028 | 0.035 | 0.044 | 0.046 | 0.040 | 0.028 |
| 13,000 | 0.051 | 0.053 | 0.035 | 0.042 | 0.058 | 0.058 | 0.048 | 0.035 |
| 14,000 | 0.058 | 0.062 | 0.046 | 0.051 | 0.077 | 0.077 | 0.059 | 0.046 |
| 15,000 | 0.069 | 0.073 | 0.065 | 0.073 | 0.122 | 0.122 | 0.080 | 0.065 |
| 16,000 | 0.086 | 0.091 | 0.127 | 0.114 | | 0.127 | 0.105 | 0.086 |
| Pressure at Failure (psi) | 17,900 | 17,850 | 16,400 | 16,400 | 15,550 | 17,900 | 16,820 | 15,550 |

Table G-21. Test Data on 1-Inch-Diameter, 90° Windows With t/D Ratio of 0.5, in DOL Type I Flange: Sample Group Size Validation Tests

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|--------|--------|--------|--------|---------------|---------------|---------------|
| | 101 | 102 | 103 | 104 | 105 | | | |
| Thickness, t (in.) | 0.496 | 0.490 | 0.512 | 0.482 | 0.515 | 0.515 | 0.499 | 0.482 |
| Temperature (°F) | 70 | 68 | 80 | 77 | 75 | 80 | 74 | 68 |
| Pressurization Rate (psi/min) | 672 | 634 | 670 | 672 | 570 | 570 | 837 | 634 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.002 | 0.003 | 0.007 | 0.011 | 0.006 | 0.011 | 0.006 | 0.002 |
| 2,000 | 0.003 | 0.005 | 0.008 | 0.015 | 0.007 | 0.015 | 0.007 | 0.003 |
| 3,000 | 0.004 | 0.006 | 0.009 | 0.018 | 0.009 | 0.018 | 0.009 | 0.004 |
| 4,000 | 0.007 | 0.007 | 0.010 | 0.024 | 0.015 | 0.024 | 0.011 | 0.007 |
| 5,000 | 0.015 | 0.009 | 0.011 | 0.028 | 0.019 | 0.028 | 0.016 | 0.009 |
| 6,000 | 0.018 | 0.010 | 0.012 | 0.031 | 0.022 | 0.031 | 0.018 | 0.010 |
| 7,000 | 0.021 | 0.011 | 0.013 | 0.036 | 0.027 | 0.036 | 0.021 | 0.011 |
| 8,000 | 0.025 | 0.014 | 0.014 | 0.039 | 0.030 | 0.039 | 0.024 | 0.014 |
| 9,000 | 0.030 | 0.016 | 0.018 | 0.046 | 0.034 | 0.046 | 0.028 | 0.016 |
| 10,000 | 0.035 | 0.020 | 0.020 | 0.053 | 0.039 | 0.053 | 0.032 | 0.020 |
| 11,000 | 0.041 | 0.026 | 0.023 | 0.062 | 0.044 | 0.062 | 0.038 | 0.023 |
| 12,000 | 0.048 | 0.033 | 0.031 | 0.076 | 0.051 | 0.076 | 0.046 | 0.031 |
| 13,000 | 0.058 | 0.043 | 0.040 | 0.110 | 0.060 | 0.110 | 0.060 | 0.040 |
| 14,000 | 0.075 | 0.067 | 0.056 | | 0.071 | 0.075 | 0.065 | 0.056 |
| 15,000 | 0.107 | 0.110 | 0.073 | | 0.090 | 0.110 | 0.090 | 0.073 |
| Pressure at Failure (psi) | 15,850 | 15,700 | 16,550 | 13,850 | 17,750 | 17,750 | 15,940 | 13,850 |

Table G-22. Test Data on 1-Inch-Diameter, 90° Windows With
t/D Ratio of 0.625, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 106 | 107 | 108 | 109 | 110 | | | |
| Thickness, t (in.) | 0.626 | 0.632 | 0.633 | 0.631 | 0.631 | 0.633 | 0.631 | 0.626 |
| Temperature (° F) | 67.1 | 65.3 | 67.1 | 62.6 | 65.3 | 67.1 | 65.5 | 62.6 |
| Pressurization Rate (psi/min) | 669 | 702 | 851 | 934 | 613 | 934 | 754 | 613 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.003 | 0.002 | | 0.003 | 0.004 | 0.004 | 0.003 | 0.002 |
| 2,000 | 0.007 | 0.004 | 0.001 | 0.005 | 0.007 | 0.007 | 0.005 | 0.001 |
| 3,000 | 0.010 | 0.005 | 0.002 | 0.006 | 0.010 | 0.010 | 0.007 | 0.002 |
| 4,000 | 0.013 | 0.006 | 0.016 | 0.007 | 0.013 | 0.016 | 0.011 | 0.006 |
| 5,000 | 0.015 | 0.007 | 0.016 | 0.008 | 0.016 | 0.016 | 0.012 | 0.007 |
| 6,000 | 0.018 | 0.008 | 0.017 | 0.009 | 0.019 | 0.019 | 0.014 | 0.008 |
| 7,000 | 0.020 | 0.009 | 0.017 | 0.011 | 0.022 | 0.022 | 0.016 | 0.009 |
| 8,000 | 0.023 | 0.010 | 0.018 | 0.012 | 0.024 | 0.024 | 0.017 | 0.010 |
| 9,000 | 0.025 | 0.013 | 0.022 | 0.013 | 0.027 | 0.027 | 0.020 | 0.013 |
| 10,000 | 0.029 | 0.025 | 0.025 | 0.014 | 0.031 | 0.031 | 0.025 | 0.014 |
| 11,000 | 0.031 | 0.026 | 0.027 | 0.015 | 0.033 | 0.033 | 0.026 | 0.015 |
| 12,000 | 0.035 | 0.026 | 0.031 | 0.017 | 0.036 | 0.036 | 0.029 | 0.017 |
| 13,000 | 0.038 | 0.027 | 0.035 | 0.018 | 0.040 | 0.040 | 0.032 | 0.018 |
| 14,000 | 0.042 | 0.027 | 0.038 | 0.019 | 0.043 | 0.043 | 0.034 | 0.019 |
| 15,000 | 0.045 | 0.028 | 0.042 | 0.021 | 0.047 | 0.047 | 0.037 | 0.021 |
| 16,000 | 0.049 | 0.047 | 0.047 | 0.022 | 0.051 | 0.051 | 0.043 | 0.022 |
| 17,000 | 0.053 | 0.049 | 0.052 | 0.024 | 0.055 | 0.055 | 0.047 | 0.024 |
| 18,000 | 0.058 | 0.050 | 0.058 | 0.025 | 0.061 | 0.061 | 0.050 | 0.025 |
| 19,000 | 0.063 | 0.051 | 0.065 | 0.026 | 0.066 | 0.066 | 0.054 | 0.026 |
| 20,000 | 0.070 | 0.072 | 0.071 | 0.028 | 0.071 | 0.072 | 0.062 | 0.028 |
| 21,000 | 0.078 | 0.074 | 0.080 | 0.030 | 0.077 | 0.080 | 0.068 | 0.030 |
| 22,000 | 0.089 | 0.076 | 0.090 | 0.058 | 0.087 | 0.090 | 0.080 | 0.058 |
| 23,000 | 0.099 | 0.097 | 0.107 | 0.061 | | 0.107 | 0.091 | 0.061 |
| 24,000 | 0.108 | 0.118 | 0.127 | 0.065 | 0.120 | 0.127 | 0.108 | 0.065 |
| 25,000 | 0.120 | 0.140 | 0.154 | 0.069 | 0.133 | 0.154 | 0.123 | 0.069 |
| 26,000 | 0.140 | 0.186 | 0.192 | 0.083 | | 0.192 | 0.150 | 0.083 |
| 27,000 | 0.176 | 0.248 | 0.287 | 0.105 | | 0.287 | 0.204 | 0.105 |
| Pressure at Failure (psi) | 28,850 | 27,400 | 27,700 | 29,900 | 27,100 | 29,900 | 28,190 | 27,100 |

Table G-23. Test Data on 1-Inch-Diameter, 120° Windows With t/D Ratio of 0.125, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 111 | 112 | 113 | 114 | 115 | | | |
| Thickness, t (in.) | 0.120 | 0.120 | 0.121 | 0.120 | 0.120 | 0.121 | 0.120 | 0.120 |
| Temperature (°F) | 63.5 | 64 | 63.5 | 63 | 63 | 64 | 63.4 | 63 |
| Pressurization Rate (psi/min) | 329 | 524 | 429 | 449 | 372 | 524 | 421 | 329 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| — | ← (All failed at pressures below 1,000 psi) → | | | | | | | |
| Pressure Failure (psi) | 850 | 750 | 750 | 750 | 850 | 850 | 790 | 750 |

Table G-24. Test Data on 1-Inch-Diameter, 120° Windows With t/D Ratio of 0.25, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 116 | 117 | 118 | 119 | 120 | | | |
| Thickness, t (in.) | 0.241 | 0.240 | 0.244 | 0.243 | 0.239 | 0.244 | 0.243 | 0.239 |
| Temperature (°F) | 63 | 64 | 61 | 61 | 61 | 64 | 62 | 61 |
| Pressurization Rate (psi/min) | 705 | 657 | 642 | 623 | 651 | 703 | 655 | 623 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.004 | 0.003 | 0.002 | 0.003 | 0.002 | 0.004 | 0.003 | 0.002 |
| 2,000 | 0.007 | 0.006 | 0.005 | 0.005 | 0.005 | 0.007 | 0.006 | 0.005 |
| 3,000 | 0.011 | 0.010 | 0.009 | 0.008 | 0.009 | 0.011 | 0.009 | 0.008 |
| 4,000 | | 0.024 | 0.014 | 0.015 | 0.016 | 0.024 | 0.017 | 0.014 |
| Pressure at Failure (psi) | 3,500 | 4,400 | 4,950 | 4,400 | 4,350 | 4,950 | 4,320 | 3,500 |

Table G-25. Test Data on 1-Inch-Diameter, 120° Windows With
t/D Ratio of 0.375, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 121 | 122 | 123 | 124 | 125 | | | |
| Thickness, t (in.) | 0.349 | 0.331 | 0.330 | 0.328 | 0.337 | 0.349 | 0.335 | 0.328 |
| Temperature (°F) | 65.5 | 65.5 | 67 | 61.4 | 62.7 | 67 | 64.4 | 61.4 |
| Pressurization Rate (psi/min) | 716 | 717 | 833 | 680 | 674 | 833 | 724 | 674 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.002 | 0.002 | 0.002 | 0.001 | 0.002 | 0.002 | 0.002 | 0.001 |
| 2,000 | 0.004 | 0.003 | 0.005 | 0.002 | 0.004 | 0.005 | 0.004 | 0.002 |
| 3,000 | 0.005 | 0.005 | 0.007 | 0.004 | 0.006 | 0.007 | 0.005 | 0.002 |
| 4,000 | 0.008 | 0.007 | 0.009 | 0.006 | 0.008 | 0.009 | 0.008 | 0.006 |
| 5,000 | 0.009 | 0.009 | 0.011 | 0.007 | 0.010 | 0.011 | 0.009 | 0.007 |
| 6,000 | 0.012 | 0.011 | 0.013 | 0.010 | 0.012 | 0.013 | 0.012 | 0.010 |
| 7,000 | 0.015 | 0.014 | 0.016 | 0.012 | 0.014 | 0.016 | 0.014 | 0.012 |
| 8,000 | 0.018 | 0.018 | 0.018 | 0.016 | 0.017 | 0.018 | 0.017 | 0.016 |
| 9,000 | 0.031 | 0.031 | 0.029 | 0.027 | 0.021 | 0.031 | 0.028 | 0.021 |
| 10,000 | 0.054 | 0.070 | 0.050 | 0.055 | 0.038 | 0.070 | 0.053 | 0.038 |
| 11,000 | | | | | 0.074 | | | |
| Pressure at Failure (psi) | 10,900 | 10,680 | 10,700 | 10,450 | 11,300 | 11,300 | 10,806 | 10,450 |

Table G-26. Test Data on 1-Inch-Diameter, 120° Windows With
t/D Ratio of 0.5, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 126 | 127 | 128 | 129 | 130 | | | |
| Thickness, t (in.) | 0.490 | 0.490 | 0.483 | 0.493 | 0.493 | 0.493 | 0.490 | 0.483 |
| Temperature (°F) | 67.5 | 68.0 | 69.0 | 67.5 | 66.5 | 69.0 | 67.7 | 66.5 |
| Pressurization Rate (psi/min) | 666 | 665 | 669 | 657 | 671 | 671 | 666 | 657 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.002 | 0.001 | 0.001 | 0.000 | 0.001 | 0.002 | 0.001 | 0.000 |
| 2,000 | 0.005 | 0.002 | 0.003 | 0.001 | 0.002 | 0.005 | 0.003 | 0.001 |
| 3,000 | 0.005 | 0.003 | 0.004 | 0.003 | 0.004 | 0.005 | 0.004 | 0.003 |
| 4,000 | 0.006 | 0.005 | 0.005 | 0.004 | 0.005 | 0.006 | 0.005 | 0.004 |
| 5,000 | 0.008 | 0.006 | 0.007 | 0.005 | 0.006 | 0.008 | 0.006 | 0.005 |
| 6,000 | 0.009 | 0.008 | 0.008 | 0.007 | 0.008 | 0.009 | 0.008 | 0.007 |
| 7,000 | 0.010 | 0.009 | 0.010 | 0.008 | 0.009 | 0.010 | 0.009 | 0.008 |
| 8,000 | 0.011 | 0.011 | 0.012 | 0.009 | 0.010 | 0.012 | 0.011 | 0.009 |
| 9,000 | 0.013 | 0.012 | 0.013 | 0.010 | 0.011 | 0.013 | 0.012 | 0.010 |
| 10,000 | 0.014 | 0.014 | 0.014 | 0.012 | 0.013 | 0.014 | 0.013 | 0.012 |
| 11,000 | 0.016 | 0.015 | 0.015 | 0.018 | 0.016 | 0.018 | 0.016 | 0.015 |
| 12,000 | 0.017 | 0.017 | 0.017 | 0.020 | 0.017 | 0.020 | 0.018 | 0.017 |
| 13,000 | 0.019 | 0.018 | 0.019 | 0.022 | 0.020 | 0.022 | 0.020 | 0.018 |
| 14,000 | 0.022 | 0.045 | 0.021 | 0.032 | 0.025 | 0.045 | 0.029 | 0.021 |
| 15,000 | 0.025 | 0.048 | 0.025 | 0.035 | 0.031 | 0.048 | 0.033 | 0.025 |
| 16,000 | 0.030 | 0.052 | 0.034 | 0.048 | 0.039 | 0.052 | 0.041 | 0.030 |
| 17,000 | 0.065 | 0.070 | 0.045 | 0.052 | 0.050 | 0.070 | 0.056 | 0.045 |
| 18,000 | 0.142 | 0.100 | 0.060 | 0.080 | 0.066 | 0.142 | 0.090 | 0.060 |
| 19,000 | | | 0.148 | 0.200 | 0.130 | 0.200 | 0.159 | 0.130 |
| Pressure at Failure (psi) | 18,400 | 18,700 | 19,300 | 19,300 | 19,300 | 19,300 | 19,000 | 18,400 |

Table G-27. Test Data on 1-Inch-Diameter, 120° Windows With
t/D Ratio of 0.625, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 131 | 132 | 133 | 134 | 135 | | | |
| Thickness, t (in.) | 0.607 | 0.602 | 0.583 | 0.600 | 0.583 | 0.607 | 0.595 | 0.583 |
| Temperature (°F) | 63.5 | 65.5 | 67.0 | 67.5 | 67.5 | 67.5 | 66.2 | 63.5 |
| Pressurization Rate (psi/min) | 732 | 643 | 661 | 603 | 646 | 732 | 657 | 603 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.002 | 0.000 | 0.003 | 0.001 | 0.001 | 0.003 | 0.001 | 0.000 |
| 2,000 | 0.004 | 0.001 | 0.005 | 0.002 | 0.003 | 0.005 | 0.003 | 0.001 |
| 3,000 | 0.005 | 0.002 | 0.007 | 0.003 | 0.004 | 0.007 | 0.004 | 0.002 |
| 4,000 | 0.007 | 0.003 | 0.009 | 0.004 | 0.005 | 0.009 | 0.006 | 0.003 |
| 5,000 | 0.008 | 0.004 | 0.010 | 0.005 | 0.006 | 0.010 | 0.007 | 0.004 |
| 6,000 | 0.009 | 0.005 | 0.011 | 0.006 | 0.007 | 0.011 | 0.008 | 0.005 |
| 7,000 | 0.010 | 0.005 | 0.012 | 0.007 | 0.009 | 0.012 | 0.009 | 0.005 |
| 8,000 | 0.011 | 0.007 | 0.013 | 0.007 | 0.010 | 0.013 | 0.010 | 0.007 |
| 9,000 | 0.012 | 0.008 | 0.015 | 0.008 | 0.011 | 0.015 | 0.011 | 0.008 |
| 10,000 | 0.014 | 0.009 | 0.015 | 0.009 | 0.019 | 0.019 | 0.013 | 0.009 |
| 11,000 | 0.015 | 0.010 | 0.017 | 0.010 | 0.020 | 0.020 | 0.014 | 0.010 |
| 12,000 | 0.016 | 0.011 | 0.018 | 0.011 | 0.021 | 0.021 | 0.015 | 0.011 |
| 13,000 | 0.018 | 0.012 | 0.020 | 0.012 | 0.023 | 0.023 | 0.017 | 0.012 |
| 14,000 | 0.040 | 0.013 | 0.021 | 0.014 | 0.024 | 0.040 | 0.022 | 0.013 |
| 15,000 | 0.041 | 0.041 | 0.022 | 0.015 | 0.025 | 0.041 | 0.029 | 0.015 |
| 16,000 | 0.042 | 0.041 | 0.024 | 0.017 | 0.027 | 0.042 | 0.030 | 0.017 |
| 17,000 | 0.044 | 0.043 | 0.025 | 0.018 | 0.043 | 0.044 | 0.035 | 0.018 |
| 18,000 | 0.045 | 0.044 | 0.027 | 0.037 | 0.045 | 0.045 | 0.040 | 0.027 |
| 19,000 | 0.047 | 0.046 | 0.029 | 0.037 | 0.047 | 0.047 | 0.041 | 0.029 |
| 20,000 | 0.049 | 0.048 | 0.031 | 0.039 | 0.049 | 0.049 | 0.043 | 0.031 |
| 21,000 | 0.075 | 0.050 | 0.051 | 0.040 | 0.067 | 0.075 | 0.057 | 0.040 |
| 22,000 | 0.079 | 0.076 | 0.054 | 0.054 | 0.070 | 0.079 | 0.067 | 0.054 |
| 23,000 | 0.080 | 0.078 | 0.057 | 0.055 | 0.094 | 0.094 | 0.073 | 0.055 |
| 24,000 | 0.084 | 0.081 | 0.073 | 0.077 | 0.098 | 0.098 | 0.083 | 0.073 |
| 25,000 | 0.109 | 0.085 | 0.093 | 0.080 | 0.116 | 0.116 | 0.097 | 0.080 |
| 26,000 | 0.119 | 0.110 | 0.204 | 0.195 | 0.199 | 0.204 | 0.165 | 0.110 |
| 27,000 | 0.170 | 0.190 | | | | 0.190 | 0.180 | 0.170 |
| Pressure at Failure (psi) | 27,900 | 27,700 | 26,300 | 26,500 | 26,700 | 27,900 | 27,020 | 26,300 |

Table G-28. Test Data on 1-Inch-Diameter, 150° Windows With t/D Ratio of 0.125, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 136 | 137 | 138 | 139 | 140 | | | |
| Thickness, t (in.) | 0.125 | 0.127 | 0.126 | 0.131 | 0.123 | 0.131 | 0.126 | 0.123 |
| Temperature (°F) | 65.5 | 61.9 | 66.5 | 67.1 | 69.1 | 69.1 | 66.0 | 61.9 |
| Pressurization Rate (psi/min) | 440 | 237 | 500 | 464 | 268 | 500 | 382 | 237 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| — | ←—————(All failed at pressures below 1,000 psi)—————→ | | | | | | | |
| Pressure at Failure (psi) | 550 | 575 | 600 | 650 | 525 | 650 | 580 | 525 |

Table G-29. Test Data on 1-Inch-Diameter, 150° Windows With t/D Ratio of 0.25, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 141 | 142 | 143 | 144 | 145 | | | |
| Thickness, t (in.) | 0.245 | 0.240 | 0.244 | 0.248 | 0.249 | 0.249 | 0.245 | 0.240 |
| Temperature (°F) | 68.1 | 68.4 | 69.1 | 69.0 | 68.1 | 69.1 | 68.5 | 68.1 |
| Pressurization Rate (psi/min) | 672 | 664 | 667 | 635 | 618 | 672 | 651 | 618 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.003 | 0.004 | 0.002 | 0.002 | 0.003 | 0.004 | 0.003 | 0.002 |
| 2,000 | 0.005 | 0.007 | 0.005 | 0.004 | 0.005 | 0.007 | 0.005 | 0.004 |
| 3,000 | 0.007 | 0.013 | 0.012 | 0.011 | 0.009 | 0.013 | 0.010 | 0.007 |
| 4,000 | 0.011 | 0.047 | 0.023 | | | 0.047 | 0.027 | 0.011 |
| 5,000 | 0.024 | | | | | | | |
| Pressure at Failure (psi) | 5,450 | 4,550 | 4,750 | 3,950 | 3,800 | 5,450 | 4,500 | 3,800 |

Table G-30. Test Data on 1-Inch-Diameter, 150° Windows With
t/D Ratio of 0.375, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 146 | 147 | 148 | 149 | 150 | | | |
| Thickness, t (in.) | 0.360 | 0.375 | 0.343 | 0.357 | 0.335 | 0.375 | 0.354 | 0.335 |
| Temperature (°F) | 66.5 | 67.9 | 67.5 | 67.6 | 67.6 | 67.9 | 67.4 | 66.5 |
| Pressurization Rate (psi/min) | 663 | 652 | 678 | 669 | 667 | 678 | 666 | 652 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.001 | 0.002 | 0.002 | 0.001 | 0.001 | 0.002 | 0.001 | 0.001 |
| 2,000 | 0.002 | 0.004 | 0.004 | 0.003 | 0.002 | 0.004 | 0.003 | 0.002 |
| 3,000 | 0.003 | 0.006 | 0.006 | 0.004 | 0.004 | 0.006 | 0.005 | 0.003 |
| 4,000 | 0.005 | 0.007 | 0.007 | 0.007 | 0.007 | 0.007 | 0.007 | 0.005 |
| 5,000 | 0.006 | 0.009 | 0.009 | 0.009 | 0.009 | 0.009 | 0.008 | 0.006 |
| 6,000 | 0.008 | 0.010 | 0.011 | 0.010 | 0.012 | 0.012 | 0.010 | 0.008 |
| 7,000 | 0.011 | 0.012 | 0.013 | 0.013 | 0.016 | 0.016 | 0.013 | 0.011 |
| 8,000 | 0.013 | 0.013 | 0.018 | 0.015 | 0.019 | 0.019 | 0.016 | 0.013 |
| 9,000 | 0.015 | 0.029 | 0.034 | 0.018 | 0.027 | 0.034 | 0.025 | 0.015 |
| 10,000 | 0.018 | 0.031 | 0.049 | 0.024 | 0.059 | 0.059 | 0.036 | 0.018 |
| 11,000 | 0.032 | 0.040 | | 0.038 | | 0.040 | 0.037 | 0.032 |
| 12,000 | | 0.061 | | | | 0.061 | 0.061 | 0.061 |
| Pressure at Failure (psi) | 11,500 | 12,525 | 10,550 | 11,300 | 10,100 | 12,525 | 11,195 | 10,100 |

Table G-31. Test Data on 1-Inch-Diameter, 150° Windows With
t/D Ratio of 0.5, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 151 | 152 | 153 | 154 | 155 | | | |
| Thickness, t (in.) | 0.465 | 0.461 | 0.468 | 0.467 | 0.467 | 0.468 | 0.466 | 0.461 |
| Temperature (°F) | 67.9 | 67.2 | 68.2 | 68.1 | 67.4 | 68.2 | 67.8 | 67.2 |
| Pressurization Rate (psi/min) | 667 | 665 | 659 | 663 | 669 | 669 | 665 | 659 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.001 | 0.001 | 0.001 | 0.001 | 0.002 | 0.002 | 0.001 | 0.001 |
| 2,000 | 0.002 | 0.003 | 0.002 | 0.003 | 0.003 | 0.003 | 0.003 | 0.002 |
| 3,000 | 0.003 | 0.004 | 0.003 | 0.004 | 0.004 | 0.004 | 0.004 | 0.003 |
| 4,000 | 0.004 | 0.005 | 0.005 | 0.005 | 0.006 | 0.006 | 0.005 | 0.004 |
| 5,000 | 0.005 | 0.006 | 0.006 | 0.007 | 0.007 | 0.007 | 0.006 | 0.005 |
| 6,000 | 0.007 | 0.007 | 0.006 | 0.008 | 0.008 | 0.008 | 0.007 | 0.006 |
| 7,000 | 0.008 | 0.008 | 0.008 | 0.010 | 0.009 | 0.010 | 0.009 | 0.008 |
| 8,000 | 0.009 | 0.009 | 0.011 | 0.011 | 0.010 | 0.011 | 0.010 | 0.009 |
| 9,000 | 0.010 | 0.010 | 0.013 | 0.013 | 0.011 | 0.013 | 0.011 | 0.010 |
| 10,000 | 0.011 | 0.011 | 0.018 | 0.015 | 0.013 | 0.018 | 0.014 | 0.011 |
| 11,000 | 0.012 | 0.013 | 0.021 | 0.016 | 0.014 | 0.021 | 0.015 | 0.012 |
| 12,000 | 0.015 | 0.015 | 0.027 | 0.019 | 0.016 | 0.027 | 0.018 | 0.015 |
| 13,000 | 0.017 | 0.017 | 0.031 | 0.040 | 0.018 | 0.031 | 0.025 | 0.017 |
| 14,000 | 0.027 | 0.020 | 0.042 | 0.043 | 0.021 | 0.043 | 0.031 | 0.020 |
| 15,000 | 0.030 | 0.022 | 0.048 | 0.045 | 0.023 | 0.048 | 0.034 | 0.022 |
| 16,000 | 0.046 | 0.026 | 0.064 | 0.065 | 0.026 | 0.065 | 0.045 | 0.026 |
| 17,000 | 0.070 | 0.034 | 0.095 | 0.091 | 0.030 | 0.095 | 0.064 | 0.030 |
| 18,000 | 0.150 | | | | 0.056 | 0.150 | 0.103 | 0.056 |
| Pressure at Failure (psi) | 18,100 | 17,600 | 17,550 | 17,650 | 18,150 | 18,150 | 17,810 | 17,550 |

Table G-32. Test Data on 1-Inch-Diameter, 150° Windows With t/D Ratio of 0.5, in DOL Type I Flange: Sample Group Size Validation Tests

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|--------|--------|--------|--------|---------------|---------------|---------------|
| | 156 | 157 | 158 | 159 | 160 | | | |
| Thickness, t (in.) | 0.498 | 0.485 | 0.498 | 0.504 | 0.500 | 0.504 | 0.497 | 0.485 |
| Temperature (°F) | 65.8 | 69.1 | 67.9 | 66.1 | 68.5 | 69.1 | 67.5 | 65.8 |
| Pressurization Rate (psi/min) | 662 | 661 | 642 | 672 | 656 | 672 | 659 | 642 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.003 | 0.001 | 0.003 | 0.002 | 0.002 | 0.003 | 0.002 | 0.001 |
| 2,000 | 0.004 | 0.002 | 0.004 | 0.003 | 0.0035 | 0.004 | 0.003 | 0.002 |
| 3,000 | 0.005 | 0.003 | 0.006 | 0.004 | 0.005 | 0.006 | 0.0045 | 0.003 |
| 4,000 | 0.006 | 0.0035 | 0.007 | 0.005 | 0.006 | 0.007 | 0.005 | 0.0035 |
| 5,000 | 0.007 | 0.004 | 0.008 | 0.006 | 0.007 | 0.008 | 0.006 | 0.004 |
| 6,000 | 0.008 | 0.011 | 0.009 | 0.007 | 0.008 | 0.011 | 0.009 | 0.007 |
| 7,000 | 0.009 | 0.012 | 0.010 | 0.008 | 0.009 | 0.012 | 0.010 | 0.008 |
| 8,000 | 0.0095 | 0.018 | 0.012 | 0.0085 | 0.012 | 0.018 | 0.012 | 0.0085 |
| 9,000 | 0.021 | 0.020 | 0.013 | 0.009 | 0.013 | 0.021 | 0.015 | 0.009 |
| 10,000 | 0.022 | 0.022 | 0.014 | 0.010 | 0.022 | 0.022 | 0.018 | 0.010 |
| 11,000 | 0.023 | 0.028 | 0.016 | 0.011 | 0.024 | 0.028 | 0.020 | 0.011 |
| 12,000 | 0.024 | 0.035 | 0.016 | 0.012 | 0.025 | 0.035 | 0.022 | 0.012 |
| 13,000 | 0.035 | 0.036 | 0.018 | 0.013 | 0.032 | 0.036 | 0.027 | 0.013 |
| 14,000 | 0.036 | 0.043 | 0.019 | 0.015 | 0.038 | 0.043 | 0.030 | 0.015 |
| 15,000 | 0.037 | 0.049 | 0.021 | 0.016 | 0.039 | 0.049 | 0.032 | 0.016 |
| 16,000 | 0.045 | 0.065 | 0.058 | 0.018 | 0.043 | 0.065 | 0.046 | 0.018 |
| 17,000 | 0.047 | 0.066 | 0.061 | 0.020 | 0.050 | 0.066 | 0.049 | 0.020 |
| 18,000 | 0.056 | 0.082 | 0.064 | 0.022 | 0.056 | 0.082 | 0.056 | 0.022 |
| 19,000 | 0.064 | 0.125 | 0.089 | 0.025 | 0.066 | 0.125 | 0.074 | 0.025 |
| 20,000 | 0.092 | | 0.150 | 0.034 | 0.105 | 0.150 | 0.095 | 0.034 |
| 21,000 | 0.153 | | | 0.150 | | 0.153 | 0.1515 | 0.150 |
| Pressure at Failure (psi) | 21,200 | 19,550 | 20,200 | 21,000 | 20,750 | 21,200 | 20,540 | 19,550 |

Table G-33. Test Data on 1-Inch-Diameter, 150° Windows With
t/D Ratio of 0.625, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 161 | 162 | 163 | 164 | 165 | | | |
| Thickness, t (in.) | 0.602 | 0.602 | 0.606 | 0.596 | 0.589 | 0.606 | 0.599 | 0.589 |
| Temperature (°F) | 67.7 | 69.0 | 66.0 | 70.4 | 68.4 | 70.4 | 68.3 | 66.0 |
| Pressurization Rate (psi/min) | 664 | 662 | 504 | 653 | 603 | 664 | 617 | 504 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.002 | 0.005 | 0.004 | 0.002 | 0.003 | 0.005 | 0.0032 | 0.002 |
| 2,000 | 0.008 | 0.006 | 0.005 | 0.004 | 0.004 | 0.008 | 0.005 | 0.004 |
| 3,000 | 0.009 | 0.007 | 0.006 | 0.006 | 0.005 | 0.009 | 0.0066 | 0.005 |
| 4,000 | 0.010 | 0.008 | 0.007 | 0.007 | 0.006 | 0.010 | 0.0076 | 0.006 |
| 5,000 | 0.011 | 0.009 | 0.0085 | 0.008 | 0.007 | 0.011 | 0.0087 | 0.007 |
| 6,000 | 0.0115 | 0.010 | 0.0095 | 0.010 | 0.008 | 0.0115 | 0.0098 | 0.008 |
| 7,000 | 0.012 | 0.011 | 0.010 | 0.011 | 0.010 | 0.012 | 0.0108 | 0.010 |
| 8,000 | 0.013 | 0.012 | 0.012 | 0.012 | 0.011 | 0.013 | 0.012 | 0.011 |
| 9,000 | 0.014 | 0.013 | 0.013 | 0.013 | 0.011 | 0.014 | 0.013 | 0.011 |
| 10,000 | 0.014 | 0.014 | 0.0145 | 0.015 | 0.012 | 0.015 | 0.014 | 0.012 |
| 11,000 | 0.015 | 0.015 | 0.015 | 0.020 | 0.013 | 0.020 | 0.0156 | 0.013 |
| 12,000 | 0.016 | 0.016 | 0.0165 | 0.024 | 0.014 | 0.024 | 0.0173 | 0.014 |
| 13,000 | 0.017 | 0.017 | 0.018 | 0.026 | 0.015 | 0.026 | 0.0186 | 0.015 |
| 14,000 | 0.0175 | 0.018 | 0.0195 | 0.031 | 0.016 | 0.031 | 0.0204 | 0.016 |
| 15,000 | 0.018 | 0.020 | 0.0205 | 0.035 | 0.017 | 0.035 | 0.022 | 0.017 |
| 16,000 | 0.019 | 0.021 | 0.022 | 0.039 | 0.025 | 0.039 | 0.025 | 0.019 |
| 17,000 | 0.020 | 0.022 | 0.024 | 0.043 | 0.025 | 0.043 | 0.027 | 0.020 |
| 18,000 | 0.022 | 0.024 | 0.025 | 0.049 | 0.026 | 0.049 | 0.029 | 0.022 |
| 19,000 | 0.0245 | 0.025 | 0.027 | 0.055 | 0.032 | 0.055 | 0.035 | 0.0245 |
| 20,000 | 0.027 | 0.028 | 0.029 | 0.062 | 0.033 | 0.062 | 0.036 | 0.027 |
| 21,000 | 0.030 | 0.029 | 0.031 | 0.072 | 0.037 | 0.072 | 0.040 | 0.029 |
| 22,000 | 0.032 | 0.032 | 0.051 | 0.081 | 0.048 | 0.081 | 0.049 | 0.032 |
| 23,000 | 0.035 | 0.035 | 0.053 | 0.097 | 0.054 | 0.097 | 0.055 | 0.035 |
| 24,000 | 0.038 | 0.076 | 0.068 | 0.145 | 0.077 | 0.145 | 0.081 | 0.038 |
| 25,000 | 0.042 | 0.085 | 0.120 | | | 0.120 | 0.082 | 0.042 |
| 26,000 | 0.066 | 0.125 | 0.280 | | | 0.280 | 0.157 | 0.066 |
| 27,000 | 0.110 | | | | | 0.110 | 0.110 | 0.110 |
| Pressure at Failure (psi) | 27,500 | 26,850 | 26,150 | 24,800 | 24,700 | 27,500 | 26,000 | 24,700 |

Table G-34. Test Data on 2-Inch-Diameter, 30° Windows With
t/D Ratio of 0.125, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|-------|-------|-------|-------|------------------|------------------|------------------|
| | 166 | 167 | 168 | 169 | 170 | | | |
| Thickness, t (in.) | 0.244 | 0.254 | 0.257 | 0.265 | 0.264 | 0.265 | 0.257 | 0.244 |
| Temperature (°F) | 70.8 | 70.1 | 69.7 | 69.4 | 69.8 | 70.8 | 69.9 | 69.4 |
| Pressurization Rate (psi/min) | 697 | 570 | 687 | 517 | 662 | 697 | 627 | 517 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 250 | 0.007 | 0.005 | 0.007 | 0.007 | 0.007 | 0.007 | 0.007 | 0.005 |
| 500 | 0.018 | 0.013 | 0.015 | 0.014 | 0.014 | 0.018 | 0.015 | 0.013 |
| 750 | 0.050 | 0.040 | 0.028 | 0.025 | 0.026 | 0.050 | 0.034 | 0.025 |
| Pressure at Failure (psi) | 850 | 850 | 900 | 900 | 900 | 900 | 880 | 850 |

Table G-35. Test Data on 2-Inch-Diameter, 30° Windows With
t/D Ratio of 0.25, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|-------|-------|-------|-------|------------------|------------------|------------------|
| | 171 | 172 | 173 | 174 | 175 | | | |
| Thickness, t (in.) | 0.490 | 0.485 | 0.490 | 0.485 | 0.485 | 0.490 | 0.487 | 0.485 |
| Temperature (°F) | 70.0 | 69.1 | 69.2 | 70.5 | 69.5 | 70.5 | 69.7 | 69.1 |
| Pressurization Rate (psi/min) | 658 | 604 | 659 | 679 | 655 | 679 | 651 | 604 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 250 | 0.002 | 0.002 | 0.002 | 0.002 | 0.002 | 0.002 | 0.002 | 0.002 |
| 500 | 0.005 | | 0.005 | 0.005 | 0.005 | 0.005 | 0.005 | 0.005 |
| 750 | 0.008 | | 0.007 | 0.009 | 0.007 | 0.009 | 0.008 | 0.007 |
| 1,000 | 0.010 | 0.009 | 0.009 | 0.012 | 0.009 | 0.012 | 0.010 | 0.009 |
| 1,250 | 0.013 | 0.012 | 0.011 | 0.015 | 0.012 | 0.015 | 0.013 | 0.011 |
| 1,500 | 0.017 | 0.015 | 0.015 | 0.018 | 0.016 | 0.018 | 0.016 | 0.015 |
| 1,750 | 0.020 | 0.018 | 0.018 | 0.022 | 0.019 | 0.022 | 0.019 | 0.018 |
| 2,000 | 0.024 | 0.021 | 0.021 | 0.028 | 0.023 | 0.028 | 0.023 | 0.021 |
| 2,250 | 0.028 | 0.025 | 0.032 | 0.033 | 0.028 | 0.033 | 0.029 | 0.025 |
| 2,500 | 0.032 | 0.031 | 0.045 | 0.040 | 0.033 | 0.045 | 0.036 | 0.031 |
| 2,750 | 0.060 | 0.070 | 0.070 | 0.046 | 0.039 | 0.070 | 0.057 | 0.039 |
| 3,000 | 0.110 | 0.110 | 0.110 | 0.070 | 0.075 | 0.110 | 0.095 | 0.070 |
| Pressure at Failure (psi) | 3,225 | 3,175 | 3,250 | 3,250 | 3,275 | 3,275 | 3,235 | 3,175 |

Table G-36. Test Data on 2-Inch-Diameter, 30° Windows With t/D Ratio of 0.5, in DOL Type I Flange: t/D Ratio Validation Tests

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 176 | 177 | 178 | 179 | 180 | | | |
| Thickness, t (in.) | 0.957 | 0.954 | 0.954 | 0.971 | 0.965 | 0.971 | 0.960 | 0.954 |
| Temperature (°F) | 64.5 | 67 | 64.5 | 62.8 | 68 | 68 | 65.4 | 62.8 |
| Pressurization Rate (psi/min) | 435 | 657 | 663 | 613 | 657 | | | |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.005 | 0.011 | 0.008 | 0.007 | 0.011 | 0.011 | 0.008 | 0.005 |
| 2,000 | 0.013 | 0.028 | 0.019 | 0.012 | 0.029 | 0.029 | 0.020 | 0.012 |
| 3,000 | 0.021 | 0.048 | 0.037 | 0.025 | 0.050 | 0.050 | 0.036 | 0.021 |
| 4,000 | 0.050 | 0.076 | 0.061 | 0.048 | 0.075 | 0.076 | 0.062 | 0.048 |
| 5,000 | 0.078 | 0.104 | 0.091 | 0.074 | 0.105 | 0.105 | 0.090 | 0.074 |
| 6,000 | 0.118 | 0.151 | 0.128 | 0.110 | 0.154 | 0.154 | 0.132 | 0.110 |
| 7,000 | 0.200 | 0.249 | 0.207 | 0.189 | 0.250 | 0.250 | 0.219 | 0.189 |
| 8,000 | 0.450 | | | | | | | |
| Pressure at Failure (psi) | 8,100 | 7,400 | 7,450 | 7,900 | 7,300 | 8,100 | 7,630 | 7,300 |

Table G-37. Test Data on 2-Inch-Diameter, 30° Windows With
t/D Ratio of 1.0, in DOL Type II Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|----------------------------------|--|--------|--------|--------|--------|------------------|------------------|------------------|
| | 181 | 182 | 183 | 184 | 185 | | | |
| Thickness, t (in.) | 2.008 | 0.981 | 1.981 | 1.993 | 2.001 | 2.008 | 1.993 | 1.981 |
| Temperature (°F) | 67 | 70 | 71 | 66 | 65 | 71 | 67.8 | 65 |
| Pressurization Rate (psi/min) | 658 | 655 | 666 | 655 | 661 | 666 | 659 | 655 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.004 | 0.005 | 0.003 | 0.004 | 0.004 | 0.005 | 0.004 | 0.003 |
| 2,000 | 0.008 | 0.015 | 0.007 | 0.018 | 0.024 | 0.024 | 0.0144 | 0.007 |
| 3,000 | 0.013 | 0.027 | 0.042 | 0.046 | 0.034 | 0.046 | 0.0324 | 0.013 |
| 4,000 | 0.021 | 0.039 | 0.045 | 0.041 | 0.044 | 0.045 | 0.0380 | 0.021 |
| 5,000 | 0.034 | 0.051 | 0.073 | 0.057 | 0.061 | 0.073 | 0.0552 | 0.034 |
| 6,000 | 0.045 | 0.065 | 0.076 | 0.072 | 0.073 | 0.076 | 0.0662 | 0.045 |
| 7,000 | 0.059 | 0.082 | 0.099 | 0.088 | 0.092 | 0.099 | 0.0840 | 0.059 |
| 8,000 | 0.074 | 0.099 | 0.104 | 0.103 | 0.109 | 0.109 | 0.0978 | 0.074 |
| 9,000 | 0.093 | 0.117 | 0.110 | 0.118 | 0.124 | 0.118 | 0.1124 | 0.093 |
| 10,000 | 0.110 | 0.138 | 0.142 | 0.139 | 0.148 | 0.148 | 0.1354 | 0.110 |
| 11,000 | 0.133 | 0.165 | 0.156 | 0.168 | 0.171 | 0.171 | 0.1586 | 0.133 |
| 12,000 | 0.157 | 0.196 | 0.198 | 0.201 | 0.202 | 0.202 | 0.1908 | 0.157 |
| 13,000 | 0.190 | 0.240 | 0.234 | 0.228 | 0.240 | 0.240 | 0.2264 | 0.190 |
| 14,000 | 0.225 | 0.290 | 0.288 | 0.259 | 0.285 | 0.290 | 0.2694 | 0.225 |
| 15,000 | 0.267 | 0.335 | 0.334 | 0.299 | 0.325 | 0.335 | 0.3120 | 0.267 |
| 16,000 | 0.310 | 0.382 | 0.382 | 0.340 | 0.371 | 0.382 | 0.3570 | 0.310 |
| 17,000 | 0.349 | 0.429 | 0.442 | 0.379 | 0.425 | 0.442 | 0.4048 | 0.349 |
| 18,000 | 0.395 | 0.485 | 0.543 | 0.419 | 0.484 | 0.543 | 0.4652 | 0.395 |
| 19,000 | 0.440 | 0.570 | 0.675 | | 0.581 | 0.675 | 0.5665 | 0.440 |
| 20,000 | 0.508 | | | | 0.780 | 0.780 | 0.6440 | 0.508 |
| Pressure at Failure (psi) | 20,800 | 20,400 | 19,800 | 20,500 | 20,500 | 20,800 | 20,400 | 19,800 |

Table G-38. Test Data on 4.5-Inch-Diameter, 60° Windows With t/D Ratio of 0.125, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 186 | 187 | 188 | 189 | 190 | | | |
| Thickness, t (in.) | 0.555 | 0.550 | 0.555 | 0.550 | 0.555 | 0.555 | 0.553 | 0.550 |
| Temperature (°F) | 67 | 67 | 67 | 67 | 67.5 | 67.5 | 67.1 | 67 |
| Pressurization Rate (psi/min) | 655 | 621 | 578 | 708 | 533 | 708 | 619 | 533 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 250 | 0.010 | 0.011 | 0.018 | 0.015 | 0.032 | 0.032 | 0.017 | 0.010 |
| 500 | 0.044 | 0.042 | 0.055 | 0.050 | 0.078 | 0.078 | 0.054 | 0.042 |
| 750 | 0.088 | 0.090 | 0.095 | 0.090 | | 0.095 | 0.090 | 0.088 |
| Pressure at Failure (psi) | 950 | 925 | 1,000 | 850 | 650 | 1,000 | 875 | 650 |

Table G-39. Test Data on 4.5-Inch-Diameter, 60° Windows With t/D Ratio of 0.25, in DOL Type I Flange

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|-------|-------|-------|-------|---------------|---------------|---------------|
| | 191 | 192 | 193 | 194 | 195 | | | |
| Thickness, t (in.) | 1.114 | 1.119 | 1.134 | 1.135 | 1.159 | 1.159 | 1.132 | 1.114 |
| Temperature (°F) | 67.1 | 67.0 | 65.5 | 68.8 | 70.7 | 70.7 | 67.8 | 65.5 |
| Pressurization Rate (psi/min) | 609 | 651 | 639 | 633 | 637 | 651 | 634 | 609 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.022 | 0.013 | 0.015 | 0.014 | 0.014 | 0.022 | 0.016 | 0.013 |
| 2,000 | 0.052 | 0.044 | 0.042 | 0.040 | 0.044 | 0.052 | 0.044 | 0.040 |
| 3,000 | 0.089 | 0.079 | 0.078 | 0.072 | 0.080 | 0.089 | 0.080 | 0.072 |
| 4,000 | 0.136 | 0.130 | 0.128 | 0.121 | 0.132 | 0.136 | 0.129 | 0.121 |
| 5,000 | 0.208 | 0.212 | 0.201 | 0.195 | 0.197 | 0.212 | 0.203 | 0.195 |
| Pressure at Failure (psi) | 5,600 | 5,850 | 5,850 | 5,900 | 5,750 | 5,900 | 5,790 | 5,600 |

Table G-40. Test Data on 4.5-Inch-Diameter, 60° Windows With t/D Ratio of 0.5, in DOL Type I Flange: t/D Ratio Validation Tests

| | Specimen Number | | | | | Maximum Value | Average Value | Minimum Value |
|-------------------------------|--|--------|--------|--------|--------|---------------|---------------|---------------|
| | 196 | 197 | 198 | 199 | 200 | | | |
| Thickness, t (in.) | 2.270 | 2.250 | 2.240 | 2.348 | 2.250 | 2.348 | 2.272 | 2.240 |
| Temperature (°F) | 62.5 | 67.5 | 64 | 69.5 | 63.5 | 69.5 | 65.4 | 62.5 |
| Pressurization Rate (psi/min) | 456 | 211 | 325 | 628 | 625 | 211 | 628 | 449 |
| Pressure (psi) | Axial Displacement of Center Point on Window Low-Pressure Face (in.) | | | | | | | |
| 1,000 | 0.006 | 0.008 | 0.008 | 0.011 | 0.004 | 0.011 | 0.007 | 0.004 |
| 2,000 | 0.014 | 0.019 | 0.023 | 0.017 | 0.029 | 0.029 | 0.020 | 0.014 |
| 3,000 | 0.020 | 0.036 | 0.038 | 0.026 | 0.034 | 0.038 | 0.031 | 0.020 |
| 4,000 | 0.032 | 0.053 | 0.055 | 0.045 | 0.055 | 0.055 | 0.048 | 0.032 |
| 5,000 | 0.048 | 0.070 | 0.071 | 0.062 | 0.065 | 0.071 | 0.063 | 0.048 |
| 6,000 | 0.066 | 0.089 | 0.089 | 0.081 | 0.091 | 0.091 | 0.083 | 0.066 |
| 7,000 | 0.086 | 0.112 | 0.108 | 0.103 | 0.122 | 0.122 | 0.106 | 0.086 |
| 8,000 | 0.108 | 0.138 | 0.129 | 0.127 | 0.128 | 0.138 | 0.126 | 0.108 |
| 9,000 | 0.137 | 0.168 | 0.155 | 0.155 | 0.160 | 0.168 | 0.155 | 0.137 |
| 10,000 | 0.175 | 0.224 | 0.188 | 0.181 | 0.188 | 0.224 | 0.191 | 0.175 |
| 11,000 | 0.211 | 0.303 | 0.230 | 0.213 | 0.234 | 0.303 | 0.238 | 0.211 |
| 12,000 | 0.241 | 0.412 | 0.294 | 0.274 | 0.282 | 0.412 | 0.301 | 0.241 |
| 13,000 | 0.282 | | 0.436 | 0.337 | 0.363 | 0.436 | 0.354 | 0.282 |
| 14,000 | 0.341 | | 0.700 | 0.438 | 0.490 | 0.700 | 0.492 | 0.341 |
| 15,000 | 0.441 | | | | | | | |
| 16,000 | 0.730 | | | | | | | |
| Pressure at Failure (psi) | 16,000 | 12,500 | 14,100 | 14,650 | 14,650 | 16,000 | 14,380 | 12,500 |

REFERENCES

1. Auguste Piccard. Earth, sky and the sea. New York, Oxford University Press, 1956.
2. Ocean Research Equipment, Inc. Staff Report 04651: Pressure tests of Plexiglas windows of ALVIN submarine. Falmouth, Mass., April 1965.
3. Allied Research Associates, Inc. Report ARA-F-271-5: Photoelastic investigation of stress in a penetrated atmosphere - final report, by H. Hamilton and H. Becker. Concord, Mass., Dec. 1964.
4. U. S. Naval Civil Engineering Laboratory. Technical Note TN-755: The conversion of 16-inch projectiles to pressure vessels. Port Hueneme, Calif., Aug. 1965.

| | |
|---|---|
| <p>U. S. Naval Civil Engineering Laboratory WINDOW FOR EXTERNAL OR INTERNAL HYDROSTATIC PRESSURE VESSELS PART I - CONICAL ACRYLIC WINDOWS UNDER SHORT-TERM PRESSURE APPLICATION, by J. D. Stachiw and K. O. Gray TR-512 100 p. illus Jan 1967 Unclassified</p> | <p>U. S. Naval Civil Engineering Laboratory WINDOW FOR EXTERNAL OR INTERNAL HYDROSTATIC PRESSURE VESSELS PART I - CONICAL ACRYLIC WINDOWS UNDER SHORT-TERM PRESSURE APPLICATION, by J. D. Stachiw and K. O. Gray TR-512 100 p. illus Jan 1967 Unclassified</p> |
| <p>1. Undersea vessels 2. Conical acrylic windows I. Y-F015-01-07-001</p> | <p>1. Undersea vessels 2. Conical acrylic windows I. Y-F015-01-07-001</p> |
| <p>Conical acrylic windows for fixed ocean-floor structures were placed under short-term loading (pressurization from zero to failure at a fixed rate). The windows, of different thicknesses and different included conical angles, were subjected to various applied pressures, and their subsequent behavior was studied.</p> <p>Acrylic windows, in the form of truncated cones with included angles of 30°, 60°, 90°, 120°, and 150°, were tested to destruction at ambient room temperature by applying hydrostatic pressure to the base of the truncated cone at a continuous rate of 650 psi/min. The pressure at which the windows failed and the magnitude of displacement through the window mounting at different pressure levels were recorded. The ultimate strength of the conical windows (denoted by the critical pressure at which actual failure occurred) was found to be related both to thickness and included conical angle.</p> <p>Graphs are presented defining the relationships of critical pressure versus thickness-to-diameter ratio, and pressure versus magnitude of displacement for the windows.</p> <p>Nondimensional scaling factors for critical pressure and displacement applicable to large-diameter windows are discussed and presented in graphic form.</p> | <p>Conical acrylic windows for fixed ocean-floor structures were placed under short-term loading (pressurization from zero to failure at a fixed rate). The windows, of different thicknesses and different included conical angles, were subjected to various applied pressures, and their subsequent behavior was studied.</p> <p>Acrylic windows, in the form of truncated cones with included angles of 30°, 60°, 90°, 120°, and 150°, were tested to destruction at ambient room temperature by applying hydrostatic pressure to the base of the truncated cone at a continuous rate of 650 psi/min. The pressure at which the windows failed and the magnitude of displacement through the window mounting at different pressure levels were recorded. The ultimate strength of the conical windows (denoted by the critical pressure at which actual failure occurred) was found to be related both to thickness and included conical angle.</p> <p>Graphs are presented defining the relationships of critical pressure versus thickness-to-diameter ratio, and pressure versus magnitude of displacement for the windows.</p> <p>Nondimensional scaling factors for critical pressure and displacement applicable to large-diameter windows are discussed and presented in graphic form.</p> |
| <p>U. S. Naval Civil Engineering Laboratory WINDOW FOR EXTERNAL OR INTERNAL HYDROSTATIC PRESSURE VESSELS PART I - CONICAL ACRYLIC WINDOWS UNDER SHORT-TERM PRESSURE APPLICATION, by J. D. Stachiw and K. O. Gray TR-512 100 p. illus Jan 1967 Unclassified</p> | <p>U. S. Naval Civil Engineering Laboratory WINDOW FOR EXTERNAL OR INTERNAL HYDROSTATIC PRESSURE VESSELS PART I - CONICAL ACRYLIC WINDOWS UNDER SHORT-TERM PRESSURE APPLICATION, by J. D. Stachiw and K. O. Gray TR-512 100 p. illus Jan 1967 Unclassified</p> |
| <p>1. Undersea vessels 2. Conical acrylic windows I. Y-F015-01-07-001</p> | <p>1. Undersea vessels 2. Conical acrylic windows I. Y-F015-01-07-001</p> |
| <p>Conical acrylic windows for fixed ocean-floor structures were placed under short-term loading (pressurization from zero to failure at a fixed rate). The windows, of different thicknesses and different included conical angles, were subjected to various applied pressures, and their subsequent behavior was studied.</p> <p>Acrylic windows, in the form of truncated cones with included angles of 30°, 60°, 90°, 120°, and 150°, were tested to destruction at ambient room temperature by applying hydrostatic pressure to the base of the truncated cone at a continuous rate of 650 psi/min. The pressure at which the windows failed and the magnitude of displacement through the window mounting at different pressure levels were recorded. The ultimate strength of the conical windows (denoted by the critical pressure at which actual failure occurred) was found to be related both to thickness and included conical angle.</p> <p>Graphs are presented defining the relationships of critical pressure versus thickness-to-diameter ratio, and pressure versus magnitude of displacement for the windows.</p> <p>Nondimensional scaling factors for critical pressure and displacement applicable to large-diameter windows are discussed and presented in graphic form.</p> | <p>Conical acrylic windows for fixed ocean-floor structures were placed under short-term loading (pressurization from zero to failure at a fixed rate). The windows, of different thicknesses and different included conical angles, were subjected to various applied pressures, and their subsequent behavior was studied.</p> <p>Acrylic windows, in the form of truncated cones with included angles of 30°, 60°, 90°, 120°, and 150°, were tested to destruction at ambient room temperature by applying hydrostatic pressure to the base of the truncated cone at a continuous rate of 650 psi/min. The pressure at which the windows failed and the magnitude of displacement through the window mounting at different pressure levels were recorded. The ultimate strength of the conical windows (denoted by the critical pressure at which actual failure occurred) was found to be related both to thickness and included conical angle.</p> <p>Graphs are presented defining the relationships of critical pressure versus thickness-to-diameter ratio, and pressure versus magnitude of displacement for the windows.</p> <p>Nondimensional scaling factors for critical pressure and displacement applicable to large-diameter windows are discussed and presented in graphic form.</p> |

Unclassified

Security Classification

DOCUMENT CONTROL DATA - R&D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

| | | | |
|---|--|---|--|
| 1. ORIGINATING ACTIVITY (Corporate author) | | 2 a. REPORT SECURITY CLASSIFICATION | |
| U. S. Naval Civil Engineering Laboratory Port Hueneme, California | | Unclassified | |
| | | 2 b. GROUP | |
| 3. REPORT TITLE | | | |
| Window For External Or Internal Hydrostatic Pressure Vessels Part I — Conical Acrylic Windows Under Short-Term Pressure Application | | | |
| 4. DESCRIPTIVE NOTES (Type of report and inclusive dates) | | | |
| Not Final; August 1965 - June 1966 | | | |
| 5. AUTHOR(S) (Last name, first name, initial) | | | |
| Stachiw, J. D. Gray, K. O. | | | |
| 6. REPORT DATE | 7 a. TOTAL NO. OF PAGES | 7 b. NO. OF REFS | |
| January 1967 | 100 | 4 | |
| 8 a. CONTRACT OR GRANT NO. | 9 a. ORIGINATOR'S REPORT NUMBER(S) | | |
| b. PROJECT NO. Y-F015-01-07-001 | TR-512 | | |
| c. | 9 b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report) | | |
| d. | | | |
| 10. AVAILABILITY/LIMITATION NOTICES | | | |
| Distribution of this document is unlimited. Copies available at the Clearinghouse (CFSTI) \$3.00. | | | |
| 11. SUPPLEMENTARY NOTES | | 12. SPONSORING MILITARY ACTIVITY | |
| | | Naval Facilities Engineering Command Washington, D. C. | |
| 13. ABSTRACT | | | |
| <p>Conical acrylic windows for fixed ocean-floor structures were placed under short-term loading (pressurization from zero to failure at a fixed rate). The windows, of different thicknesses and different included conical angles, were subjected to various applied pressures, and their subsequent behavior was studied.</p> <p>Acrylic windows, in the form of truncated cones with included angles of 30°, 60°, 90°, 120°, and 150°, were tested to destruction at ambient room temperature by applying hydrostatic pressure to the base of the truncated cone at a continuous rate of 650 psi/min. The pressure at which the windows failed and the magnitude of displacement through the window mounting at different pressure levels were recorded. The ultimate strength of the conical windows (denoted by the critical pressure at which actual failure occurred) was found to be related both to thickness and included conical angle.</p> <p>Graphs are presented defining the relationships of critical pressure versus thickness-to-diameter ratio, and pressure versus magnitude of displacement for the windows.</p> <p>Nondimensional scaling factors for critical pressure and displacement applicable to large-diameter windows are discussed and presented in graphic form.</p> | | | |

Unclassified

Security Classification

| 14. KEY WORDS | LINK A | | LINK B | | LINK C | |
|--|--------|----|--------|----|--------|----|
| | ROLE | WT | ROLE | WT | ROLE | WT |
| Undersea habitation Conical acrylic windows Hydrostatic pressure Short-term loading Failures | | | | | | |

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, roles, and weights is optional.